


BASE-LINE ✓
(MAY-JUNE, 1971)

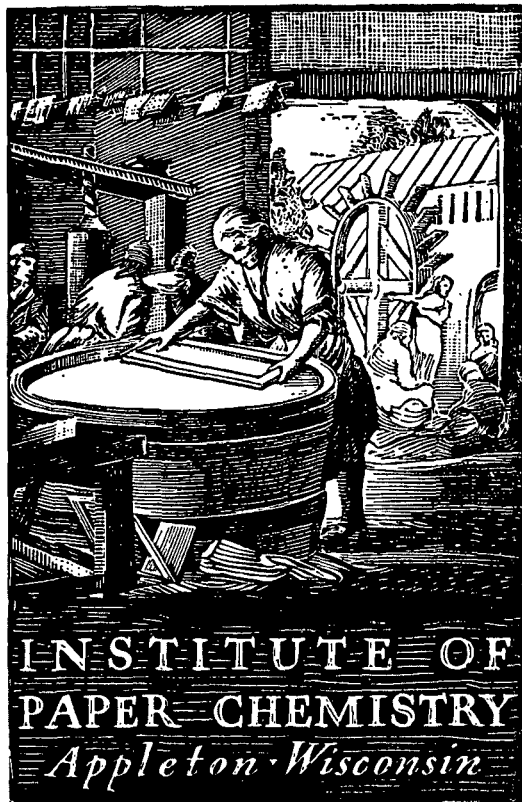

CONTINUOUS EVALUATION OF
CORRUGATING MEDIUM

(Data for May and June, 1971)

Project 2694-2

Report Twenty-Six

A Progress Report

to

FOURDRINIER KRAFT BOARD INSTITUTE, INC.

This material is intended only for the internal use of authorized
persons within Fourdrinier Kraft Board Institute member companies

July 23, 1971

BASE-LINE
(MAY-JUNE, 1971)

THE INSTITUTE OF PAPER CHEMISTRY

Appleton, Wisconsin

CONTINUOUS EVALUATION OF CORRUGATING MEDIUM

(Data for May and June, 1971)

Project 2694-2

Report Twenty-Six

A Progress Report

to

FOURDRINIER KRAFT BOARD INSTITUTE, INC.

This material is intended only for the internal use
of authorized persons within Fourdrinier Kraft Board
Institute member companies

July 23, 1971

TABLE OF CONTENTS

	Page
SUMMARY	1
INTRODUCTION	4
SUMMARY OF CURRENT MACHINE AVERAGES	6
SUMMARY OF TEST RESULTS FOR INDIVIDUAL MACHINES	8
DISCUSSION OF RESULTS	24

THE INSTITUTE OF PAPER CHEMISTRY

Appleton, Wisconsin

CONTINUOUS EVALUATION OF CORRUGATING MEDIUM
(DATA FOR MAY AND JUNE, 1971)

SUMMARY

PART I. GENERAL

A. Participation Data:

	Current Period	Previous Period
Period	May-June, 1971	March-April, 1971
Number of machines	31	32
Number of rolls	110	107

B. Distribution of Mediums by Type:

Semichemical	29	32
Bogus	2	0
Kraft	0	0

C. New Participants:

None

None

D. Nonparticipants

1. Continental Can (Hodge No. 1)	1. Crown Zellerbach (Baltimore Nos. 1 & 2)
2. Crown Zellerbach (Lebanon No. 2)	2. The Mead Corp. (Lynchburg No. 2)
3. International Paper (Bastrop No. 1)	3. Westvaco (Covington No. 7)
4. Westvaco (Covington No. 7)	
5. Weyerhaeuser (Longview No. 4)	

PART II. QUALITY DATA

A. Summary of Physical Test Data

Test	Report	Machine Averages		F.K.I. Averages	
		Max.	Min.	Current	Cumulative
Basis weight lb./1000 ft. ²	Cur.	28.4	25.1	26.7	26.7
	Prev.	28.5	25.6	26.8	26.7
Caliper, pt.	Cur.	11.2	8.8	10.1	10.1
	Prev.	11.0	9.0	10.2	10.1
Concora flat crush, p.s.i.	Cur.	48.6	37.1	41.8	42.2
	Prev.	54.0	36.8	43.2	42.0
Single-face flat crush, p.s.i.	Cur.	35.8	27.4	31.6	31.2
	Prev.	37.8	28.9	31.6	31.2

B. Summary of Runnability Data

Runnability		Current Period			Previous Period		
Speed, f.p.m.	Tension, lb./in.	No. of Rolls	% of Total	Cum., %	No. of Rolls	% of Total	Cum., %
<600	Min.	4	3.6	100.0	0	0.0	100.0
600	Min.	19	17.3	96.4	14	13.1	100.0
600	1/2	20	18.2	79.1	19	17.8	86.9
600	1	22	20.0	60.9	21	19.6	69.1
600	1-1/2	45	40.9	40.9	53	49.5	49.5

C. Trends in Quality Data in Current Report with Reference to Data from Previous Report

Physical Tests:

Basis weight: Decreased from 26.8 to 26.7 lb./M ft.²
 Caliper: Decreased from 10.2 to 10.1 pt.
 Concora flat crush: Decreased from 43.2 to 41.8 p.s.i.
 Single-face flat crush: Same as previous report.

Runnability:

<600 f.p.m. at minimum tension: Increased from 0.0 to 3.6%.
 600 f.p.m. at minimum tension: Increased from 13.1 to 17.3%.
 600 f.p.m. at 1/2 lb./in. tension: Increased from 17.8 to 18.2%.
 600 f.p.m. at 1 lb./in. tension: Increased from 19.6 to 20.0%.
 600 f.p.m. at 1-1/2 lb./in. tension: Decreased from 49.5 to 40.9%.

Comments: The current runnability is slightly lower than that of the previous period.

PART III. CONCORRA CALIBRATION DATA

A. Summary of Data (Number and Percentage of Machines Included Within the Indicated Ranges)

Range, %	Current Period		Previous Period	
	No. of Machines	% of Total	No. of Machines	% of Total
<u>± 1.0</u>	2	6.9	6	22.2
<u>± 2.5</u>	9	31.0	12	44.4
<u>± 5.0</u>	19	65.5	18	66.7
<u>±10.0</u>	29	100.0 ^a	25	92.6
<u>±12.5</u>			27	100.0 ^b

B. Significance of Calibration Data

The current level of agreement between Institute and mill Concorra flat crush data compares favorably with that of the previous report.

^aMaximum percentage difference was +9.1.

^bMaximum percentage difference was -11.6.

INTRODUCTION

As requested by the Technical Division of the Fourdrinier Kraft Board Institute, Inc., the reports pertinent to the continuous evaluation of corrugating medium have been prepared by The Institute of Paper Chemistry on a bimonthly instead of monthly basis since August, 1961. The current report summarizes the data obtained during May and June, 1971, on 110 rolls of corrugating medium submitted for evaluation from thirty-one machines.

Each roll was evaluated at the Institute for basis weight, caliper, Concora flat crush (tested immediately after fluting), H. and D. flat crush on single-faced board, and runnability. Runnability was evaluated by corrugating each roll under standardized conditions on the Institute's single-facer into A-flute board at 600 feet per minute with minimum tension and recording the draw factor at this speed and tension if the roll ran satisfactorily. If unsatisfactory runnability occurred at this speed and tension, the single-facer was slowed down in increments of 25 f.p.m. using minimum tension until satisfactory runnability was obtained, i.e., until there was no visual evidence of fractured flutes. In this latter case the draw factor was recorded for the highest speed below 600 f.p.m. (with minimum tension) at which the roll ran satisfactorily. On the other hand, if initial fabrication of the roll was satisfactory at 600 f.p.m. with minimum tension, further runs were made at 600 f.p.m. using higher tension to determine the maximum tension at 600 f.p.m. which the medium could sustain without visual evidence of fracturing. The higher tensions used at 600 f.p.m. were 0.5, 1.0, and 1.5 lb./inch. For each roll, flat crush was determined on the single-faced board obtained at a speed of 600 f.p.m. with minimum tension, or if the roll could not be corrugated satisfactorily at 600 f.p.m. with minimum tension, flat crush was determined on the single-faced board obtained at the highest speed below 600 f.p.m. at which the medium

could be corrugated with minimum tension. The flat crush results on the single-faced board, in addition to supplying information about quality, also provide data which may be useful to each participant as a means of evaluating the nature of the quantitative relationship between Concora flat crush and combined board flat crush for his medium.

For each participating machine, test data for the current period are shown in Table I. A tabulation of the number of rolls and type of medium evaluated is also given in Table I for each machine. The current machine test averages given in Table I are the means for each test property of the averages obtained on all rolls of corrugating medium evaluated from a given machine during the current period. In addition to the current machine test averages, Table I also presents current F.K.I. averages, cumulative F.K.I. averages, and F.K.I. indexes. The current F.K.I. average for each test property is the mean of the current machine averages for the same property for all machines participating in the study during a given period. The cumulative F.K.I. average for a given test property is the mean of the current F.K.I. averages for the same property for the previous twelve-month period excluding the average for the current period. The F.K.I. index for each test property is obtained as follows:

$$\frac{\text{current F.K.I. average}}{\text{cumulative F.K.I. average}} \times 100 = \text{F.K.I. index (\%)}$$

The F.K.I. index for each test property provides a convenient means of comparing current average quality with corresponding average quality for the previous six periods. An index greater than 100% indicates, of course, that current average quality is higher than the corresponding average quality for the previous six periods; similarly an index below 100% indicates that current average quality is lower than the corresponding average quality for the previous six periods.

TABLE I

SUMMARY OF CURRENT MACHINE AVERAGES

MAY AND JUNE, 1971

MILL CODE	NO. OF ROLLS	TYPE OF MEDIUM	BASIS WEIGHT, LB.	CALIPER, POINTS	CONCORA FLAT CRUSH, P.S.I.	SINGLE-FACE FLAT CRUSH, P.S.I.
A	4	SEMICHEMICAL	27.3	10.6	41.4	30.6
B	2	SEMICHEMICAL	27.4	9.2	48.6	35.8
C	5	SEMICHEMICAL	27.1	10.9	41.6	29.0
D	4	SEMICHEMICAL	27.4	10.3	43.3	32.3
E	4	SEMICHEMICAL	26.2	10.4	40.2	31.2
F	4	SEMICHEMICAL	26.6	11.1	39.5	30.4
G	4	SEMICHEMICAL	27.4	10.3	37.9	29.3
H	4	SEMICHEMICAL	27.4	8.8	42.7	33.5
I	2	SEMICHEMICAL	27.4	10.1	48.2	35.4
J	2	SEMICHEMICAL	26.2	10.1	42.8	31.0
K	4	SEMICHEMICAL	25.9	9.8	46.6	34.2
L	4	SEMICHEMICAL	27.7	10.2	38.7	30.2
M	4	SEMICHEMICAL	25.4	10.0	43.4	33.1
N	4	SEMICHEMICAL	26.3	10.7	39.3	29.8
O	4	SEMICHEMICAL	26.0	9.8	38.5	29.4
P	2	SEMICHEMICAL	25.8	10.4	42.8	31.2
Q	4	SEMICHEMICAL	25.1	10.0	44.5	32.6
R	5	SEMICHEMICAL	26.5	9.9	41.4	31.0
S	4	SEMICHEMICAL	26.6	11.2	42.8	32.7
T	4	SEMICHEMICAL	26.4	10.1	38.9	29.9
U	2	BOGUS	28.0	10.2	37.2	29.0
V	4	SEMICHEMICAL	26.6	9.9	40.9	30.7
W	2	SEMICHEMICAL	28.4	10.5	42.6	32.2
X	4	SEMICHEMICAL	26.8	10.2	42.2	31.2
Y	4	SEMICHEMICAL	26.8	10.5	40.8	32.0
Z	2	SEMICHEMICAL	27.4	9.6	41.9	33.3
AA	4	SEMICHEMICAL	26.2	9.7	40.0	30.9
BB	4	SEMICHEMICAL	26.0	9.1	43.8	32.3
CC	4	SEMICHEMICAL	27.4	8.8	45.4	34.3
DD	4	SEMICHEMICAL	25.8	10.1	42.0	33.2
EE	2	BOGUS	26.8	9.8	37.1	27.4

TOTAL 110

CURRENT F.K.I. AVERAGE	26.7	10.1	41.8	31.6
CUMULATIVE F.K.I. AVERAGE	26.7	10.1	42.2	31.2
F.K.I. INDEX, PERCENT	100.0	100.0	99.0	101.3

The test results obtained on the rolls submitted from the production of individual machines during the current period are shown in Tables II through XXXII for Machines A through Z and Machines AA, BB, CC, DD, and EE, respectively. For each machine, the maximum, minimum, and average results obtained on each roll are shown for all test properties except basis weight for which only the average is shown; in addition, the overall average result for all rolls submitted from a given machine is shown for each test property. The latter overall averages are reported as "current machine averages." A cumulative machine average for each test property is also shown and represents the mean of the current machine averages for the same property for the previous six periods (excluding the current period). Also shown for each machine and for each test property in Tables II to XXXII are a machine factor and machine index which are defined as follows:

$$\frac{\text{current machine average}}{\text{cumulative machine average}} \times 100 = \text{machine factor (\%)}$$

$$\frac{\text{current machine average}}{\text{cumulative F.K.I. average}} \times 100 = \text{machine index (\%)}$$

The machine factor and machine index provide a convenient means for comparing the current machine average for each test property with either the previous results obtained on the same machine for the same test property or with the cumulative result for all machines - i.e., the cumulative F.K.I. average for the same test property.

TABLE II

SUMMARY OF TEST RESULTS FOR MACHINE A

MAY AND JUNE, 1971

TYPE OF MEDIUM- SEMICHEMICAL

CODE	DATE MADE	MILL ROLL NO.	BASIS WT., LB./M. SQ. FT.	CALIPER, PT.			CONCORA FLAT CRUSH, P.S.I.			SINGLE-FACE FLAT CRUSH, P.S.I.			RUNNABILITY DRAW	
				MAX.	MIN.	AV.	MAX.	MIN.	AV.	MAX.	MIN.	AV.	LB./IN.*A	FACTOR*B
A-1	4-26-71	2180	27.6	11.0	10.9	11.0	44.4	39.0	42.2	31.0	29.8	30.7	0.5	1.554
A-2	4-27-71	2181	27.3	11.0	10.6	10.9	45.0	38.4	41.2	30.8	29.6	30.2	0.5	1.561
A-3	5-24-71	2188	27.3	10.5	10.0	10.2	47.4	33.6	42.4	31.8	30.2	31.1	MIN.	1.554
A-4	5-24-71	2189	27.0	10.7	10.2	10.5	43.2	36.0	39.6	31.0	29.8	30.5	MIN.	1.552
CURRENT MACHINE AVERAGE			27.3			10.6			41.4			30.6		1.555
CUMULATIVE MACHINE AVERAGE			27.3			10.5			41.5			29.7		
MACHINE FACTOR, PERCENT			100.0			101.0			99.8			103.0		
MACHINE INDEX, PERCENT			102.2			105.0			98.1			98.1		

A Maximum tension at 600 f.p.m.

B 600 f.p.m. minimum tension.

TABLE III

SUMMARY OF TEST RESULTS FOR MACHINE B

MAY AND JUNE, 1971

TYPE OF MEDIUM- SEMICHEMICAL

CODE	DATE MADE	MILL ROLL NO.	BASIS WT., LB./M. SQ. FT.	CALIPER, PT.			CONCORA FLAT CRUSH, P.S.I.			SINGLE-FACE FLAT CRUSH, P.S.I.			RUNNABILITY DRAW	
				MAX.	MIN.	AV.	MAX.	MIN.	AV.	MAX.	MIN.	AV.	LB./IN.*A	FACTOR*B
B-1	4-11-71	752	26.9	9.5	8.8	9.2	49.8	40.2	46.1	37.0	32.4	34.7	1.0	1.563
B-2	4-24-71	753	27.9	9.5	8.7	9.1	52.2	50.4	51.2	37.8	35.6	36.9	1.5	1.564
CURRENT MACHINE AVERAGE			27.4			9.2			48.6			35.8		1.564
CUMULATIVE MACHINE AVERAGE			27.0			9.6			48.4			36.4		
MACHINE FACTOR, PERCENT			101.5			95.8			100.4			98.4		
MACHINE INDEX, PERCENT			102.6			91.1			115.2			114.7		

TABLE IV

SUMMARY OF TEST RESULTS FOR MACHINE C

MAY AND JUNE, 1971

TYPE OF MEDIUM- SEMICHEMICAL

CODE	DATE MADE	MILL ROLL NO.	BASIS WT., LB./M. SQ. FT.	CALIPER, PT.			CONCORDA FLAT CRUSH, P.S.I.			SINGLE-FACE FLAT CRUSH, P.S.I.			RUNNABILITY LB./IN.*A	DRAW FACTOR*B
				MAX.	MIN.	AV.	MAX.	MIN.	AV.	MAX.	MIN.	AV.		
C-1	4-28-71	8672	26.9	11.2	10.8	10.9	41.4	38.4	39.5	27.4	26.2	26.8	1.5	1.566
C-2	4-28-71	8682	27.2	11.2	10.8	11.0	44.4	34.8	39.2	30.0	26.8	28.6	1.0	1.570
C-3	5- 8-71	3872	26.5	11.2	10.7	11.0	48.6	42.0	43.8	32.6	29.6	30.9	1.5	1.564
C-4	5-13-71	5962	26.6	10.8	10.2	10.7	46.8	39.6	41.9	30.8	27.8	29.3	1.5	1.570
C-5	6-14-71	7632	28.1	11.4	10.3	11.1	46.2	40.8	43.6	30.4	29.0	29.5	1.5	1.580
CURRENT MACHINE AVERAGE			27.1			10.9			41.6			29.0		1.570
CUMULATIVE MACHINE AVERAGE			27.2			11.5			41.6			28.9		
MACHINE FACTOR, PERCENT			99.6			94.8			100.0			100.3		
MACHINE INDEX, PERCENT			101.5			107.9			98.6			92.9		

TABLE V

SUMMARY OF TEST RESULTS FOR MACHINE D

MAY AND JUNE, 1971

TYPE OF MEDIUM- SEMICHEMICAL

CODE	DATE MADE	MILL ROLL NO.	BASIS WT., LB./M. SQ. FT.	CALIPER, PT.			CONCORDA FLAT CRUSH, P.S.I.			SINGLE-FACE FLAT CRUSH, P.S.I.			RUNNABILITY LB./IN.*A	DRAW FACTOR*B
				MAX.	MIN.	AV.	MAX.	MIN.	AV.	MAX.	MIN.	AV.		
D-1	5-10-71	279	27.1	10.4	10.0	10.2	46.2	40.2	43.7	33.6	31.8	32.5	0.5	1.552
D-2	5-13-71	280	27.1	10.5	9.8	10.1	44.4	39.6	42.1	32.2	29.8	31.0	MIN.	1.551
D-3	5-21-71	281	27.8	10.8	10.2	10.4	46.2	37.8	43.1	33.6	31.4	32.8	MIN.	1.559
D-4	5-27-71	282	27.6	10.9	10.1	10.5	46.8	42.6	44.4	34.2	31.6	32.8	0.5	1.559
CURRENT MACHINE AVERAGE			27.4			10.3			43.3			32.3		1.555
CUMULATIVE MACHINE AVERAGE			26.8			10.4			38.9			28.4		
MACHINE FACTOR, PERCENT			102.2			99.0			111.3			113.7		
MACHINE INDEX, PERCENT			102.6			102.0			102.6			103.5		

*See Table II for Notes A and B.

TABLE VI

SUMMARY OF TEST RESULTS FOR MACHINE E

MAY AND JUNE, 1971

TYPE OF MEDIUM- SEMICHEMICAL

CODE	DATE MADE	MILL ROLL NO.	BASIS WT., LB./M. SQ. FT.	CALIPER, PT.			CONCORA FLAT CRUSH, P.S.I.			SINGLE-FACE FLAT CRUSH, P.S.I.			RUNNABILITY	
				MAX.	MIN.	AV.	MAX.	MIN.	AV.	MAX.	MIN.	AV.	LB./IN.*A	DRAW FACTOR*B
E-1	4-30-71	4185-2	25.6	10.0	9.6	9.8	42.6	41.4	41.8	34.0	31.4	32.8	NOTE C	1.566
E-2	4-30-71	4185-5	25.5	10.3	9.7	10.0	40.8	36.6	39.1	32.6	30.4	31.6	NOTE C	1.578
E-3	6- 3-71	4836-2	26.9	11.6	10.2	10.8	41.4	37.8	39.5	31.4	29.4	30.7	MIN.	1.569
E-4	6- 3-71	4836-5	26.6	11.3	10.3	10.9	43.8	36.6	40.4	32.0	28.0	29.8	MIN.	1.565
CURRENT MACHINE AVERAGE			26.2			10.4			40.2			31.2		1.570
CUMULATIVE MACHINE AVERAGE			25.8			10.2			39.8			30.0		
MACHINE FACTOR, PERCENT			101.6			102.0			101.0			104.0		
MACHINE INDEX, PERCENT			98.1			103.0			95.3			100.0		

*See Table II for Notes A and B.

C Maximum speed at which this roll could be corrugated with minimum tension was 400 f.p.m.

TABLE VII

SUMMARY OF TEST RESULTS FOR MACHINE F

MAY AND JUNE, 1971

TYPE OF MEDIUM- SEMICHEMICAL

CODE	DATE MADE	MILL ROLL NO.	BASIS WT., LB./M. SQ. FT.	CALIPER, PT.			CONCORA FLAT CRUSH, P.S.I.			SINGLE-FACE FLAT CRUSH, P.S.I.			RUNNABILITY	
				MAX.	MIN.	AV.	MAX.	MIN.	AV.	MAX.	MIN.	AV.	LB./IN.*A	DRAW FACTOR*B
F-1	4- 4-71	401	26.8	11.3	10.8	11.1	43.2	36.6	40.3	32.2	29.8	31.1	MIN.	1.554
F-2	4-25-71	3200	26.9	11.3	11.0	11.1	41.4	36.0	38.8	30.2	29.2	29.7	MIN.	1.555
F-3	5- 5-71	1016	26.5	11.5	11.0	11.2	42.0	36.6	38.8	31.6	29.4	30.7	MIN.	1.551
F-4	5-26-71	3900	26.4	11.8	10.8	11.1	42.0	38.4	40.2	31.0	29.4	30.2	MIN.	1.555
CURRENT MACHINE AVERAGE			26.6			11.1			39.5			30.4		1.554
CUMULATIVE MACHINE AVERAGE			26.4			10.2			42.0			30.6		
MACHINE FACTOR, PERCENT			100.8			108.8			94.0			99.3		
MACHINE INDEX, PERCENT			99.6			109.9			93.6			97.4		

*See Table II for Notes A and B.

TABLE VIII

SUMMARY OF TEST RESULTS FOR MACHINE G
MAY AND JUNE, 1971

TYPE OF MEDIUM- SEMICHEMICAL

CODE	DATE MADE	MILL ROLL NO.	BASIS WT., LB./M. SQ. FT.	CALIPER, PT.			CONCORA FLAT CRUSH, P.S.I.			SINGLE-FACE FLAT CRUSH, P.S.I.			RUNNABILITY DRAW	
				MAX.	MIN.	AV.	MAX.	MIN.	AV.	MAX.	MIN.	AV.	LB./IN.*A	FACTOR*B
G-1	5- 3-71	4353	28.4	11.2	9.9	10.6	39.0	35.4	36.8	30.8	28.0	29.4	MIN.	1.550
G-2	5-14-71	4511	27.4	11.1	9.8	10.7	43.2	39.0	40.6	32.6	28.0	30.7	1.5	1.559
G-3	5-21-71	4353	26.0	10.8	9.8	10.2	41.4	36.0	38.0	29.8	29.0	29.6	1.0	1.560
G-4	6- 2-71	4591	27.7	10.1	9.6	9.8	39.6	32.4	36.1	28.8	26.8	27.5	1.5	1.569
CURRENT MACHINE AVERAGE			27.4			10.3			37.9			29.3		1.560
CUMULATIVE MACHINE AVERAGE			27.4			10.4			41.7			31.5		
MACHINE FACTOR, PERCENT			100.0			99.0			90.9			93.0		
MACHINE INDEX, PERCENT			102.6			102.0			89.8			93.9		

TABLE IX

SUMMARY OF TEST RESULTS FOR MACHINE H
MAY AND JUNE, 1971

TYPE OF MEDIUM- SEMICHEMICAL

CODE	DATE MADE	MILL ROLL NO.	BASIS WT., LB./M. SQ. FT.	CALIPER, PT.			CONCORA FLAT CRUSH, P.S.I.			SINGLE-FACE FLAT CRUSH, P.S.I.			RUNNABILITY DRAW	
				MAX.	MIN.	AV.	MAX.	MIN.	AV.	MAX.	MIN.	AV.	LB./IN.*A	FACTOR*B
H-1	4-27-71	338	27.8	9.0	8.2	8.8	44.4	39.0	42.0	33.8	31.8	33.0	1.5	1.574
H-2	4-29-71	339	27.8	9.1	8.8	8.9	46.8	42.6	44.8	35.6	34.8	35.3	1.0	1.567
H-3	5-20-71	342	26.8	8.9	8.1	8.6	48.0	40.8	44.5	34.6	33.0	33.8	MIN.	1.560
H-4	5-26-71	343	27.0	9.3	8.9	9.1	42.0	37.2	39.6	32.6	31.0	31.9	1.5	1.570
CURRENT MACHINE AVERAGE			27.4			8.8			42.7			33.5		1.568
CUMULATIVE MACHINE AVERAGE			27.4			9.3			44.6			33.8		
MACHINE FACTOR, PERCENT			100.0			94.6			95.7			99.1		
MACHINE INDEX, PERCENT			102.6			87.1			101.2			107.4		

*See Table II for Notes A and B.

TABLE X

SUMMARY OF TEST RESULTS FOR MACHINE I

MAY AND JUNE, 1971

TYPE OF MEDIUM- SEMICHEMICAL

CODE	DATE MADE	MILL ROLL NO.	BASIS WT., LB./M. SQ. FT.	CALIPER, PT.			CONCORDA FLAT CRUSH, P.S.I.			SINGLE-FACE FLAT CRUSH, P.S.I.			RUNNABILITY LB./IN.*A	DRAW FACTOR*B
				MAX.	MIN.	AV.	MAX.	MIN.	AV.	MAX.	MIN.	AV.		
I-1	4-14-71	1	27.4	10.2	10.0	10.1	52.2	44.4	49.1	36.8	35.2	36.0	1.5	1.575
I-2	4-14-71	2	27.4	10.3	9.9	10.1	50.4	45.0	47.3	37.8	32.8	34.7	1.5	1.578
CURRENT MACHINE AVERAGE			27.4			10.1			48.2			35.4		1.577
CUMULATIVE MACHINE AVERAGE			26.9			10.4			45.5			33.2		
MACHINE FACTOR, PERCENT			101.8			97.1			105.9			106.6		
MACHINE INDEX, PERCENT			102.6			100.0			114.2			113.5		

TABLE XI

SUMMARY OF TEST RESULTS FOR MACHINE J

MAY AND JUNE, 1971

TYPE OF MEDIUM- SEMICHEMICAL

CODE	DATE MADE	MILL ROLL NO.	BASIS WT., LB./M. SQ. FT.	CALIPER, PT.			CONCORDA FLAT CRUSH, P.S.I.			SINGLE-FACE FLAT CRUSH, P.S.I.			RUNNABILITY LB./IN.*A	DRAW FACTOR*B
				MAX.	MIN.	AV.	MAX.	MIN.	AV.	MAX.	MIN.	AV.		
J-1	5-14-71	683	25.8	10.2	9.9	10.1	47.4	42.0	43.7	34.8	31.4	32.9	1.5	1.565
J-2	5-25-71	684	26.6	10.3	9.9	10.1	45.0	38.4	41.8	31.6	27.8	29.1	1.0	1.566
CURRENT MACHINE AVERAGE			26.2			10.1			42.8			31.0		1.566
CUMULATIVE MACHINE AVERAGE			26.6			9.9			40.7			30.0		
MACHINE FACTOR, PERCENT			98.5			102.0			105.2			103.3		
MACHINE INDEX, PERCENT			98.1			100.0			101.4			99.4		

*See Table II for Notes A and B.

TABLE XII

SUMMARY OF TEST RESULTS FOR MACHINE K

MAY AND JUNE, 1971

TYPE OF MEDIUM- SEMICHEMICAL

CODE	DATE MADE	MILL ROLL NO.	BASIS WT., LB./M. SQ. FT.	CALIPER, PT.			CONCORA FLAT CRUSH, P.S.I.			SINGLE-FACE FLAT CRUSH, P.S.I.			RUNNABILITY	
				MAX.	MIN.	AV.	MAX.	MIN.	AV.	MAX.	MIN.	AV.	LB./IN.*A	DRAW FACTOR*8
K-1	6- 1-71		25.8	10.1	9.9	10.0	46.8	43.2	45.6	34.6	32.8	33.8	1.0	1.563
K-2	6- 2-71		25.9	10.3	9.7	10.0	48.0	43.8	45.8	35.2	32.6	33.8	1.0	1.563
K-3	6- 4-71		26.2	10.0	9.0	9.5	50.4	43.8	47.5	35.6	33.6	34.8	1.5	1.560
K-4	6- 5-71		25.7	10.0	9.3	9.8	49.8	45.6	47.6	35.6	32.6	34.2	0.5	1.563
CURRENT MACHINE AVERAGE			25.9			9.6			46.6			34.2		1.562
CUMULATIVE MACHINE AVERAGE			26.7			10.4			45.4			33.3		
MACHINE FACTOR, PERCENT			97.0			94.2			102.6			102.7		
MACHINE INDEX, PERCENT			97.0			97.0			110.4			109.6		

TABLE XIII

SUMMARY OF TEST RESULTS FOR MACHINE L

MAY AND JUNE, 1971

TYPE OF MEDIUM- SEMICHEMICAL

CODE	DATE MADE	MILL ROLL NO.	BASIS WT., LB./M. SQ. FT.	CALIPER, PT.			CONCORA FLAT CRUSH, P.S.I.			SINGLE-FACE FLAT CRUSH, P.S.I.			RUNNABILITY	
				MAX.	MIN.	AV.	MAX.	MIN.	AV.	MAX.	MIN.	AV.	LB./IN.*A	DRAW FACTOR*8
L-1	4-25-71	3392	27.6	11.0	10.2	10.5	44.4	37.2	40.1	32.0	30.0	30.8	1.5	1.572
L-2	5-15-71	3031	28.1	10.2	9.1	9.6	41.4	37.2	39.2	32.8	30.4	31.6	0.5	1.550
L-3	5-21-71	3442	28.0	10.8	10.2	10.4	41.4	36.6	39.1	32.0	29.6	30.2	1.5	1.565
L-4	6- 2-71	3042	27.0	10.5	9.8	10.2	38.4	34.8	36.5	29.2	27.6	28.3	1.5	1.576
CURRENT MACHINE AVERAGE			27.7			10.2			38.7			30.2		1.566
CUMULATIVE MACHINE AVERAGE			27.8			10.4			42.6			31.2		
MACHINE FACTOR, PERCENT			99.6			98.1			90.8			96.8		
MACHINE INDEX, PERCENT			103.7			101.0			91.7			96.8		

*See Table II for Notes A and B.

TABLE XIV

SUMMARY OF TEST RESULTS FOR MACHINE M

MAY AND JUNE, 1971

TYPE OF MEDIUM- SEMICHEMICAL

CODE	DATE MADE	MILL ROLL NO.	BASIS WT., LB./M. SQ. FT.	CALIPER, PT.			CONCORA FLAT CRUSH, P.S.I.			SINGLE-FACE FLAT CRUSH, P.S.I.			RUNNABILITY LB./IN.*A	DRAW FACTOR*B
				MAX.	MIN.	AV.	MAX.	MIN.	AV.	MAX.	MIN.	AV.		
M-1	3-16-71	9287	26.4	9.8	9.1	9.3	47.4	41.4	45.6	34.2	31.6	33.0	1.0	1.568
M-2	3-22-71	9467	24.3	10.9	9.9	10.3	43.8	41.4	43.0	33.2	31.6	32.4	0.5	1.560
M-3	3-30-71	9726	24.7	11.0	10.1	10.5	43.2	38.4	41.3	32.6	29.2	31.4	0.5	1.562
M-4	4- 4-71	9881	26.3	10.1	9.0	9.7	46.2	42.0	43.6	37.0	34.6	35.0	0.5	1.557
CURRENT MACHINE AVERAGE			25.4			10.0			43.4			33.1		1.562
CUMULATIVE MACHINE AVERAGE			26.0			10.2			44.4			33.9		
MACHINE FACTOR, PERCENT			97.7			98.0			97.7			97.6		
MACHINE INDEX, PERCENT			95.1			99.0			102.8			106.1		

TABLE XV

SUMMARY OF TEST RESULTS FOR MACHINE N

MAY AND JUNE, 1971

TYPE OF MEDIUM- SEMICHEMICAL

CODE	DATE MADE	MILL ROLL NO.	BASIS WT., LB./M. SQ. FT.	CALIPER, PT.			CONCORA FLAT CRUSH, P.S.I.			SINGLE-FACE FLAT CRUSH, P.S.I.			RUNNABILITY LB./IN.*A	DRAW FACTOR*B
				MAX.	MIN.	AV.	MAX.	MIN.	AV.	MAX.	MIN.	AV.		
N-1	4- 8-71	23	26.3	11.0	10.4	10.7	40.2	36.6	38.8	32.2	29.2	30.4	0.5	1.551
N-2	4-29-71	24	26.7	11.0	10.5	10.8	46.2	42.6	43.8	33.0	31.6	32.4	MIN.	1.557
N-3	5-19-71	25	26.0	12.0	10.7	11.2	41.4	33.0	36.2	28.8	27.2	28.1	MIN.	1.561
N-4	6- 7-71	27	26.1	10.3	9.8	10.1	39.6	36.6	38.3	30.4	26.8	28.1	MIN.	1.566
CURRENT MACHINE AVERAGE			26.3			10.7			39.3			29.8		1.559
CUMULATIVE MACHINE AVERAGE			26.6			11.2			39.1			29.9		
MACHINE FACTOR, PERCENT			98.9			95.5			100.5			99.7		
MACHINE INDEX, PERCENT			98.5			105.9			93.1			95.5		

*See Table II for Notes A and B.

TABLE XVI

SUMMARY OF TEST RESULTS FOR MACHINE D

MAY AND JUNE, 1971

TYPE OF MEDIUM- SEMICHEMICAL

CODE	DATE MADE	MILL ROLL NO.	BASIS WT., LB./M. SQ. FT.	CALIPER, PT.			CONCORA FLAT CRUSH, P.S.I.			SINGLE-FACE FLAT CRUSH, P.S.I.			RUNNABILITY LB./IN.*A	DRAW FACTOR*B
				MAX.	MIN.	AV.	MAX.	MIN.	AV.	MAX.	MIN.	AV.		
0-1	4-20-71	380	25.7	10.3	9.8	10.0	40.8	37.2	39.0	30.0	28.6	29.1	1.0	1.567
0-2	5- 1-71	381	26.0	10.9	9.8	10.2	37.8	33.6	36.5	30.2	26.8	28.9	1.0	1.561
0-3	5-16-71	382	26.3	10.2	9.2	9.8	42.0	33.0	37.1	31.2	29.0	29.6	0.5	1.562
0-4	6- 7-71	383	25.8	9.8	9.0	9.3	43.8	39.6	41.4	31.0	28.0	29.8	1.5	1.575
CURRENT MACHINE AVERAGE			26.0			9.8			38.5			29.4		1.566
CUMULATIVE MACHINE AVERAGE			26.6			9.8			40.8			30.3		
MACHINE FACTOR, PERCENT			97.7			100.0			94.4			97.0		
MACHINE INDEX, PERCENT			97.4			97.0			91.2			94.2		

TABLE XVII

SUMMARY OF TEST RESULTS FOR MACHINE P

MAY AND JUNE, 1971

TYPE OF MEDIUM- SEMICHEMICAL

CODE	DATE MADE	MILL ROLL NO.	BASIS WT., LB./M. SQ. FT.	CALIPER, PT.			CONCORA FLAT CRUSH, P.S.I.			SINGLE-FACE FLAT CRUSH, P.S.I.			RUNNABILITY LB./IN.*A	DRAW FACTOR*B
				MAX.	MIN.	AV.	MAX.	MIN.	AV.	MAX.	MIN.	AV.		
P-1	5-13-71	6132	25.5	10.8	9.4	10.3	45.6	40.8	43.0	31.6	29.4	30.1	1.5	1.565
P-2	5-13-71	6142	26.2	10.8	9.9	10.4	47.4	39.0	42.6	33.6	31.0	32.4	1.5	1.566
CURRENT MACHINE AVERAGE			25.8			10.4			42.8			31.2		1.566
CUMULATIVE MACHINE AVERAGE			26.4			10.6			41.1			30.1		
MACHINE FACTOR, PERCENT			97.7			98.1			104.1			103.6		
MACHINE INDEX, PERCENT			96.6			103.0			101.4			100.0		

*See Table II for Notes A and B.

TABLE XVIII

SUMMARY OF TEST RESULTS FOR MACHINE Q

MAY AND JUNE, 1971

TYPE OF MEDIUM- SEMICHEMICAL

CODE	DATE MADE	MILL ROLL NO.	BASIS WT., LB./M. SQ. FT.	CALIPER, PT.			CONCORA FLAT CRUSH, P.S.I.			SINGLE-FACE FLAT CRUSH, P.S.I.			RUNNABILITY LB./IN.*A	DRAW FACTOR*8
				MAX.	MIN.	AV.	MAX.	MIN.	AV.	MAX.	MIN.	AV.		
Q-1	4-14-71	619	24.6	10.2	8.9	9.8	50.4	42.6	45.6	34.6	30.0	31.8	0.5	1.555
Q-2	4-21-71	620	25.6	11.0	9.0	10.1	45.6	41.4	43.7	33.0	31.6	32.5	1.0	1.565
Q-3	4-27-71	621	25.1	10.1	8.8	9.6	49.2	42.0	45.0	34.2	31.0	32.5	1.0	1.564
Q-4	5-11-71	622	25.1	13.0	9.0	10.7	48.0	40.2	43.6	35.4	32.8	33.6	1.5	1.566
CURRENT MACHINE AVERAGE			25.1			10.0			44.5			32.6		1.563
CUMULATIVE MACHINE AVERAGE			25.9			10.0			47.7			35.3		
MACHINE FACTOR, PERCENT			96.9			100.0			93.3			92.4		
MACHINE INDEX, PERCENT			94.0			99.0			105.4			104.5		

TABLE XIX

SUMMARY OF TEST RESULTS FOR MACHINE R

MAY AND JUNE, 1971

TYPE OF MEDIUM- SEMICHEMICAL

CODE	DATE MADE	MILL ROLL NO.	BASIS WT., LB./M. SQ. FT.	CALIPER, PT.			CONCORA FLAT CRUSH, P.S.I.			SINGLE-FACE FLAT CRUSH, P.S.I.			RUNNABILITY LB./IN.*A	DRAW FACTOR*8
				MAX.	MIN.	AV.	MAX.	MIN.	AV.	MAX.	MIN.	AV.		
R-1	4-21-71	379	27.7	10.0	9.0	9.8	57.0	40.8	46.7	37.2	30.8	33.3	1.5	1.577
R-2	4-20-71	380	26.5	11.0	10.2	10.6	40.8	37.2	38.9	32.2	30.4	31.2	1.0	1.565
R-3	5-1-71	381	26.0	10.1	9.8	10.0	39.6	34.8	38.0	30.2	29.0	29.6	1.5	1.562
R-4	5-16-71	382	26.1	10.1	9.7	9.8	43.2	39.0	41.8	32.4	29.6	30.8	1.0	1.571
R-5	6-7-71	383	26.1	9.8	9.2	9.5	44.4	38.4	41.4	31.0	29.0	30.0	1.5	1.580
CURRENT MACHINE AVERAGE			26.5			9.9			41.4			31.0		1.571
CUMULATIVE MACHINE AVERAGE			26.6			10.0			39.3			29.2		
MACHINE FACTOR, PERCENT			99.6			99.0			105.3			106.2		
MACHINE INDEX, PERCENT			99.2			98.0			98.1			99.4		

*See Table II for Notes A and B.

TABLE XX

SUMMARY OF TEST RESULTS FOR MACHINE S

MAY AND JUNE, 1971

TYPE OF MEDIUM- SEMICHEMICAL

CODE	DATE MADE	MILL ROLL NO.	BASIS WT., LB./M. SQ. FT.	CALIPER, PT.			CONCORA FLAT CRUSH, P.S.I.			SINGLE-FACE FLAT CRUSH, P.S.I.			RUNNABILITY LB./IN.*A	DRAW FACTOR*8
				MAX.	MIN.	AV.	MAX.	MIN.	AV.	MAX.	MIN.	AV.		
S-1	4- 6-71	311	26.8	12.0	11.1	11.4	48.0	40.8	43.3	33.4	30.4	32.2	1.0	1.562
S-2	4-19-71	427	26.7	11.5	10.9	11.2	43.2	39.0	41.8	33.6	30.4	32.4	MIN.	1.553
S-3	5-15-71	1996	26.5	11.9	10.9	11.3	45.6	38.4	42.1	33.4	31.4	32.9	MIN.	1.556
S-4	5-27-71	2769	26.4	11.4	11.0	11.1	46.2	40.2	43.9	33.8	32.8	33.2	0.5	1.561
CURRENT MACHINE AVERAGE			26.6			11.2			42.8			32.7		1.558
CUMULATIVE MACHINE AVERAGE			26.6			10.2			42.0			31.4		
MACHINE FACTOR, PERCENT			100.0			109.8			101.9			104.1		
MACHINE INDEX, PERCENT			99.6			110.9			101.4			104.8		

TABLE XXI

SUMMARY OF TEST RESULTS FOR MACHINE T

MAY AND JUNE, 1971

TYPE OF MEDIUM- SEMICHEMICAL

CODE	DATE MADE	MILL ROLL NO.	BASIS WT., LB./M. SQ. FT.	CALIPER, PT.			CONCORA FLAT CRUSH, P.S.I.			SINGLE-FACE FLAT CRUSH, P.S.I.			RUNNABILITY LB./IN.*A	DRAW FACTOR*8
				MAX.	MIN.	AV.	MAX.	MIN.	AV.	MAX.	MIN.	AV.		
T-1	3-23-71	12	26.5	10.9	10.0	10.3	37.2	33.6	35.9	28.6	26.6	27.9	0.5	1.556
T-2	4-10-71	14	27.4	10.1	9.0	9.8	45.0	40.8	43.1	34.0	31.2	32.2	MIN.	1.552
T-3	4-21-71	16	26.0	10.9	9.9	10.2	40.8	37.2	38.8	32.4	29.4	31.5	0.5	1.560
T-4	5-21-71	18	25.5	10.4	9.6	10.0	39.6	36.6	37.9	30.2	26.8	28.0	0.5	1.567
CURRENT MACHINE AVERAGE			26.4			10.1			38.9			29.9		1.559
CUMULATIVE MACHINE AVERAGE			26.3			10.0			38.2			28.7		
MACHINE FACTOR, PERCENT			100.4			101.0			101.8			104.2		
MACHINE INDEX, PERCENT			98.9			100.0			92.2			95.8		

*See Table II for Notes A and B.

TABLE XXII

SUMMARY OF TEST RESULTS FOR MACHINE U

MAY AND JUNE, 1971

TYPE OF MEDIUM- BUGUS

CODE	DATE MADE	MILL ROLL NO.	BASIS WT., LB./M. SQ. FT.	CALIPER, PT.			CONCORA FLAT CRUSH, P.S.I.			SINGLE-FACE FLAT CRUSH, P.S.I.			RUNNABILITY	
				MAX.	MIN.	AV.	MAX.	MIN.	AV.	MAX.	MIN.	AV.	LB./IN.*A	DRAW FACTOR*B
U-1	4-15-71	534	27.8	11.3	9.4	10.1	40.8	36.0	37.7	31.4	30.6	31.0	1.5	1.569
U-2	6-11-71	535	28.2	10.6	9.8	10.2	39.0	34.8	36.8	27.8	25.0	26.9	1.5	1.578
CURRENT MACHINE AVERAGE			28.0			10.2			37.2			29.0		1.574
CUMULATIVE MACHINE AVERAGE			27.4			10.4			42.5			31.1		
MACHINE FACTOR, PERCENT			102.2			98.1			87.5			93.2		
MACHINE INDEX, PERCENT			104.9			101.0			88.2			92.9		

TABLE XXIII

SUMMARY OF TEST RESULTS FOR MACHINE V

MAY AND JUNE, 1971

TYPE OF MEDIUM- SEMICHEMICAL

CODE	DATE MADE	MILL ROLL NO.	BASIS WT., LB./M. SQ. FT.	CALIPER, PT.			CONCORA FLAT CRUSH, P.S.I.			SINGLE-FACE FLAT CRUSH, P.S.I.			RUNNABILITY	
				MAX.	MIN.	AV.	MAX.	MIN.	AV.	MAX.	MIN.	AV.	LB./IN.*A	DRAW FACTOR*B
V-1	5-11-71	225	26.7	10.5	9.5	10.1	45.0	37.8	41.3	31.4	29.4	30.6	1.5	1.579
V-2	5-20-71	226	26.8	10.7	9.7	10.2	41.4	37.2	39.5	32.2	29.4	31.2	1.5	1.582
V-3	6- 3-71	227	26.3	10.1	9.3	9.6	43.8	37.8	41.6	31.0	29.4	30.3	1.5	1.585
V-4	6-12-71	228	26.5	10.1	9.2	9.7	42.6	37.8	41.2	30.8	30.0	30.6	1.5	1.587
CURRENT MACHINE AVERAGE			26.6			9.9			40.9			30.7		1.583
CUMULATIVE MACHINE AVERAGE			26.8			9.9			42.2			30.1		
MACHINE FACTOR, PERCENT						100.0			96.9			102.0		
MACHINE INDEX, PERCENT			99.6			98.0			96.9			98.4		

*See Table II for Notes A and B.

TABLE XXIV

SUMMARY OF TEST RESULTS FOR MACHINE W

MAY AND JUNE, 1971

TYPE OF MEDIUM- SEMICHEMICAL

CODE	DATE MADE	MILL ROLL NO.	BASIS WT., LB./M. SQ. FT.	CALIPER, PT.			CONCORA FLAT CRUSH, P.S.I.			SINGLE-FACE FLAT CRUSH, P.S.I.			RUNNABILITY	
				MAX.	MIN.	AV.	MAX.	MIN.	AV.	MAX.	MIN.	AV.	LB./IN.*A	DRAW FACTOR*B
W-1	3-19-71		29.6	10.8	9.9	10.2	45.0	40.8	42.8	34.2	31.0	32.4	NOTE C	1.540
W-2	5- 9-71	5057	27.1	11.2	10.2	10.8	44.4	40.8	42.4	33.4	30.0	32.1	NOTE D	1.550
CURRENT MACHINE AVERAGE			28.4			10.5			42.6			32.2		1.545
CUMULATIVE MACHINE AVERAGE			27.2			10.6			42.5			32.9		
MACHINE FACTOR, PERCENT			104.4			99.0			100.2			97.9		
MACHINE INDEX, PERCENT			106.4			104.0			100.9			103.2		

*See Table II for Notes A and B.

C Maximum speed at which this roll could be corrugated with minimum tension was 225 f.p.m.

D Maximum speed at which this roll could be corrugated with minimum tension was 200 f.p.m.

TABLE XXV

SUMMARY OF TEST RESULTS FOR MACHINE X

MAY AND JUNE, 1971

TYPE OF MEDIUM- SEMICHEMICAL

CODE	DATE MADE	MILL ROLL NO.	BASIS WT., LB./M. SQ. FT.	CALIPER, PT.			CONCORA FLAT CRUSH, P.S.I.			SINGLE-FACE FLAT CRUSH, P.S.I.			RUNNABILITY	
				MAX.	MIN.	AV.	MAX.	MIN.	AV.	MAX.	MIN.	AV.	LB./IN.*A	DRAW FACTOR*B
X-1	5-31-71		26.8	10.2	9.8	10.0	45.6	40.8	42.7	33.6	31.8	32.4	0.5	1.566
X-2	6- 1-71		27.3	10.6	10.0	10.2	43.8	41.4	42.2	33.4	30.4	31.8	1.0	1.562
X-3	6- 8-71		26.6	10.6	10.0	10.3	45.6	35.4	41.2	32.2	30.4	31.4	1.5	1.578
X-4	6- 9-71		26.3	11.6	10.0	10.4	45.0	40.2	42.5	30.6	28.6	29.3	1.5	1.580
CURRENT MACHINE AVERAGE			26.8			10.2			42.2			31.2		1.572
CUMULATIVE MACHINE AVERAGE			26.7			10.3			43.8			31.6		
MACHINE FACTOR, PERCENT			100.4			99.0			96.3			98.7		
MACHINE INDEX, PERCENT			100.4			101.0			100.0			100.0		

*See Table II for Notes A and B.

TABLE XXVI

SUMMARY OF TEST RESULTS FOR MACHINE Y

MAY AND JUNE, 1971

TYPE OF MEDIUM- SEMICHEMICAL

CODE	DATE MADE	MILL ROLL NO.	BASIS WT., LB./M. SQ. FT.	CALIPER, PT.			CONCORDA FLAT CRUSH, P.S.I.			SINGLE-FACE FLAT CRUSH, P.S.I.			RUNNABILITY LB./IN.*A	DRAW FACTOR*B
				MAX.	MIN.	AV.	MAX.	MIN.	AV.	MAX.	MIN.	AV.		
Y-1	4- 9-71	850	27.2	11.0	9.8	10.2	51.0	40.2	44.8	36.2	32.8	34.3	1.5	1.564
Y-2	4-20-71	851	26.9	12.9	9.8	10.7	43.8	37.2	41.0	32.0	30.4	31.4	1.5	1.568
Y-3	5- 7-71	852	26.9	12.6	9.5	10.6	40.8	34.2	37.9	31.0	29.4	30.3	1.5	1.570
Y-4	5-18-71	853	26.4	11.5	9.8	10.4	42.6	38.4	39.5	33.2	31.4	32.0	1.5	1.567
CURRENT MACHINE AVERAGE			26.8			10.5			40.8			32.0		1.567
CUMULATIVE MACHINE AVERAGE			26.3			10.2			41.8			31.3		
MACHINE FACTOR, PERCENT			101.9			102.9			97.6			102.2		
MACHINE INDEX, PERCENT			100.4			104.0			96.7			102.6		

TABLE XXVII

SUMMARY OF TEST RESULTS FOR MACHINE Z

MAY AND JUNE, 1971

TYPE OF MEDIUM- SEMICHEMICAL

CODE	DATE MADE	MILL ROLL NO.	BASIS WT., LB./M. SQ. FT.	CALIPER, PT.			CONCORDA FLAT CRUSH, P.S.I.			SINGLE-FACE FLAT CRUSH, P.S.I.			RUNNABILITY LB./IN.*A	DRAW FACTOR*B
				MAX.	MIN.	AV.	MAX.	MIN.	AV.	MAX.	MIN.	AV.		
Z-1	4-12-71		27.1	10.0	9.0	9.7	46.2	36.6	41.0	34.0	31.8	32.8	1.0	1.567
Z-2	5-19-71		27.8	9.8	8.9	9.4	49.2	39.6	42.8	35.0	32.0	33.8	1.0	1.567
CURRENT MACHINE AVERAGE			27.4			9.6			41.9			33.3		1.567
CUMULATIVE MACHINE AVERAGE			26.9			9.9			41.4			30.6		
MACHINE FACTOR, PERCENT			101.8			97.0			101.2			108.8		
MACHINE INDEX, PERCENT			102.6			95.0			99.3			106.7		

*See Table II for Notes A and B.

TABLE XXVIII

SUMMARY OF TEST RESULTS FOR MACHINE 4A

MAY AND JUNE, 1971

TYPE OF MEDIUM- SEMICHEMICAL

CODE	DATE MADE	MILL ROLL NO.	BASIS WT., LB./M. SQ. FT.	CALIPER, PT.			CONCORA FLAT CRUSH, P.S.I.			SINGLE-FACE FLAT CRUSH, P.S.I.			RUNNABILITY	
				MAX.	MIN.	AV.	MAX.	MIN.	AV.	MAX.	MIN.	AV.	LB./IN.*A	DRAW FACTOR*B
AA-1	3-24-71	11	25.2	9.9	9.0	9.4	43.8	31.8	38.4	34.6	31.0	32.6	1.5	1.560
AA-2	4-11-71	13	26.8	10.1	9.1	9.6	48.6	36.0	41.9	31.6	29.4	30.5	0.5	1.557
AA-3	4-22-71	15	27.1	10.9	9.8	10.1	45.6	40.2	42.4	34.4	31.2	32.5	1.5	1.550
AA-4	5-28-71	17	25.8	9.8	9.2	9.6	40.2	33.0	37.2	29.0	27.0	27.9	1.0	1.565
CURRENT MACHINE AVERAGE			26.2			9.7			40.0			30.9		1.558
CUMULATIVE MACHINE AVERAGE			26.1			9.9			38.3			28.8		
MACHINE FACTOR, PERCENT			100.4			98.0			104.4			107.3		
MACHINE INDEX, PERCENT			98.1			96.0			94.8			99.0		

TABLE XXIX

SUMMARY OF TEST RESULTS FOR MACHINE 8B

MAY AND JUNE, 1971

TYPE OF MEDIUM- SEMICHEMICAL

CODE	DATE MADE	MILL ROLL NO.	BASIS WT., LB./M. SQ. FT.	CALIPER, PT.			CONCORA FLAT CRUSH, P.S.I.			SINGLE-FACE FLAT CRUSH, P.S.I.			RUNNABILITY	
				MAX.	MIN.	AV.	MAX.	MIN.	AV.	MAX.	MIN.	AV.	LB./IN.*A	DRAW FACTOR*B
BB-1	6- 1-71		26.0	9.3	9.0	9.2	46.8	41.4	44.3	32.4	30.8	31.4	1.5	1.568
BB-2	6- 2-71		26.0	9.2	9.0	9.1	48.6	43.8	45.2	34.4	32.6	33.4	1.5	1.568
BB-3	6- 3-71		26.3	9.4	9.1	9.2	49.8	41.4	43.8	32.8	31.8	32.2	1.5	1.572
BB-4	6- 5-71		25.8	9.2	8.9	9.0	47.4	38.4	42.1	33.0	31.6	32.2	1.0	1.567
CURRENT MACHINE AVERAGE			26.0			9.1			43.8			32.3		1.569
CUMULATIVE MACHINE AVERAGE			26.6			9.7			44.3			32.2		
MACHINE FACTOR, PERCENT			97.7			93.8			98.9			100.3		
MACHINE INDEX, PERCENT			97.4			90.1			103.6			103.5		

*See Table II for Notes A and B.

TABLE XXX

SUMMARY OF TEST RESULTS FOR MACHINE CC

MAY AND JUNE, 1971

TYPE OF MEDIUM- SEMICHEMICAL

CODE	DATE MADE	MILL ROLL NO.	BASIS WT., LB./M. SQ. FT.	CALIPER, PT.			CONCORA FLAT CRUSH, P.S.I.			SINGLE-FACE FLAT CRUSH, P.S.I.			RUNNABILITY LB./IN.*A	DRAW FACTOR*B
				MAX.	MIN.	AV.	MAX.	MIN.	AV.	MAX.	MIN.	AV.		
CC-1	4-19-71	336	27.6	9.3	8.9	9.0	47.2	43.2	45.4	35.8	34.0	35.2	1.5	1.566
CC-2	4-22-71	337	28.2	9.8	8.9	9.2	50.4	43.2	45.5	34.4	33.2	33.8	1.5	1.565
CC-3	5-6-71	340	26.4	8.9	8.4	8.6	48.6	39.0	43.8	34.2	32.4	33.5	MIN.	1.555
CC-4	5-12-71	341	27.5	9.0	8.2	8.6	50.4	42.6	46.7	36.4	33.0	34.7	1.5	1.569
CURRENT MACHINE AVERAGE			27.4			8.8			45.4			34.3		1.564
CUMULATIVE MACHINE AVERAGE			27.2			9.1			43.8			33.0		
MACHINE FACTOR, PERCENT			100.7			96.7			103.6			103.9		
MACHINE INDEX, PERCENT			102.6			87.1			107.6			109.9		

TABLE XXXI

SUMMARY OF TEST RESULTS FOR MACHINE DD

MAY AND JUNE, 1971

TYPE OF MEDIUM- SEMICHEMICAL

CODE	DATE MADE	MILL ROLL NO.	BASIS WT., LB./M. SQ. FT.	CALIPER, PT.			CONCORA FLAT CRUSH, P.S.I.			SINGLE-FACE FLAT CRUSH, P.S.I.			RUNNABILITY LB./IN.*A	DRAW FACTOR*B
				MAX.	MIN.	AV.	MAX.	MIN.	AV.	MAX.	MIN.	AV.		
DD-1	4-12-71	74	26.4	10.5	10.0	10.2	41.4	37.8	39.7	31.6	30.0	31.0	0.5	1.566
DD-2	4-14-71	75	26.2	10.3	10.0	10.0	43.2	39.0	41.0	34.0	32.0	33.3	0.5	1.561
DD-3	5-10-71	76	25.1	10.4	9.8	10.1	44.4	38.4	42.4	35.8	33.8	34.8	MIN.	1.564
DD-4	5-11-71	77	25.6	10.7	9.9	10.2	46.2	43.8	44.9	35.0	32.8	33.8	1.0	1.569
CURRENT MACHINE AVERAGE			25.8			10.1			42.0			33.2		1.565
CUMULATIVE MACHINE AVERAGE			26.1			9.8			40.7			31.0		
MACHINE FACTOR, PERCENT			98.8			103.1			107.1			107.1		
MACHINE INDEX, PERCENT			96.6			100.0			99.5			106.4		

*See Table II for Notes A and B.

TABLE XXXII

SUMMARY OF TEST RESULTS FOR MACHINE EE
MAY AND JUNE, 1971.

TYPE OF MEDIUM- BOGUS

CODE	DATE MADE	MILL ROLL NO.	BASIS WT., LB./M. SQ. FT.	CALIPER, PT.			CONCORA FLAT CRUSH, P.S.I.			SINGLE-FACE FLAT CRUSH, P.S.I.			RUNNABILITY	
				MAX.	MIN.	AV.	MAX.	MIN.	AV.	MAX.	MIN.	AV.	LB./IN.*A	DRAW FACTOR*B
EE-1	4-15-71	434	26.6	10.1	9.3	9.8	39.6	32.4	36.2	30.8	27.0	28.3	1.5	1.578
EE-2	6-11-71	435	27.1	10.0	9.2	9.8	40.2	35.4	38.0	27.6	26.0	26.6	1.5	1.579
CURRENT MACHINE AVERAGE			26.8			9.8			37.1			27.4		1.579
CUMULATIVE MACHINE AVERAGE			27.2			10.0			38.0			26.6		
MACHINE FACTOR, PERCENT			98.5			98.0			97.6			103.0		
MACHINE INDEX, PERCENT			100.4			97.0			87.9			87.8		

*See Table II for Notes A and B.

DISCUSSION OF RESULTS

Shown on page 2, Part II, Section "A" of the Summary are the maximum and minimum current machine averages obtained for each test property during the current period and the previous period. Also shown for each test property is the current F.K.I. average which represents the mean of the current machine averages and hence is indicative of the test level being maintained by the industry as a whole for each test property to the extent that the industry is represented by the participating machines. Also given for each test property is the cumulative F.K.I. average which represents the mean of the current F.K.I. averages for the previous six periods.

The runnability data for the 110 rolls evaluated during the current period and the 107 rolls evaluated during the previous period are summarized on page 2, Part II, Section "B" of the Summary.

Supplementary to the runnability data, draw factors were determined for each roll of medium at 600 f.p.m. with minimum tension (or, for rolls with poor runnability, at the maximum speed runnable with minimum tension) and are given in Tables II through XXXII for Machines A through Z and Machines AA, BB, CC, DD, and EE, respectively.

In Table XXXIII, an effort has been made to compare Institute and mill Concora flat crush test results for each machine for the current period. The following information is presented in this table: (1) Current machine average based on Institute data, (2) current machine average based on mill data, (3) the average difference -- that is, the difference between the current machine average based on Institute data and the current machine average based on mill data, and (4) the average differences expressed as percentage differences, along with the percentage differences of the previous two-month period. In those cases where mill Concora flat crush data

TABLE XXXIII

A COMPARATIVE SUMMARY FOR EACH MACHINE OF THE CONCORA
FLAT CRUSH AVERAGES BASED ON INSTITUTE DATA AND MILL DATA
MAY AND JUNE, 1971

Machine Code	No. of Rolls Compared	Concora Flat Crush, p.s.i.			Av. Diff., % ^c	
		I.P.C. Av. ^a	Mill Av. ^a	Av. Diff. ^b	Current	Previous
A	4	41.4	43.4	+2.0	+4.8	+5.5
B	0	48.6	39.5 ^d	--	--	--
C	4	41.0	38.3	-2.7	-6.6	-3.6
D	4	43.3	41.9	-1.4	-3.2	-8.2
E	4	40.2	38.0	-2.2	-5.5	-2.8
F	4	39.5	43.1	+3.6	+9.1	+1.2
G	4	37.9	35.2	-2.7	-7.1	-10.4
H	4	42.7	40.9	-1.8	-4.2	-2.1
I	2	48.2	47.6	-0.6	-1.2	--
J	2	42.8	41.2	-1.6	-3.7	-0.7
K	4	46.6	46.0	-0.6	-1.3	-2.6
L	4	38.7	36.2	-2.5	-6.5	-11.6
M	4	43.4	42.6	-0.8	-1.8	-4.0
N	3	39.6	40.5	+0.9	+2.3	+0.3
O	4	38.5	38.0	-0.5	-1.3	+1.0
P	2	42.8	40.8	-2.0	-4.7	-4.7
Q	0	44.5	35.9 ^d	--	--	--
R	5	41.4	40.8	-0.6	-1.4	-0.3
S	4	42.8	46.4	+3.6	+8.4	-3.6
T	4	38.9	37.8	-1.1	-2.8	-2.5
U	2	37.2	34.5	-2.7	-7.3	--
V	4	40.9	42.2	+1.3	+3.2	+1.7
W	2	42.6	41.0	-1.6	-3.8	--
X	4	42.2	43.4	+1.2	+2.8	-0.4
Y	4	40.8	39.3	-1.5	-3.7	-6.7
Z	2	41.9	41.7	-0.2	-0.5	-7.6
AA	4	40.0	40.3	+0.3	+0.8	+1.3
BB	4	43.8	44.6	+0.8	+1.8	-0.9
CC	4	45.4	42.9	-2.5	-5.5	-5.3
DD	4	42.0	45.6	+3.6	+8.6	+2.1
EE	2	37.1	34.0	-3.1	-8.4	--

^aComparisons based on current machine average include only those rolls for which mill data were submitted.

^bAverage difference is the difference between the current machine average based on Institute test results and that based on mill test results with the Institute test results used as the reference.

^cAverage difference (percent) is computed by dividing the average difference in p.s.i. by the Institute current machine average and multiplying by 100.

^dMill data were not obtained on specimens tested immediately after fluting.

are still obtained on specimens conditioned after fluting, no average differences between current machine averages based on Institute and mill data are shown. The inclusion of these comparisons is made possible by the fact that interested participants submit their Concora flat crush results to The Institute of Paper Chemistry (on data sheets obtainable from the Institute). This affords each participant an opportunity to review the level of agreement noted for his data with the levels noted for the other participants. Comparisons of this kind are a helpful adjunct to other calibration procedures.

THE INSTITUTE OF PAPER CHEMISTRY

R. C. McKee, Chairman
Container Section

IPST HASELTON LIBRARY



5 0602 01053274 7