

12T
THE EFFECT OF TEMPERATURE,
SALT, AND pH, IN THE APPLICATION
OF DIRECT DYES ON COTTON

A THESIS

Presented to
the Faculty of the Graduate Division
Georgia Institute of Technology

In Partial Fulfillment
of the Requirements for the Degree
Master of Science in Textile Engineering

By
Leonard John Challain

November 1954

In presenting the dissertation as a partial fulfillment of the requirements for an advanced degree from the Georgia Institute of Technology, I agree that the Library of the Institution shall make it available for inspection and circulation in accordance with its regulations governing materials of this type. I agree that permission to copy from, or to publish from, this dissertation may be granted by the professor under whose direction it was written, or such copying or publication is solely for scholarly purposes and does not involve potential financial gain. It is understood that any copying from, or publication of, this dissertation which involves potential financial gain will not be allowed without written permission.

LEONARD B. COLEMAN

THE EFFECT OF TEMPERATURE,
SALT, AND pH, IN THE APPLICATION
OF DIRECT DYES ON COTTON

Approved:

[Redacted signature area]

Date Approved by Chairman: Nov. 24, 1954

ACKNOWLEDGEMENTS

A sincere expression of gratitude is offered to the United States Naval Postgraduate School under the auspices of which this course of study was undertaken; to Dr. James L. Taylor, of the Georgia Institute of Technology Textile School, who actively directed and guided the work performed in this thesis; to Dr. William Postman of the Georgia Institute of Technology Textile School, who materially helped solve the colorimeter problems involved in this thesis; and to Mr. L. A. Burroughs of the Atlanta Laboratory of the E. I. du Pont de Nemours and Company, Inc., who provided the dyes used in the laboratory phase of this investigation.

TABLE OF CONTENTS

| | Page |
|--|------|
| ACKNOWLEDGEMENTS | ii |
| LIST OF TABLES | iv |
| LIST OF ILLUSTRATIONS | ix |
| SUMMARY | x |
| Chapter | |
| I. INTRODUCTION | 1 |
| The Problem | |
| History of Direct Dyes | |
| II. THEORETICAL CONSIDERATIONS | 5 |
| The Direct Dye | |
| The High Temperature Theory | |
| Literature Survey | |
| III. INSTRUMENTATION AND EQUIPMENT | 15 |
| IV. PROCEDURE | 19 |
| Characterization of the Yarn | |
| Preparation for Dyeing | |
| Sample Preparation | |
| Outline of General Dyeing Procedure | |
| Dyeing | |
| Colorimetry | |
| pH Control and Determination | |
| Dyed Yarn Strength | |
| Light-Fastness Tests | |
| Wash-Fastness Tests | |
| V. DISCUSSION OF RESULTS | 28 |
| VI. CONCLUSIONS | 46 |
| VII. RECOMMENDATIONS | 48 |
| APPENDIX | 49 |
| BIBLIOGRAPHY | 122 |

LIST OF TABLES

| Table | Page |
|--|------|
| 1. Concentration of Dyebath Calculated from Per Cent Transmission of Diluted Dyebath Sample. | 31 |
| 2. Comparison of Dyebath Exhaustions for Pontamine Fast Yellow RL. | 41 |
| 3. Comparison of Dyebath Exhaustions for Pontamine Fast Orange EGL | 42 |
| 4. Comparison of Dyebath Exhaustions for Pontamine Blue AX Conc. | 43 |
| 5. List of Dyes Used | 50 |
| 6. Yarn Number of Scoured, Undyed Yarn | 51 |
| 7. Twist of Scoured, Undyed Yarn | 52 |
| 8. Single Strand Breaking Strength for Scoured, Undyed Yarn | 53 |
| 9. Light Absorption Percentages for Pontamine Fast Yellow RL. | 54 |
| 10. Light Absorption Percentages for Pontamine Fast Orange EGL | 55 |
| 11. Light Absorption Percentages for Pontamine Blue AX Conc. | 56 |
| 12. Light Transmission for Pontamine Fast Yellow RL, with Sodium Chloride. | 57 |
| 13. Light Transmission for Pontamine Fast Yellow RL, with Ammonium Sulphate. | 58 |
| 14. Light Transmission for Pontamine Fast Yellow RL, with Sodium Acetate | 59 |
| 15. Light Transmission for Pontamine Fast Yellow RL, with Ammonium Phosphate | 60 |
| 16. Light Transmission for Pontamine Fast Yellow RL | 61 |

| Table | Page |
|--|------|
| 17. Light Transmission for Pontamine Fast Yellow RL, with Ammonium Sulphate and Sodium Chloride. | 62 |
| 18. Light Transmission for Pontamine Fast Yellow RL, with Sodium Acetate and Sodium Chloride | 63 |
| 19. Light Transmission for Pontamine Fast Yellow RL, with Ammonium Phosphate and Sodium Chloride | 64 |
| 20. Light Transmission for Pontamine Fast Orange EGL, with Sodium Chloride. | 65 |
| 21. Light Transmission for Pontamine Fast Orange EGL, with Ammonium Sulphate. | 66 |
| 22. Light Transmission for Pontamine Fast Orange EGL, with Sodium Acetate | 67 |
| 23. Light Transmission for Pontamine Fast Orange EGL, with Ammonium Phosphate | 68 |
| 24. Light Transmission for Pontamine Fast Orange EGL. | 69 |
| 25. Light Transmission for Pontamine Fast Orange EGL, with Ammonium Sulphate and Sodium Chloride. | 70 |
| 26. Light Transmission for Pontamine Fast Orange EGL, with Sodium Acetate and Sodium Chloride | 71 |
| 27. Light Transmission for Pontamine Fast Orange EGL, with Ammonium Phosphate and Sodium Chloride | 72 |
| 28. Light Transmission for Pontamine Blue AX Conc., with Sodium Chloride. | 73 |
| 29. Light Transmission for Pontamine Blue AX Conc., with Ammonium Sulphate. | 74 |
| 30. Light Transmission for Pontamine Blue AX Conc., with Sodium Acetate | 75 |
| 31. Light Transmission for Pontamine Blue AX Conc., with Ammonium Phosphate | 76 |
| 32. Light Transmission for Pontamine Blue AX Conc.. . . . | 77 |
| 33. Light Transmission for Pontamine Blue AX Conc., with Ammonium Sulphate and Sodium Chloride. | 78 |

| Table | Page |
|---|------|
| 34. Light Transmission for Pontamine Blue AX Conc., with Sodium Acetate and Sodium Chloride. | 79 |
| 35. Light Transmission for Pontamine Blue AX Conc., with Ammonium Phosphate and Sodium Chloride. | 80 |
| 36. Summary of Absorption Indices Computed in Tables 12-35 | 81 |
| 37. Dyeing Cycle Data of Pontamine Fast Orange EGL at Normal Temperature. | 82 |
| 38. Dyeing Cycle Data of Pontamine Fast Orange EGL at Normal Temperature. | 83 |
| 39. Dyeing Cycle Data of Pontamine Fast Yellow RL at Normal Temperature. | 84 |
| 40. Dyeing Cycle Data of Pontamine Fast Yellow RL at Normal Temperature. | 85 |
| 41. Dyeing Cycle Data of Pontamine Blue AX Conc. at Normal Temperature. | 86 |
| 42. Dyeing Cycle Data of Pontamine Blue AX Conc. at Normal Temperature. | 87 |
| 43. Dyeing Cycle Data of Pontamine Fast Yellow RL. | 88 |
| 44. Test for Heat Stability of Pontamine Fast Yellow RL of Table 43. | 89 |
| 45. Dyeing Cycle Data of Pontamine Fast Orange EGL | 90 |
| 46. Test for Heat Stability of Pontamine Fast Orange EGL of Table 45. | 91 |
| 47. Dyeing Cycle Data of Pontamine Blue AX Conc. | 92 |
| 48. Test for Heat Stability of Pontamine Blue AX Conc. of Table 47. | 93 |
| 49. Dyeing Cycle Data of Pontamine Fast Yellow RL - High Temperature | 94 |
| 50. Test for Stability of Pontamine Fast Yellow RL of Table 49. | 95 |
| 51. Dyeing Cycle Data for Pontamine Fast Orange EGL - High Temperature | 96 |

| Table | Page |
|---|------|
| 52. Test for Stability of Pontamine Fast Orange EGL of Table 51. | 97 |
| 53. Dyeing Cycle Data for Pontamine Fast Orange EGL - High Temperature | 98 |
| 54. Test for Stability of Pontamine Fast Orange EGL of Table 53. | 99 |
| 55. Dyeing Cycle Data for Pontamine Blue AX Conc. - High Temperature | 100 |
| 56. Test for Stability of Pontamine Blue AX Conc. of Table 55. | 101 |
| 57. Dyeing Cycle Data for Pontamine Blue AX Conc. - High Temperature | 102 |
| 58. Test for Stability of Pontamine Blue AX Conc. of Table 57. | 103 |
| 59. Dyeing Cycle Data for Pontamine Fast Yellow RL - High Temperature, Neutral Bath | 104 |
| 60. Test for Stability of Pontamine Fast Yellow RL of Table 59. | 105 |
| 61. Dyeing Cycle Data for Pontamine Fast Yellow RL - High Temperature, Acid Bath. | 106 |
| 62. Test for Stability of Pontamine Fast Yellow RL of Table 61. | 107 |
| 63. Dyeing Cycle Data for Pontamine Fast Yellow RL - High Temperature, Alkaline Bath. | 108 |
| 64. Test for Stability of Pontamine Fast Yellow RL of Table 63. | 109 |
| 65. Dyeing Cycle Data for Pontamine Fast Orange EGL - High Temperature, Neutral Bath | 110 |
| 66. Test for Stability of Pontamine Fast Orange EGL of Table 65. | 111 |
| 67. Dyeing Cycle Data for Pontamine Fast Orange EGL - High Temperature, Alkaline Bath. | 112 |
| 68. Test for Stability of Pontamine Fast Orange EGL of Table 67. | 113 |

| Table | Page |
|---|------|
| 69. Dyeing Cycle Data for Pontamine Fast Orange EGL - High Temperature, Acid Bath. | 114 |
| 70. Test for Stability of Pontamine Fast Orange EGL of Table 69. | 115 |
| 71. Dyeing Cycle Data for Pontamine Blue AX Conc. - High Temperature, Neutral Bath | 116 |
| 72. Test for Stability of Pontamine Blue AX Conc. of Table 71. | 117 |
| 73. Dyeing Cycle Data for Pontamine Blue AX Conc. - High Temperature, Alkaline Bath. | 118 |
| 74. Test for Stability of Pontamine Blue AX Conc. of Table 73. | 119 |
| 75. Dyeing Cycle Data for Pontamine Blue AX Conc. - High Temperature, Acid Bath. | 120 |
| 76. Test for Stability of Pontamine Blue AX Conc. of Table 75. | 121 |

LIST OF ILLUSTRATIONS

| Figure | Page |
|---|------|
| 1. Morton One-Pound Package Machine (modified), Top View. . . . | 16 |
| 2. Morton One-Pound Package Machine (modified), Side View . . . | 17 |
| 3. Lumetron Colorimeter, Model 402-E. | 18 |

THE EFFECT OF TEMPERATURE,
SALT, AND pH IN THE APPLICATION
OF DIRECT DYES ON COTTON

SUMMARY

The success experienced in applying dyes to the new synthetic fibers with high temperatures started several investigations as to the possibility of using the same high temperature technique in applying direct dyes to cotton. These investigations demonstrated that some direct dyes can be applied to cotton successfully with high temperatures; however, many questions were raised such as: What is the heat stability of each dye? What is the effect of the pH of the dyebath on the stability of each dye? What is the effect of salt with high temperature? What is the effect of high temperature on the exhaustion of each dye? What is the effect of high temperature on the quality of the dyed product?

The purpose of this thesis was to answer some of these questions, and thereby increase the empirical knowledge available to the dyeing industry, for three direct cotton dyes. The dyes used in this investigation were: Pontamine Fast Yellow RL, representing the Class A, or good-leveling, type direct dye; Pontamine Fast Orange EGL, representing the Class B, or salt-controllable, poor-leveling, type direct dye; and Pontamine Blue AX Conc., representing the Class C or temperature-controllable, poor-leveling, type direct dye.

Four sets of dyeings were made on cotton yarn for each dye as follows:

1. Normal temperature dyeings with dye and salt applied as recommended by the manufacturer.
2. High temperature runs, with dye and salt added initially, but with no cotton yarn in the bath (the heat stability tests).
3. High temperature dyeings, at 250° F., with dye applied to cotton, but with salt added to bath during the cooling phase.
4. High temperature dyeings, at 250° F., with dye applied to cotton, with a buffer added initially to control the pH of the dyebath, and with salt added during the cooling phase of the dyeing cycle.

The dye runs were compared for heat stability of the dyes, and for dyebath exhaustions. The dyed yarns were compared for differences in color, light-fastness, wash-fastness, and strength.

It was found that dyebath concentrations can be accurately measured only if dyebath samples can be read on the colorimeter in undiluted form. The concentration results obtained by reading diluted dyebath samples in the colorimeter indicated the exhaustion of the Class C dye only was significantly improved with high temperature application.

It was found that the three dyes tested were stable at high temperatures, and the additions of buffers to the dyebath had no apparent affect on their stability.

It was also found that the dyeings with high temperature were equal in color, fastness, and strength, to dyeings with normal temperature. The overall dyeing time was not decreased with high temperature application

because of the time required to raise the temperature of the bath to 250° F.

The results of all dyeings indicate that the most powerful dyeing assistant for direct dyes is not temperature but salt. In all dye runs the high temperature actually reduced the dyebath exhaustions. The dyebath was not significantly exhausted during the Class B or C dye runs until the bath was cooled and salt added.

CHAPTER I

INTRODUCTION

Considerable interest in the field of high temperature dyeing has been seen in the past several years. This interest was aroused primarily when it was found that the new synthetic fibers, such as nylon, Orlon, and Dacron, could be dyed within a short time in dyebaths at 250° F., whereas they were not dyed well in dyebaths at the normal dyeing temperature of 212° F. The success of high temperature application of dyes on the synthetics started an investigation as to the possible advantages in using the same high temperature techniques in applying dyes to cotton, and rayon, as well as wool.

Direct dyes are used in great quantities for dyeing cellulose products in all forms. Although several types of dyes have been developed, such as vat dyes, which are superior to direct dyes in fastness properties, the direct dyes continue to be used because they are easier, and consequently less expensive, to apply to cellulose. It is felt that the continued popularity of the direct dyes will be even more insured if they can be applied better and in less time by new methods.

It has been found by Young (1) that some direct dyes can be applied to cotton at high temperatures, in less time, and with no decrease in product quality. Relatively few of the actual number of popular direct dyes have been studied as to their high temperature stability and other dyeing characteristics. Before industry can determine the economic feasibility of using the high temperature method in place of the relatively

easy normal temperature application of direct dyes on cotton, many technical questions must be answered, and they must be answered for each individual direct dye.

The art of dyeing is based mainly on empirical knowledge. If the high temperature method is to be put in actual use then the fund of empirical knowledge must include the effects of high temperature for all the direct dyes and cotton combinations. The dyer must have information for each dye as to: the effect of high temperature on the chemical stability of the dyestuff; the effect of high temperature on the dyed product; the effect of the pH condition of the dyebath; the effect of high temperature on the exhaustion of the dyebath; and the effect of salt on the dyebath when using high temperature.

The purpose of this work was to supply some of the empirical information which will help answer the above questions. The various effects of high temperature, pH, and salt on three types of direct dyes were investigated. One dye from each of the three leveling classes of direct dyes (2) was chosen for this experiment in order to give representative and comparative results between the known leveling types.

High temperature dyeing means application with dyebath temperature over 212° F. and up to possibly 300° F. In this investigation 250° was used as the temperature for a high temperature dyeing run. The increased temperature over 212° F. is thought to increase the speed of penetration so that the same or a greater amount of dye can be applied to cotton in a much shorter time than now required in normal temperature dyeing. This shorter time in the bath would allow a speed-up of modern continuous dyeing

machinery or allow less time for yarn to be dyed in a package dye machine. If the theory is equally sound in actual production dyeing, the high temperature technique can materially benefit the cotton textile industry.

Faster application will be of little value if the end product is not as good as dyeings now achieved with normal temperatures. In this investigation yarns dyed at high temperature were compared with yarns dyed at normal temperature, and any changes in fastness properties, color, or yarn strength were noted.

History of Direct Dyes.—Synthetic dyes are made from the aromatic hydrocarbons, benzene, toluene, naphthalene, and anthracene, and the chief sources of these are coal tar and petroleum. The honor of discovering the first synthetic dye went to an Englishman named Perkin in 1856 (3). Perkin was attempting to synthesize quinine by the addition of oxygen to allyltoluidine, in observing the action of potassium dichromate on aniline sulfate, he noticed a black product was formed. From this black substance Perkin isolated a coloring matter which he found would dye silk. His main contribution to the industry was in overcoming many obstacles, financial and technical, in order to transform a casual laboratory experiment into manufacturing practice. Perkin actually established a plant in 1857 which produced Mauve or Tyrian Purple as he called it. His success in demonstrating the value of his product to the dyer and printer started a feverish search on the part of chemists all over the world for other possible synthetic dyes.

Many dyes were discovered thereafter which would dye wool and silk nicely but they all had to be mordanted on cotton. In 1883 Walter made

Sun Yellow, the first stilbene dye, and the first soluble dye which would dye cotton (4). In 1884 the first direct cotton dye from benzidine, Congo Red, was discovered by Bottiger (5). This dye enjoyed immediate popularity and is still used a great deal in spite of its fugitive character. Since 1884 hundreds of other direct dyes have been synthesized by coupling tetrazotized benzidine and analogous diamines with various components.

CHAPTER II

THEORETICAL CONSIDERATIONS

Direct cotton dyes are so called because they have the ability to dye cotton without a mordant in the bath. Because salt is generally added to aid exhaustion they are sometimes called salt dyes. Direct dyes are mainly sodium salts of azo sulfonic acids; they are azo dyes with certain specific structural features (6). In order for the dye to be able to dye cellulose without the aid of a mordant the direct dye must have functional groups which can be held by hydrogen bonds with the hydroxyl groups in the cellulose polymer. As corresponding hydroxyl groups in the cellulose chain are spaced 10.3 Angstrom units apart, the functional groups on the direct dye must also be spaced a similar distance apart. In most cases only dyes with this special structural arrangement will dye cotton directly. As only direct dyes possess these specific structural features associated with substantivity for the cellulose fibers they are sometimes called substantive dyes.

Direct dyes as a class have poor fastness to washing and light. This drawback can be somewhat overcome with proper after treatment. Recent developments have made available direct dyes which are either copper complexes or dioxazines which have excellent light fastness properties (7).

Most direct dyes are salts of dye acids and these dyes may exist in solution as ions, molecular dispersions, or colloidal dispersions. The majority of dyes exist in solution as single ions or molecules and as simple aggregates of 2-10 molecules. Depending on amount of aggregation the actual

size of dye particles in solution varies. If the amount of aggregation is large it may not be possible for the dye to enter the intermicellular spaces of cellulose. With direct dyes it was found aggregation varies inversely with temperature (8).

The diameter of the capillary pores of cellulose is of the same order as the length of a direct cotton dye molecule. These pores are a network of cellulose chains which act like pores, but are not necessarily continuous capillary tubes. Royer states that it is thought that it is through these pores the dye is absorbed molecularly. High temperature acts to increase the pore size by swelling and at the same time decreases the aggregation and increases diffusion by increased thermal activity (9).

The great disadvantage uncovered so far with high temperature dyeing is that some of the dyes decompose when exposed to temperatures above the boil. One big advantage is that high temperatures should increase the migratory activity of the dye particles and thus produce more level dyeing.

The textile and dyeing publications for the past several years have included articles concerning the theory and application of direct dyes to cotton. In 1939 Valko (10) successfully measured the size of various acid and direct dyes by diffusion methods. He showed that most acids and some direct dyes are partly dispersed in the dye bath into single ions and are partly dispersed in the form of aggregates which in size do not exceed 3 dye ions, at 90° C. Some dyes do aggregate to a size of 100 ions but this type is in the minority. Valko further found that dye particle size has been overestimated as most acid and some directs are dispersed completely or at least nearly so into molecules or ions under dyeing conditions. He stated that the important factor in dyeing is not the molecule size, but

the effect of attraction forces such as hydrogen bonding between fiber molecule and dye particle.

In 1946 the Society of Dyers and Colourists (11) reported that their research resulted in the classification of direct cotton dyes into three classes:

Class A, Direct dyes having good migratory and leveling properties.

Class B, Direct dyes having poor migrating properties but which can be controlled by additions of salt to give uniform dyeing.

Class C, Direct dyes of poor migrating and leveling properties, but which can be controlled by temperature and salt addition to give level dyeing.

The direct dyes used in this thesis have been classified on the basis of the recommendations of the Society of Dyers and Colourists (12). In order to get an indication of how each class of dye might react when applied to cotton at high temperature, a representative dye from each class was used.

It has also been reported by the Society of Dyers and Colourists that temperature influence on direct dyeing is twofold. That is, an increase in temperature increases the rate of dyeing and at the same time decreases the equilibrium exhaustion. Thus if a given dye is dyed for a fixed time at various temperatures the influence of the temperature on exhaustion will depend upon both the time chosen and the dyeing rate of the individual dye. With a rapid dyeing dye the equilibrium may have been reached in the time chosen and an increase in the temperature actually would reduce the depth of dyeing. On the other hand with a slow dyeing dyestuff equilibrium may not have been reached in the time chosen and any increase in temperature would increase the exhaustion or depth of dyeing.

In 1949 the Philadelphia Section of the AATCC (13) published a survey of the application of most common dyestuffs at high temperatures. They investigated the effect of high temperature on both the dyebath and the dye bath container, and found that chemical reactions occurred at high temperature between metals normally used in the containers and the dyestuffs; the result being the dye was reduced and in many cases the color destroyed completely. This group found that special stainless steel or glass lined stainless steel containers must be used as only these did not react with dyestuffs at high temperature. The same article also reported that heat destroyed many dyes in each major class, especially the vats, but there were still many dyes in each class which would tolerate the high temperatures for reasonable periods. The article stated the most important advantage revealed for high temperature direct dye application was better leveling of certain fast-striking dyes; however, this advantage was partly offset by the availability of a large number of excellently performing dyes applicable at conventional temperature. The article also stated there was no improvement in fastness properties in the direct dyes on cotton. One point on the side of high temperature application was that diffusion was greatly increased in the fiber, and many unlevel dyes behaved like level dyes. Thus the high temperature method did increase the number of available leveling dyes.

One of the first investigators to consolidate several of the most accepted theories of dyeing and apply this information to high temperature application was Drijvers (14). His interpretation of the high temperature dyeing theory was the guiding principle of this thesis. The following is a summary of high temperature application as presented by Drijvers.

The fundamental principle of high temperature dyeing is based on the fact that dyeing is accomplished by physico-chemical (or purely chemical) reactions, which being reversible, create a state of equilibrium after a certain period. The state of equilibrium and the rate at which it is established are functions of the temperature.

The dyeing of any textile occurs in three steps:

1. The diffusion of the dye in the bath towards the surface of the fiber. As a result of residual valencies the molecules of the dye tend to aggregate in the dyebath. At each temperature a state of equilibrium is reached between the amount of dye in the bath in molecular state and amount in an aggregated state.
2. Adsorption on the surface of the fiber. The molecularly-diffused dye in the bath comes into contact with the fiber through movement of bath, and an adsorption phenomenon occurs until equilibrium is reached.
3. Diffusion into fiber. The surface adsorbed dye has to penetrate into the inter-crystalline spaces of the macromolecule of the cellulose fiber. This penetration is slow because of the mechanical resistance encountered by the dye. This accounts for the rapid accumulation of the dye on the surface of the fiber and for the time required in all dyeings to reach equilibrium. Further adsorption will not continue unless diffusion of dye into the fiber is proceeding. Thus it is seen that diffusion is very important as it governs the speed of dyeing and also determines the fixation of the dye and resistance to rubbing.

The fundamental principle which insures level dyeing as stated by Drijvers is:

In a dynamic system (dye solution and mass to be dyed) no change whatsoever, so far as exhaustion of the bath is concerned, can be achieved as long as tinctorial equilibrium has not been reached between the entire mass and whole of the bath.

In other words the repeated circulation of the dye bath alternately creates phenomenon of desorption and adsorption which causes migration of the dye from light to dark places until a tinctorial equilibrium is reached. The principle factors governing the equilibrium are temperature, concentration of the electrolyte, and the nature of the dye.

Drijvers performed experiments with the three classes of direct dyes and plotted curves of exhaustion vs temperature (as abscissa). He found that each dyestuff has a characteristic curve and the point at which it falls off towards the abscissa is a critical point. From the temperature corresponding to this critical point the exhaustion curve approaches equilibrium and at higher temperatures falls. This finding is in agreement with previous statements that dyebath exhaustion is reduced by high temperature.

This characteristic of direct dyes is overcome by raising the temperature to the critical point as rapidly as possible. Thus the high temperature promotes more rapid diffusion of the dye into the fiber and consequently arrives rapidly at the physico-chemical equilibrium. After equilibrium is reached the curve is descended by cooling, and most of the dye goes onto the fiber during this salting and cooling phase.

In the work for this thesis this theory of applying most of the dye during the salting and cooling phase was investigated. It is known that

salt tends to aggregate the dye molecules (15) and this effect of salt would be in direct competition with the high temperature theory which holds that high temperature decreases aggregation. Therefore to get the maximum penetration possible, and to arrive at tinctorial equilibrium in the shortest time, only the dye or dye and buffer, was in the bath at the high temperature phase of the dye run. When the bath was cooled salt was then added and most of the dye put on the yarn during this cooling phase of the dye run. This procedure should give the maximum effect of high temperature and allow dyeing in the shortest time.

Drijvers also found that many direct dyes are reduced at high temperature especially under slightly alkaline conditions. He theorized that certain organic products from decomposition of the cellulose act as reducing agents which are capable of destroying the azo bond of the dye molecule. He advocated use of oxidizing agents such as hydrogen peroxide and perborates to prevent reduction.

Steeverlynck (16) agrees that alkalinity causes decomposition of some direct dyes and recommends ammonium sulphate be added to the dyebath to maintain an essentially neutral pH, and thereby prevent dye reduction.

Drijvers (17) in 1954 further stated that the latest improvement in the application of direct dyes on cellulose at high temperature is improved dye stability. He found that reduction of the dyestuff can be prevented by simply removing the alkalinity of the bath. He also recommends ammonium sulphate as a buffer and states that fastness properties are not affected and shades are not dulled when this buffer is used.

Herrmann (18) classifies many German direct dyestuffs according to their stability at 248° F. He found that there are three classes of direct

dyes according to behavior at high temperature. Class 1 dyes include some 40 different dye colors which are stable at 248° F. when applied for 30 minutes on viscose rayon. Class 2 dyes include some 34 dye colors the stability of which suffer somewhat at high temperature. Class 3 includes 35 dye colors which suffer severely.

Herrmann states that by adding a "monochrome mordant" as a buffer the deterioration can be prevented on Class 2 dyes and lessened on Class 3 dyes. The stability of substantive dyes above 212° F. is dependent upon the following:

- (a) temperature of bath
- (b) length of time in process
- (c) pH of dyebath
- (d) material being dyed
- (e) degree of dyeing

In discussing the above Herrmann states that the danger of damage increases with the temperature and some direct dyes even break down below the boil. The nature of the dye determines its stability. The length of time of dye cycle is important as some dyes withstand 2-6 hours of high temperature while others are affected in a few minutes. He states the length of time of 30 minutes was chosen to test the dyes as this time reflected a normal dye run. The danger of damage at high temperature seems to be increased if the bath is alkaline. Herrmann found that there is much less danger of breakdown if the bath is kept neutral or slightly acid. Agents remaining from previous treatment of the fiber may also affect the pH of the bath and hence the stability of the dye.

The stability of many dyes above 212° F. is dependent upon the material dyed. Herrmann found that any impurities on the fabric or yarn

may reduce the dyestuff. His experiments show that dyes are stable on materials in the following order from least to best:

1. Raw cotton
2. Acetate
3. Cupra-ammonium rayon
4. Scoured cotton
5. Viscose rayon
6. Scoured and bleached cotton

A dye which would be unstable at high temperatures on raw cotton might be stable on scoured cotton. This finding bears out Drijvers (19) theory that many direct dyes are reduced at high temperature because certain organic products resulting from decomposition of cellulose, or impurities on the fiber, act as reducing agents capable of destroying the azo bond.

Butterworth (20) observed in 1953 that with the exception of Steverlynck's work all high temperature investigation has been confined to the laboratory. He concludes that the high temperature method is best applicable to groups B and C of direct dyes. He disagrees with Drijvers that most of the dye should be put on the fiber during the cooling cycle after the high temperature phase, but instead recommends salt be added during the last half of the high temperature phase. This takes advantage of high temperature as it utilizes the greater redistribution powers of high temperature, as well as gaining the desired equilibrium in shortest time.

Butterworth states that stability of the dyestuff is very important and gives a short list of English dyes which are placed in three groups according to stability at high temperature. Ammonium sulphate is recommend-

ed as a buffer to maintain neutral pH and prevent reduction of the dye. Butterworth states that it is not known why ammonium sulphate acts as a dyebath assistant in a closed system as the ammonia cannot escape. The chemical function of the buffer in preventing reduction has not been ascertained.

Butterworth summarized that high temperature application of direct dyes permits equal or better results on rayon in a shorter time, but as direct dyes are destroyed by an alkali-cellulose system it is essential to maintain neutrality.

There has been little work done in the United States concerning stability of direct dyes on cotton. The dyestuff manufacturers have not published data concerning the heat stability of their direct dyes, nor have researchers attempted to investigate the stability of American directs as Herrmann did with the German direct dyes. This information is greatly needed before commercial high temperature application can be attempted.

CHAPTER III

INSTRUMENTATION AND EQUIPMENT

The following items of special equipment were used in this problem:

Morton Twelve-Pound Package Machine

Morton One-Pound Package Machine (modified)

Atlas Fade-Ometer

Lumetron Colorimeter, Model 402-E

Beckman pH Meter, Model H-2

Beckman Spectrophotometer, Model DU

Suter Single Strand Yarn Testing Machine

All items of equipment except the modified Morton one pound package machine are standard equipment available on the open market and require no special description.

The Morton one pound package machine was modified by the addition of a stainless steel cover which can be secured to the top of the expansion chamber. This encloses the entire dyebath and permits circulation under high temperature and pressure.

Two views of the modified machine are shown in figures 1 and 2.

A view of the lumetron colorimeter Model 402-E is shown in Figure

3.

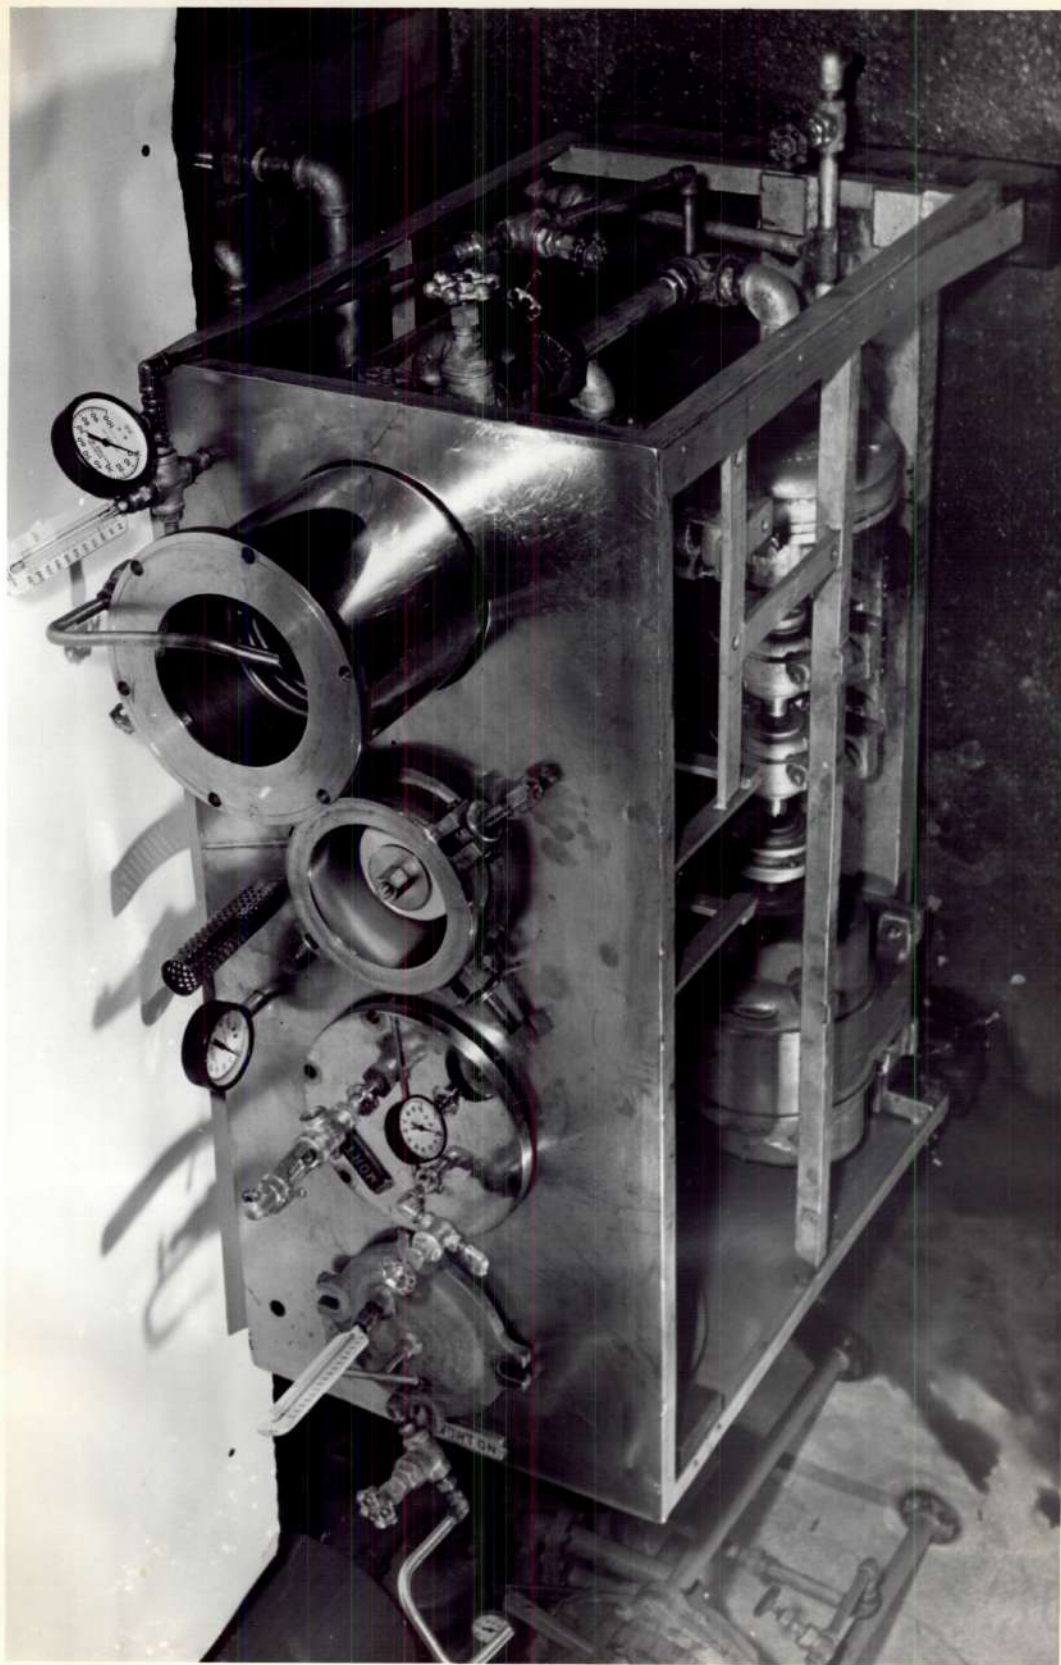


Figure 1. Morton One-Pound Package Machine (Modified) Top View

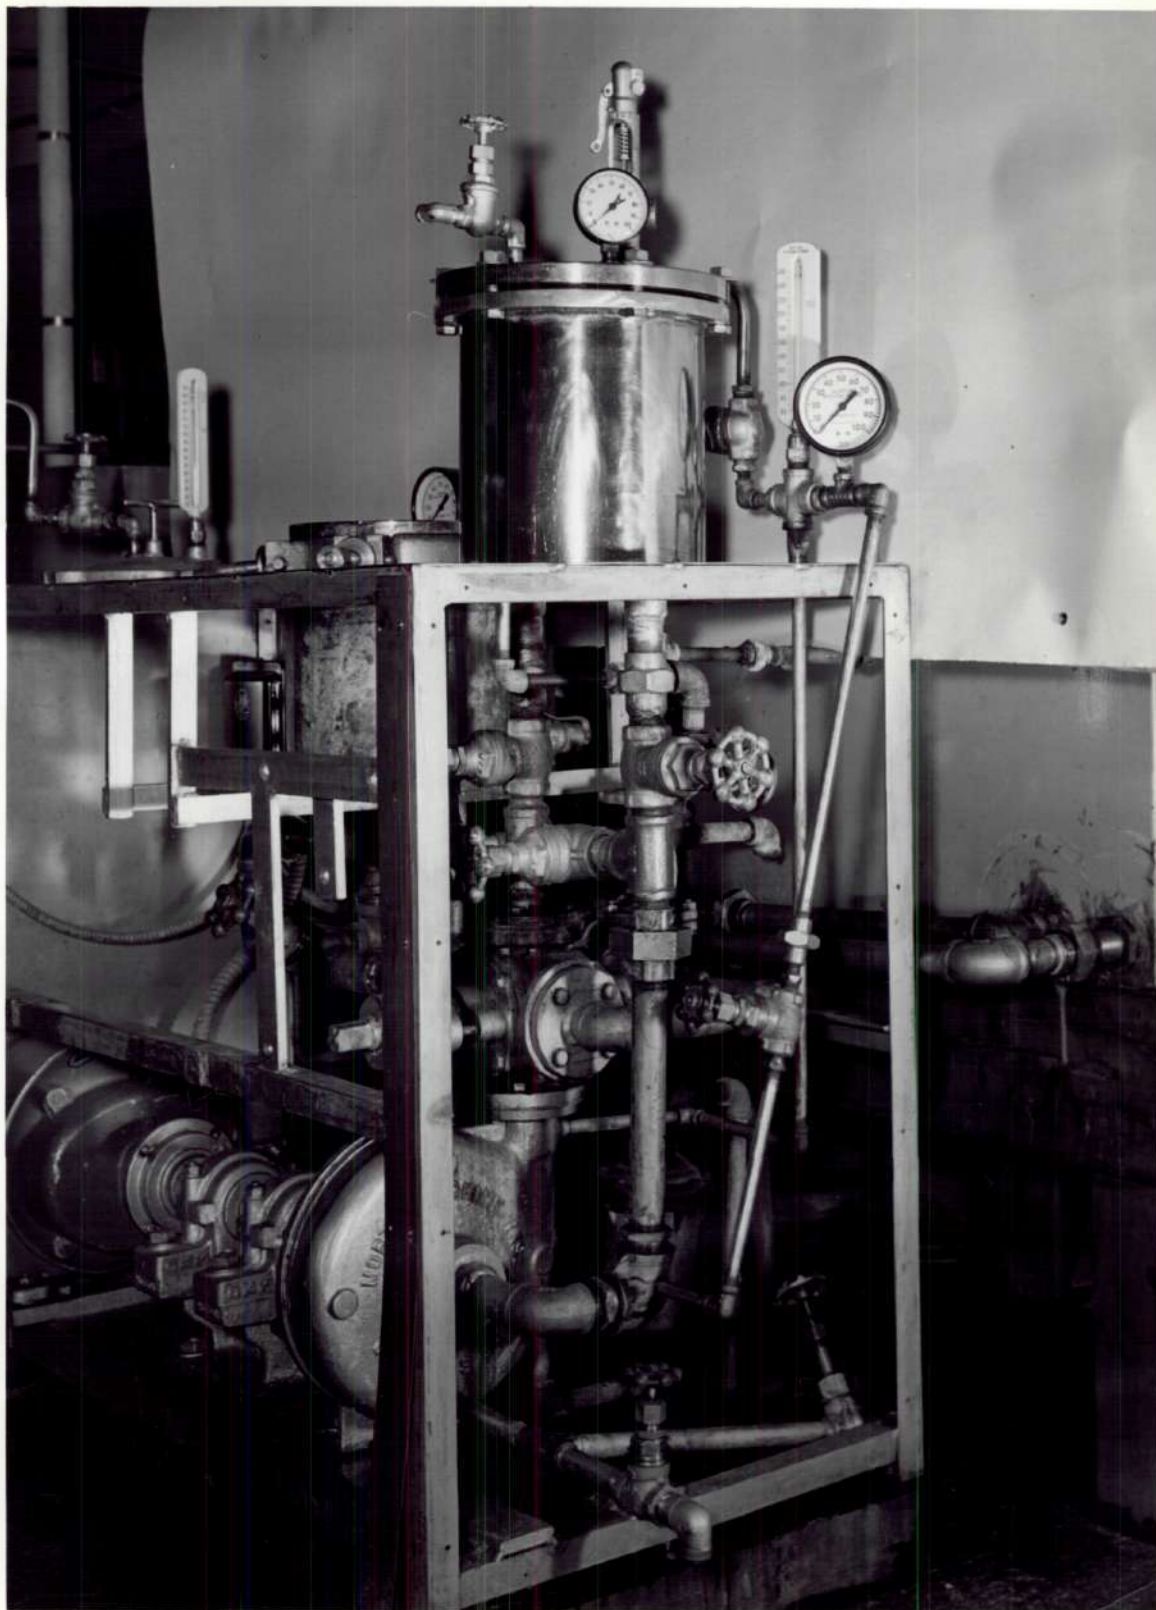


Figure 2. Morton One-Pound Package Machine
(Modified), Side View



Figure 3. Lumetron Colorimeter, Model 402-E

CHAPTER IV

PROCEDURE

Characterization of the Yarn.--The cotton yarn used was first characterized with regard to size, twist, and breaking strength in accordance with the American Society for Testing Materials standard test D180-527 (21). The yarn was found to be a number 15.85 single ply yarn with Z twist of 18.17 turns per inch, and with a breaking strength of 1.247 pounds. The strength was highly irregular, varying from 1.09 to 1.55 pounds, and this deviation may affect the accuracy of strength tests on the dyed samples. The results are shown in Tables 6, 7 and 8.

Preparation for Dyeing.--The yarn was scoured in groups of twelve in the Morton Twelve Pound Package Machine. In scouring, the yarn was first wet out with one-half per cent of Tergitol-08 penetrant, with the machine filled with water, at 180° F. for fifteen minutes. Then the yarn was scoured in a bath containing five per cent sodium hydroxide, three per cent sodium carbonate, and one per cent soap for one hour at 200° F. All percentages are on net weight of the yarn. The flow was reversed every five minutes. The bath was drained and yarn rinsed until neutral. The packages were then hydro-extracted and dried in a hot air oven. The packages were then conditioned for forty-eight hours at sixty-five per cent relative humidity and 70° F.

Sample Preparation.--Each package of scoured yarn was tagged with a number it would have throughout the experiments. Three breaking strength tests

were made on each package, averaged and recorded in Table 8.

The weight of each package was determined to within one-tenth of a gram and was recorded on each package to be used as a basis for the calculation of weights of dyes and chemicals used in dyeing runs.

Outline of General Dyeing Procedure.—In order to test the three dyes used in this experiment for heat stability, three dye runs were made for each dye. In the first run dye and salt alone were used in the dyebath, without cotton yarn, at high temperature. Per cent transmission versus wavelength curves, before and after heating at 250° F. for 30 minutes, were plotted from colorimeter readings on samples of dyebath, and these curves were compared for any changes which might indicate a chemical breakdown of the dyestuff.

In the second set of high temperature dye runs, dye alone was in the dyebath, with cotton yarn. Per cent transmission versus wavelength curves were similarly plotted and compared. In the third set of high temperature dye runs, dye was in the bath, with cotton yarn, and in addition a buffer was added to control the pH of the dyebath. Per cent transmission versus wavelength curves were plotted from colorimeter readings of the beginning and ending dyebath samples and compared.

The other major aim of this investigation was to compare the dyebath exhaustion of normal temperature dye runs with the exhaustions of the high temperature runs. This was done by comparing the final dyebath exhaustions determined in the three sets of heat stability dye runs with the exhaustions obtained by dyeing cotton yarn in the manner recommended by the manufacturer.

The effect of salt on the dyebaths was investigated by comparing the dyebath concentration of various samples taken before and after salting for each dye run.

Thus four sets of dyeings were made for each dye as follows:

1. Normal temperature dye runs with dye and salt applied as recommended by manufacturer.
2. High temperature runs, with dye and salt added initially, but with no cotton yarn in the dyebath. (The heat stability runs)
3. High temperature dye runs with dye applied to cotton, but with salt added to dyebath during the cooling phase.
4. High temperature dye runs with dye applied to cotton, with a buffer added initially to control the pH of the dyebath, and with salt added to bath during the cooling phase of the dyeing cycle.

Dyeing.—All dyeings were made in a one pound package dyeing machine which had a 15 liter capacity with the yarn in the machine. For every dyeing run two per cent dye, based on the weight of the yarn, was used. Chemically pure sodium chloride was used in the amount of 15 per cent based on the weight of the yarn. Sodium chloride in pure form was chosen as the salting agent so it would not introduce impurities into the bath which might affect the pH of the bath and hence affect the stability of the dye at high temperatures. The amount of buffer, such as ammonium sulphate required to obtain a pH near 7, was found by actually adding sufficient amounts of buffer to solutions of each dye to give the required pH.

The dyes, salt, and buffers were all weighed accurately on an analytical balance. They were then diluted to five hundred milliliters and added to the dyebath in this form.

The yarn was first placed in the one pound package machine and wet out in 5 cc of Tergitol Penetrant 08 and 15 liters of water at 180° F. for ten minutes. After wetting out, the bath was drained and the yarn thoroughly rinsed with water so as to prevent foaming during the dyeing cycle.

In the normal temperature runs the dyeing machine was filled with water to the fourteen liter mark. The five hundred milliliter solution of dye was then added to the cold water. After an initial mixing a sample of the bath was obtained and the temperature of the bath raised to 212° F. and maintained for thirty minutes. One half of the five hundred milliliters of salt solution was added after each 15 minutes. The total volume at this point was 15 liters. Dyebath samples were taken at various times and temperatures as noted in the dye run tables. Thirty minutes dyeing time at the boil was chosen because the dye manufacturer's specifications of all three dyes indicated maximum exhaustion within this time. The Pontamine Fast Yellow RL is stated to be 90% exhausted at 15 minutes, the Pontamine Fast Orange EGL is supposed to be 90% exhausted in 5 minutes and the Pontamine Blue AX conc. is reported to be 75% exhausted in 15 minutes or 100% exhausted in 30 minutes (22).

The bath was then drained and the dyed yarn thoroughly rinsed with cold water. The package was removed from the machine and hydro-extracted. The yarn was dried in a hot air oven at 212° F., and then conditioned for forty-eight hours at sixty-five per cent relative humidity and 70° F.

The dyebath samples were tested on the colorimeter after cooling, the same day the dye run was made.

The high temperature dyeing runs were conducted in the same manner with the exception of the dyeing cycle and the addition of salt. The dye, or dye and buffer, as appropriate, was added to the cold bath and an initial dye sample drawn. The temperature was then raised to 200° F., with several samples of the bath withdrawn during this time. The top of the expansion chamber was bolted on and the temperature raised to 250° F. as rapidly as possible. Dyeing was allowed to proceed for ten minutes at 250° F., then the bath was cooled rapidly by spraying cold water on the machine to 190° F. The cover of the expansion chamber was removed and all the salt added. The run was ended after a fifteen minute salting phase. Dyebath samples were drawn at regular time and temperature intervals through the high temperature cycle as noted in the dye run tables.

The time of ten minutes for the high temperature phase was determined by a preliminary run for each dye during which dyebath samples were taken at intervals for 20 minutes at the high temperature (Tables 49, 53 and 55). This information indicated that after ten minutes very little additional effect on exhaustion would be realized, by continued dyeing at high temperature without salt.

Colorimetry.—Colorimetric measurements were used to determine the exhaustion of the bath and the dye stability. Colorimetric instruments are comparative; they only compare the optical properties of a given colored solution with those of another standard solution. The Lumetron Colorimeter which was used in these experiments measures the transmission of

light through a solution. The colorimeter can be used to measure the per cent light transmission of a solution of known concentration. From this a plot of concentration versus transmission or optical density can be made. The concentration of a solution of unknown concentration can then be obtained from its per cent transmission by referring to this plot of concentration versus density.

A two per cent dyeing based on the actual weight of yarn was used for all runs. This percentage yields an initial dyebath concentration of a little more than one-half of a gram of dye per liter. This solution was too concentrated to be read on the colorimeter. It was found that a dilution of 50 times gave a solution the transmission readings of which fell within the limits of the colorimeter. This determined that known concentration versus transmission tables would have to be made to cover a range of 0.001 to 0.030 grams per liter.

The original calibration tables of concentration and per cent transmission were made by preparing a solution of exactly 0.03 grams of dye in 1.0 liter of tap water. From this working solution, concentrations of 0.025, 0.020, 0.015, 0.010, and 0.005 grams of dye per liter were then prepared. When salt and buffer were added to the dye for calibration they were dissolved separately and added to the dye solution. Then the solution was mixed with tap water to form exactly one liter of solution, and diluted as above.

With the standard solution of 0.03 grams per liter for each dye it was necessary next to get a spectrum curve of wavelength versus per cent transmission in order to determine the proper filter to be used for transmission readings for each dye. According to Vickerstaff (23) when color

filters are used the band passed by the filter should be narrow and should coincide with the maximum absorption wavelength of the dye solution in order to give a linear relationship between optical density and concentration over the widest possible range.

In order to determine the proper filter for each dye, colorimeter readings were taken for each of the twelve available filters covering the entire range of visible light, using the solution containing 0.03 grams per liter of dye. Thus the filter giving the greatest absorption or least transmission, was determined for each of the three dyes used in this experiment. These absorption values are shown for each dye in Tables 9 through 11.

Next, with the proper filter selected for each dye, readings of light transmission for each of the prepared concentrations were taken with the colorimeter. These values are shown for each dye (and dye, salt, and buffer, combination to be used in the dye runs) in tables 12 through 35. The same tables were then completed by computing values of optical density (D), and absorption index constant (K) as will be explained in Chapter V. These tables were used in computing the concentration of each dyebath sample from a dyebath sample transmission reading.

The dyebath samples were obtained by drawing dye through the dye chamber bleed-off valve. The sample was allowed to cool, then 10 milliliters was pipetted from the sample and diluted with tap water to 500 milliliters. This diluted sample was then measured for per cent transmission in the colorimeter at the wavelength of maximum absorption. By computing the optical density of this transmission from formula (5), and dividing this density by the appropriate absorption index (K) obtained

from Table 36, the concentration of the diluted sample was obtained. Then by multiplying this concentration by fifty (the amount of dilution) a value for the concentration of the original dyebath sample was obtained. The above terms and computations and their limitations are fully discussed in Chapter V.

In operating the colorimeter, tap water was used as a standard reference solution in all cases. One centimeter cuvettes were used as dye sample holders; and a sensitivity ratio of fifteen galvanometer graduations to ten transmission dial graduations was used.

The colorimeter was also used in an attempt to determine the stability to heat of the three dyes used. In addition to obtaining a value for per cent transmission at the wavelength of maximum absorption, complete per cent transmission versus wavelength curves were obtained for several samples taken during each run. If no change in the shape of these curves was noted, this would likely indicate there was no chemical change of the dye during the dye run.

pH Control and Determination.—As the result of some preliminary experiments, it was determined that ammonium sulphate would give a neutral dyebath; sodium acetate an acid dyebath; and ammonium phosphate an alkaline dyebath. Each dyebath sample which was tested on the colorimeter was also tested for pH on the Beckman Calomel electrode pH meter.

Dyed Yarn Strength.—Six break tests were made on each package of dyed yarn, three before and three after rewinding. The average dyed yarn strengths were compared with the undyed yarn strengths.

Light-Fastness Tests.—Light-fastness tests were performed on the dyed yarn in accordance with Test 16A-54 described in the AATCC 1954 Yearbook (24). The samples were exposed to the arc-light in the Fade-Ometer for four twenty-hour intervals. The fading of each yarn was determined by visual inspection. The first appreciable change of shade determined the light-fastness rating of the yarn.

Wash-Fastness Tests.—Wash-fastness tests were performed on the dyed yarn in accordance with AATCC Wash-fastness Test Method 36-54, test number three (25).

CHAPTER V

DISCUSSION OF RESULTS

Colorimetry.—Considerable difficulty was experienced in measuring the dye-bath exhaustions with the colorimeter. With Pontamine Fast Yellow RL all the dye runs indicate very low dyebath exhaustions. The normal temperature runs (Tables 39 and 40) indicate an overall exhaustion of only 30 per cent. The du Pont Company has not published the exhaustion characteristics of its dyes; however, the Geigy Chemical Corp. (26) has published the exhaustions which should be achieved with its direct dyes. By referring to the Geigy dye with the same prototype number as the du Pont dye used in this thesis an approximate exhaustion for the dyes used may be obtained. This reference indicates an exhaustion of about 60 per cent should be obtained with the Pontamine Fast Yellow RL.

The yellow dye exhaustion results for the high temperature runs are even more suspicious. Tables 49 and 59 indicate an over-all exhaustion of 9.47 and 13.7 per cent respectively. Furthermore samples taken during the middle of some of the yellow and orange high temperature dye runs show more dye in the bath than was put in the machine originally.

The Pontamine Fast Orange EGL dye runs similarly indicate a low exhaustion, but to a much lesser degree. The Geigy prototype dye indicates an exhaustion of 60 per cent should be obtained, and most of the orange exhaustions are over 45 per cent.

The Pontamine Blue AX Conc. dye runs show more reasonable dyebath exhaustions. The blue runs all show dye bath exhaustions of over 64 per cent and are considered more reliable, although data on the actual exhaustion of this dyestuff is not available.

A summary of the exhaustions of all three dyes is shown in Table 2 through 4.

On the basis of the above observations it was concluded that the colorimeter measurements were in error on the yellow dyebath samples, probably somewhat in error on the orange dyebath samples, and slightly in error on the blue dye samples. Although the individual exhaustions can not be called accurate they may be used, with caution, as relative values. In other words although each per cent exhaustion of the Pontamine Fast Orange EGL was low, all of the dye runs showed exhaustions similarly low; and one orange dye run can be roughly compared with another to ascertain changes brought about by the high temperatures or buffer additions to the dye cycle.

The colorimetry error evident with the yellow dye could be made by others attempting to measure dyebath concentrations and exhaustions. Therefore in order to call attention to, and to illustrate, some possible errors that arise, the yellow and orange dye runs are included in this work. It must be emphasized however, that the results, especially the per cent exhaustion, must be questioned. They are included only for illustrative purposes.

The original dyebath concentration was computed for each dye by dividing the number of grams of dye for the run by the known volume of bath. A sample of this same concentration was then prepared and diluted

in the same manner as a sample taken from an actual dye run. The per cent transmission of this diluted sample was then read on the colorimeter, and the concentration computed from this transmission reading. The value obtained using the method of calculation discussed in Chapter V was too high. The results of these tests are shown in Table 1.

This shows that the concentrations calculated from colorimeter readings are higher than the actual dyebath concentrations, and explains why the exhaustions are lower, especially for the yellow dye.

The per cent transmission versus wavelength curve plotted from the data of Table 9, for Pontamine Fast Yellow RL as determined with the colorimeter does not show an absorption maximum. To locate the wavelength of maximum absorption a curve was obtained with the aid of a Beckman spectrophotometer. The results showed that the maximum absorption occurred at 390 millimicrons which comes within the filter of lowest wavelength available for the colorimeter.

The explanation for the observed discrepancies in dyebath exhaustion can be found in the theories of colorimetry. The absorption of light by colored solutions is based on two laws, known as Lambert's law and Beer's law (29). Both laws are applicable to absorption of monochromatic light through perfectly molecularly dispersed solutions. Lambert's law states that light absorbed by a substance is independent of the intensity of the light. This may be stated mathematically as,

$$I_T = I_0 e^{-al}$$

Where I_T is the intensity of light transmitted through a solution of thickness l , I_0 is the intensity of light on the solution, and a is a constant.

Table 1. Concentration of Dyebath Calculated
from Per Cent Transmission of
Diluted Dyebath Sample

| Dye | Actual Concentration of Diluted Sample (grams/liter) | Per Cent Transmission (T) | Concentration of Diluted Sample Computed from (T), (D) & (K) (grams/liter) | Concentration of Original Dye- bath before Dilution (grams/liter) | |
|---------------------------------|--|---------------------------------|--|---|------------|
| | | | | Actual | Calculated |
| Pontamine Fast Yellow RL | 0.119 | 56.0 | 0.135 | 0.544 | 0.678 |
| Pontamine Fast Orange EGL | 0.113 | 52.4 | 0.126 | 0.565 | 0.630 |
| Pontamine Blue AX Conc. | 0.111 | 32.0 | 0.119 | 0.555 | 0.594 |

Beer's law states that the absorption of light in the colored solution is proportional to the number of molecules of absorbing substance through which the light passes. This is expressed mathematically as,

$$I_T = I_O e^{-BC} \quad (2)$$

where B is a constant and C is the concentration of the colored substance. The two laws can be combined,

$$I_T = I_O e^{-KCl} \quad (3)$$

where K is the Absorbancy Index Constant.

The spectrophotometer is constructed so that the intensity of light passing through a dye solution in a glass cell can be compared photoelectrically with the light passing through a similar cell containing a standard solution such as water. The light is dispersed into a spectrum with a diffraction prism and a narrow band of wavelength isolated for transmission. In the colorimeter, color filters are used instead of an expensive prism to render light approximately monochromatic. The colorimeter is calibrated to read directly the percentage transmission of the dye sample as compared with the standard water sample.

Transmission,

$$T = \frac{I_T}{I_O} \times 100 \quad (4)$$

The transmission of a solution is not especially convenient in estimating concentration of dyes as it does not vary linearly with concentration, as does optical density (28). The optical density of a solution is defined by the equation:

$$D = \log_{10} \frac{I_o}{I_T} = \log_{10} \frac{100}{T} \quad (5)$$

This equation can be combined with (3) to give,

$$D = KCl \quad (6)$$

where D is the optical density of the solution, K is the absorbancy index constant, C is the concentration of the solution in grams per liter, and l is the thickness of the solution in centimeters.

The validity of Beer's law has been questioned by many observers; particularly when working with the colorimeter with color filters, it was found that a linear relation between concentration and optical density did not always occur. Vickerstaff (29) states that the apparent discrepancy is not due to a breakdown of Beer's law but to a fundamental error of the instrument in not using monochromatic light.

Formula (5) is the one normally used with a colorimeter or spectrophotometer; when density is plotted against concentration it should yield a straight line. This is possible, as mentioned before, only with monochromatic light through a dye in perfectly molecular solution. In this experiment neither condition was possible. The colorimeter uses a filament white light source which is transmitted through filters which can only reduce the light to a band thirty millimicrons wide, instead of true monochromatic light. The dyes were not tested for molecular dispersion but as some dyes are known to aggregate this may have introduced additional error.

In view of these known errors in colorimetry it was expected that the dyes might depart somewhat from Beer's law. In trial runs with

precisely controlled very dilute concentrations of dye, it was found that when density obtained from formula (5) was plotted against concentration the resulting line was not straight but slightly curved for each dye. As the line thus generated by optical density and concentration was fairly close to being a straight line it was concluded the dye solutions were measurable, that is the solutions followed Beer's law closely enough to be in accord with Vickerstaff (30) who states the optical density of a solution is directly proportional to its concentration if the thickness of a solution is constant. He advocates computing the constant K for each dye as the most convenient method of determining concentration of dye samples.

As a trial the absorbancy index (K) was computed for each transmission reading of each concentration previously noted. This was done by rewriting formula (6) to

$$K = D/Cl \quad (7)$$

Where D is optical density as computed from formula (5), C is known prepared concentration in grams per liter, and l is width of cell which is one centimeter. The absorbancy index was averaged for each dye, and dye, buffer, salt combination. The results are shown in Tables 12-36. The absorbancy index was found quite constant for the blue dye, fairly constant for the orange, and quite variable for the yellow dye.

By using the now known absorbancy index (K) for each dye solution the concentration of each sample was computed directly by using formula (6) rewritten as,

$$C = D/Kl \quad (8)$$

By checking several dye runs and obtaining the concentration by referring to curves plotted from formulas (4) and (5), and by obtaining the concentration of the same samples by computing directly from formula (8), it was found that all three methods gave relatively similar results. It is questionable as to which method is the most accurate but it can be noted that all three are simply different presentations of the same basic transmission versus known concentration data.

It was decided that the formula (8) method of computing concentrations from sample transmission readings would be used in this investigation.

The formula (8) method could not be used if the absorption index constant (K) was not constant for each concentration. For instance with the Pontamine Fast Orange EGL dye each K is relatively the same for a particular dye-salt combination. The same is true with the K's determined for Pontamine Blue AX conc. By using an average K the formula method gives practically the same result as the graphical method. The Yellow absorption "constants" (K) are not constant. They vary from 15 to 22.3 on the same table of dye-salt combination. Without a fairly constant K the formula cannot be used, even if an average constant is found, as this indicates a non-linear relationship between density and concentration. In the case of the yellow dye the formula (8) should not be used.

Vickerstaff (31) states that even when precautions are taken to eliminate errors by using monochromatic light a departure from Beer's law may still be possible due to a change in the condition of the dye concentration. This change is generally because of a change in aggregation of the molecules of the dye. He states that several investigators have found some very marked tendencies by direct dyes to change from single

molecules at low concentrations to double molecules at higher concentrations. He found that the maximum absorption points, as obtained from wavelength versus transmission, of some direct dyes did not remain at a constant wavelength, with varying concentrations, but moved towards lower wavelengths with increasing concentrations.

From this it may be assumed that even though a straight line relationship between optical density and concentration was found for a dilute sample, this relationship may not hold for a more concentrated dyebath. In this experiment by using a dilute sample and multiplying the concentration obtained by the dilution factor, the actual dyebath concentration was obviously not obtained. Because of this it is thought that dilute samples are not always related to concentrated samples and the method used was wrong.

In a concentrated solution (0.5 g/l) the yellow dye is very red; when diluted so it can be read on the colorimeter (0.03 g/l), it is pale yellow. This change in color alone would indicate different optical properties, and that the diluted solution readings would not necessarily give the actual concentrations. The same color change occurs when the orange dye solution is diluted. The blue dye stays blue at all concentrations which would indicate at least a constant optical property. It is noted that the blue dye gave the best results on the colorimeter.

As the colorimeter can not read concentrated dyebath solutions with the normal cell available, the samples had to be diluted. It now appears that this dilution was the source of error. Dilution can only be done if there is no aggregation or other change of the solution at high concentrations. By using diluted samples which apparently follow Beer's law, it

could not be proven the more concentrated dyebath samples also follow Beer's law. In this case aggregation was not determined but the results indicate the possibility. Stearns (32) recommends, when using the spectrophotometer in analyzing direct dyes, the use of polyethylene oxide condensate together with a pH of 7 (neutral) in the dyebath to prevent aggregation.

An intensive review of the colorimetry literature did not reveal a specific reference that it was appropriate to use diluted sample solutions for colorimeter readings. Mellon (33) did state that in quantitative analysis with the spectrophotometer, dilution of the sample must sometime be done. He states that there must be no change in aggregation with different concentrations, and the solution must follow Beer's law. The method may introduce error due to measuring dilutions, but the error should not be prohibitive.

It would seem the answer to the question is in being able to measure the per cent transmission of light through a actual undiluted dyebath sample. This cannot be done with the present colorimeter using a one centimeter wide cuvette for holding the dye solution. By using a very narrow cuvette or a very narrow cell on the spectrophotometer the undiluted dyebath solution could possibly be measured. This would allow the preparation of actual concentration versus per cent transmission or density curves and their actual relationship could be determined without involving dilution or aggregation errors, provided, of course, polyethylene oxide condensate, or some similar compound was used to prevent aggregation.

The Calco Division of the American Cyanamid Company, Bound Brook, New Jersey has developed a special instrument, the Dyeometer, which measures

accurately dyebath concentrations. As described by Kienle (34) the Dyeometer consists of two units, the dyebath chamber, and the cell measuring unit. A sample of the dyebath is continuously put through the cell unit. The cell unit is a special glass unit constructed to allow photoelectric measurement of the dye solution. A spectrophotometer is used to actually measure the concentration in the cell unit. The dyebath of any concentration can be measured directly, without dilution, by using several specially made interchangeable cell units of different thicknesses. The cell widths vary from one to ten millimeters in width.

Simon (35) similarly found that dyebaths could be measured in concentrated form with a spectrophotometer by putting the dye solution through a special absorption cell that can be varied in thickness. He found that dyebaths of most common dyes could be measured in this cell which can be adjusted from less than one millimeter to eleven millimeters in thickness.

Both Kienle and Simon found good correlation with dyebath exhaustion determined with their special equipment, and dyebath exhaustion data obtained from actual productions runs in industry.

It would seem that special narrow cells of one millimeter to ten millimeters would have to be used with the colorimeter in order to actually measure concentrated dyebath solutions.

It must be concluded that the principle of diluting the dyebath to obtain colorimeter readings with a 10 millimeter cell, as was done in this work, gives inaccurate results.

Dyeing Results.—For this work it was desired to use direct cotton dyes which are used a great deal in dyeing cellulose today. The dyes were

chosen because of their popularity, and because they represent a dye for each leveling class. It was felt that if an already popular dye which gave good results at normal temperature also gave good results when applied in less time at high temperature, then the applicability of the new method would be more convincingly demonstrated. The dyes used are listed in Table 5, with their properties.

It was hoped that the dyes would not be stable at high temperatures in order that a determination of the effect of buffer control of the pH of the dyebath in retarding breakdown of the dye could be ascertained. By plotting curves of per cent transmission versus wavelength from each of the heat stability tables (which immediately follow their respective dye run data tables) it can be seen that the curve for the beginning and the curve for the end of the dye run are similar. This indicates that, within the limitations of the colorimeter, the dyes were stable for each high temperature run. The action of the various buffers used to give alkaline, neutral, and acid dyebaths therefore had no demonstrable effect on the heat stability of these particular dyes.

By visual inspection of the dyed yarns it was determined that the addition of a buffer with high temperature did give the orange dyed yarn a brighter shade. Little effect of the buffers was noticed on the shade of yellow and blue dyed yarns.

It was particularly noted that all the buffers used imparted a slightly better light-fastness to all three dyes.

The buffers did affect the exhaustion of the baths. The ammonium sulphate and ammonium phosphate buffers, with high temperature especially, increased the overall dyebath exhaustion as compared to the exhaustion

obtained at high temperatures without these buffers. The sodium acetate made little difference in the high temperature exhaustions.

The temperature did affect the exhaustions as was expected. The high temperature alone with Pontamine Fast Orange EGL lowered the exhaustion slightly as compared with normal temperature dyeing. However, when a buffer was added to the orange dye the exhaustion was increased. For instance high temperature alone gave an exhaustion of 41 per cent; when ammonium sulphate was used with high temperature the exhaustion increased to 61.5 per cent. The high temperature alone raised the exhaustion of Pontamine Blue AX eleven per cent over normal temperatures, and when a buffer was added the exhaustion was increased slightly more. The actual exhaustions for each dye, and dye buffer combination, are summarized in Tables 2 through 4.

The normal dye runs were of forty minutes duration. The high temperature dye runs were of sixty minutes duration, which included ten minutes at 250° F., and fifteen minutes at 190° F. for salting. The rest of the sixty minutes was required to raise and lower the temperature, and if this time could be shortened, although it probably would not affect the dyeing, it would speed the application. On the package dyeing machine used, the high temperature application did take longer because of the time required to attain high temperature.

As the Pontamine Blue AX gave better exhaustions when applied at high temperature and appeared a more level and deeper shade on the yarn, it would seem logical that high temperature is most applicable to the Class C, temperature controllable, hard to level type direct dyes.

Table 2. Comparison of Dyebath Exhaustions
for Pontamine Fast Yellow RL

| Type Run | Average Dyebath Per Cent Exhaustion | Average Time of Dye Runs in Minutes | Change in Time from Normal in Minutes | Per Cent Change in Exhaustion from Normal |
|---------------------------------|--|---|---|--|
| Normal Temp. | 30.3 | 40 | | |
| High Temp. with salt only | 9.47 | 85 | 45 More | 20.8 Less |
| High Temp. with pH (7.5) | 13.7 | 85 | 45 More | 16.6 Less |
| High Temp. pH (6.0) | 27.5 | 45 | 5 More | 2.8 Less |
| High Temp. pH (8.5) | 19.0 | 60 | 20 More | 11.3 Less |

Table 3. Comparison of Dyebath Exhaustions
for Pontamine Fast Orange EGL

| Type Run | Average Dyebath Per Cent Exhaustion | Average Time of Dye Runs in Minutes | Change in Time from Normal in Minutes | Per Cent Change in Exhaustion from Normal |
|------------------------------------|--|---|---|--|
| Normal Temp. Dyeing | 47.0 | 35 | | |
| High Temp. Dyeing, salt only | 45.3 | 85 | 50 More | 1.7 Less |
| High Temp. pH (7.5) | 61.5 | 55 | 20 More | 14.5 More |
| High Temp. pH (8.5) | 50.8 | 57 | 22 More | 2.2 More |
| High Temp. pH (6.0) | 53.8 | 58 | 23 More | 6.8 More |

Table 4. Comparison of Dyebath Exhaustions
for Pontamine Blue AX Conc.

| Type Run | Average Dyebath Per Cent Exhaustion | Average Time of Dye Runs in Minutes | Change in Time from Normal in Minutes | Per Cent Change in Exhaustion from Normal |
|-------------------------|--|---|---|--|
| Normal Temp. Dyeing | 63.9 | 45 | | |
| High Temp. salt only | 75.0 | 80 | 35 More | 11.1 More |
| High Temp. pH (7.8) | 76.3 | 60 | 15 More | 12.4 More |
| High Temp. pH (9.8) | 66.9 | 65 | 20 More | 3.0 More |
| High Temp. pH (6.0) | 76.1 | 67 | 22 More | 12.2 More |

As the Pontamine Fast Orange gave much better exhaustions, and brightness, when high temperature and a buffer was used it would seem that the buffer is most applicable to the Class B or salt-controllable leveling type direct dye.

Light-Fastness Results.—All of the dyes faded within forty hours in the Fade-Ometer. The Pontamine Fast Orange EGL faded just slightly at forty hours, and was still only slightly affected after eighty hours in the Fade-Ometer. The Pontamine Fast Yellow RL faded just appreciably in twenty hours, but was considerably deteriorated after forty hours. The Pontamine Blue AX was not light fast. It faded just appreciably within five hours, and was greatly deteriorated after twenty hours.

The low temperature applied dyes and the high temperature applied dyes faded just appreciably at the same time, and therefore must be given the same light-fastness classification. It was noted however that the high temperature applied dyes were subject to less deterioration overall when exposed up to eighty hours. Thus it can be stated that the light fastness was slightly improved by high temperature for the orange and blue dye especially. This improvement is probably not the result of a better chemical resistance, but due to better diffusion of dye into the fibers, and more dye on the yarn.

Wash-Fastness Results.—All of the dyes and various dye buffer combinations bled onto the white cotton backing sewn to the tested yarn sample during the wash-fast test. Direct dyes are not notably wash-fast without after treatment, and the high temperature, or buffers, did not improve the wash-fastness of the three dyes used.

Yarn Strength Test.—The overall average strength of the yarn before dyeing was 1.248 pounds. The overall strength of the dyed yarns was 1.193 pounds, a slight decrease. This loss in strength was just as applicable to the high temperature samples as to the normal temperature samples of yarn. It is therefore stated that high temperature application of dyes has no significant effect on the strength of the yarn.

CHAPTER VI

CONCLUSIONS

The remarks which follow are applicable only to the three direct cotton dyes used in this investigation. One direct dye representing a leveling class can not be considered to reflect the general characteristics of the entire class. At best the results of this investigation can be compared with the results of other investigations for an indication of how the remainder of the dyes in each class might react to high temperature application.

High temperatures can be used to apply these three dyes successfully. The dyeings were as good in every way, and slightly superior in light fastness, as the normal temperature applied dyeings. There was no significant loss in strength of the yarn, or loss of shade of the dye color, when high temperature application was used.

Whether the high temperature method is economical, or necessary to get the best possible application, must still be determined. With an efficient dyeing machine the time of high temperature application could be reduced below the time required for dyeing at the boil, but this saving in time would be small and would not seem to justify the added expense from either an economic or a technical standpoint.

The results of this experiment do not indicate a significant improvement in the high temperature applied dyes investigated to warrant recommendation of the method. The Class C dye used gave better exhaustions

with high temperature, and this indicates the Class C, or temperature controllable hard to level dyes, are benefited by the high temperature technique more than Class A or B direct dyes. Whatever improvement may be gained by using high temperature application of direct dyes on cotton would seem to be with the Class C dyes only.

The difficulties experienced in measuring dyebath concentration were the result of inadequate information on the subject of colorimetry of dyebath solutions. The errors noted may have been made in other dyebath measurements by other investigators. If diluted samples of the dyebath are used for colorimetric light transmission measurements, this fact should be stated in all published articles, as dilution has a direct bearing on the accuracy of the measurement.

When a direct dye is stable at high temperatures the use of a buffer to control the pH is apparently not necessary.

Even though high temperatures may give greater diffusion and leveling the most powerful dyeing assistant for direct dyes is salt. In all dye runs, except the yellow, very little dye was put on the fiber with temperature until the dyebath was salted. In fact high temperature in all cases actually reduced the amount of dye on the yarn, and the yarn was not really dyed until the bath was cooled and salt added.

CHAPTER VII

RECOMMENDATIONS

Only three direct dyes were tested in this work as to heat stability and exhaustion at high temperatures. It has been shown that these dyes can be applied at high temperature without dyestuff breakdown, or color change. In order to get a complete picture, and before the dyeing industry can actually realize any possible benefits, each direct dye must be tested for heat stability. This can best be done by the dyestuff manufacturers.

It was found that the buffers used imparted to the dyes a better resistance to overall fading. It was also found that the buffers in combination with high temperature gave better exhaustions to the Class B or salt-controllable leveling type direct dye used. The role of the buffers in giving these results should be investigated.

A more thorough study of colorimetry as applicable to dye solutions should be made. All of the dyes should be tested for aggregation and color differences at varying concentrations. The results of these investigations should be published together with the most practical and accurate method of measuring dye solution concentrations with standard equipment.

Until the above empirical knowledge is obtained, the dyeing industry will not be able to determine whether any material benefit is to be gained from the use of high temperatures in applying direct dyes to cotton.

APPENDIX

Table 5. List of Dyes Used

Manufacturer: E. I. du Pont de Nemours and Company, Inc.

| Direct Cotton Dye | Light Fastness Rating | Wash Fastness Rating | Solubility in Water |
|---|-----------------------------|----------------------------|-------------------------------------|
| Class A | | | |
| Pontamine Fast Yellow RL best affinity 120° F., pr. 582 | 4 | 5 | Very Sol. Hot or Cold |
| Class B | | | |
| Pontamine Fast Orange EGL best affinity 160° F., pr. 72 | 4 | 5 | Very Sol. Hot or Cold |
| Class C | | | |
| Pontamine Blue AX Conc. best affinity 190° F., C.I. 502 | 1 | 5 | Moderately Sol. - Hot or Cold |

Table 6. Yarn Number of Scoured,
Undyed Cotton Yarn

| Sample Number | Weight in Grains of 120 Yards | Yarn Number |
|------------------|----------------------------------|----------------|
| 1 | 61.5 | 16.25 |
| 2 | 63.8 | 15.68 |
| 3 | 64.0 | 15.62 |
| 4 | 61.6 | 16.24 |
| 5 | 63.9 | 15.65 |
| 6 | 61.1 | 16.37 |
| 7 | 59.9 | 16.70 |
| 8 | 62.4 | 16.05 |
| 9 | 68.1 | 14.69 |
| 10 | 65.6 | 15.22 |
| 11 | 63.2 | 15.80 |
| 12 | 59.8 | 16.70 |
| 13 | 61.4 | 16.27 |
| 14 | 62.8 | 15.91 |
| 15 | 68.6 | 14.59 |
| 16 | 65.4 | 15.28 |
| 17 | 63.7 | 15.69 |
| 18 | 64.1 | 15.60 |
| 19 | 63.5 | 15.75 |
| 20 | 59.7 | 16.77 |
| 21 | 68.2 | 14.67 |
| 22 | 61.4 | 16.28 |
| 23 | 60.3 | 16.59 |
| Total | | 364.73 |
| Average | | 15.85 |

Table 7. Twist of Scoured, Undyed
Cotton Yarn in Turns per Inch

Direction of Twist: "Z"

| Sample Number | Turns per Inch |
|------------------|-------------------|
| 1 | 17.5 |
| 2 | 18.2 |
| 3 | 19.78 |
| 4 | 16.8 |
| 5 | 18.2 |
| 6 | 16.5 |
| 7 | 17.5 |
| 8 | 19.6 |
| 9 | 18.9 |
| 10 | 19.7 |
| 11 | 18.55 |
| 12 | 16.5 |
| 13 | 18.8 |
| 14 | 17.4 |
| 15 | 18.1 |
| 16 | 19.8 |
| 17 | 18.5 |
| 18 | 17.7 |
| 19 | 17.6 |
| 20 | 18.45 |
| 21 | 18.55 |
| 22 | 17.9 |
| 23 | 16.9 |
| Total | 418.03 |
| Average | 18.17 |

Table 8. Single Strand Breaking Strength
of Scoured, Undyed Cotton Yarn

| Sample Number | Strength (pounds) (average of 3 breaks) |
|------------------|---|
| 1 | 1.22 |
| 2 | 1.20 |
| 3 | 1.34 |
| 4 | 1.25 |
| 5 | 1.21 |
| 6 | 1.15 |
| 7 | 1.22 |
| 8 | 1.18 |
| 9 | 1.38 |
| 10 | 1.25 |
| 11 | 1.26 |
| 12 | 1.09 |
| 13 | 1.26 |
| 14 | 1.19 |
| 15 | 1.55 |
| 16 | 1.38 |
| 17 | 1.14 |
| 18 | 1.34 |
| 19 | 1.18 |
| 20 | 1.20 |
| 21 | 1.27 |
| 22 | 1.24 |
| 23 | 1.18 |
| Total | 28.68 |
| Average | 1.24 |

Table 9. Light Absorption Percentages
for Pontamine Fast Yellow RL

| Value of Transmission of Monochromatic Filter (millimicrons) | Color | Percentage Transmission of Light | Percentage Absorption of Light |
|--|--------|--|--------------------------------------|
| 390 | Violet | 31 | 69 |
| 420 | Blue | 40.6 | 59.4 |
| 440 | Blue | 51.4 | 48.6 |
| 465 | Blue | 67.4 | 32.6 |
| 490 | Green | 83.7 | 16.3 |
| 515 | Green | 88.6 | 11.4 |
| 550 | Green | 99.0 | 1.0 |
| 575 | Amber | 99.3 | .7 |
| 595 | Orange | 99.6 | .4 |
| 620 | Red | 100 | 0 |
| 640 | Red | 99.6 | .4 |
| 660 | Red | 99.6 | .4 |

Composition of Solution:

1 gram of dye
8 grams of sodium chloride
Sufficient tap water to make one
liter of solution

The above solution was then diluted to yield a concentration of .03 gram
of dye per liter of solution.

Table 10. Light Absorption Percentages
for Pontamine Fast Orange EGL

| Value of Transmission of Monochromatic Filter (millimicrons) | Color | Percentage Transmission of Light | Percentage Absorption of Light |
|--|--------|--|--------------------------------------|
| 390 | Violet | 20.5 | 79.5 |
| 420 | Blue | 20.2 | 79.8 |
| 440 | Blue | 25.0 | 75.0 |
| 465 | Blue | 40.8 | 59.2 |
| 490 | Green | 58.0 | 42.0 |
| 515 | Green | 76.6 | 23.4 |
| 550 | Green | 97.1 | 2.9 |
| 575 | Amber | 99.0 | 1.0 |
| 595 | Orange | 99.4 | .6 |
| 620 | Red | 99.9 | .1 |
| 640 | Red | 99.9 | .1 |
| 660 | Red | 99.9 | .1 |

Composition of Solution:

1 gram dye
8 grams sodium chloride
Sufficient tap water to make one
liter of solution

The above solution was then diluted to yield a concentration of .03 grams of dye per liter of solution.

Table 11. Light Absorption Percentages
for Pontamine Blue AX Conc.

| Value of Transmission of Monochromatic Filter (millimicrons) | Color | Percentage Transmission of Light | Percentage Absorption of Light |
|--|--------|--|--------------------------------------|
| 390 | Violet | 61.9 | 39.1 |
| 420 | Blue | 60.4 | 39.6 |
| 440 | Blue | 59.0 | 41.0 |
| 465 | Blue | 55.5 | 44.5 |
| 490 | Green | 30.5 | 69.5 |
| 515 | Green | 21.1 | 78.9 |
| 550 | Green | 5.6 | 94.4 |
| 575 | Amber | 9.6 | 90.4 |
| 595 | Orange | 12.7 | 87.3 |
| 620 | Red | 20.6 | 79.4 |
| 640 | Red | 37.1 | 62.9 |
| 660 | Red | 44.4 | 55.6 |

Composition of Solution:

1 grams of dye
8 grams of sodium chloride
Sufficient tap water to make one
liter of solution

The above solution was then diluted to yield a concentration of .03 gram
of dye per liter of solution.

Table 12. Light Transmission for
Pontamine Fast Yellow RL

| Concentration of Dye (grams/liter) (C) | Per Cent Transmission (T) | Optical Density (D) | Absorbancy Index (K) |
|---|---------------------------------|---------------------------|----------------------------|
| 0.03 | 22.0 | 0.658 | 21.9 |
| 0.025 | 28.3 | 0.548 | 21.9 |
| 0.02 | 36.7 | 0.435 | 21.8 |
| 0.015 | 54.4 | 0.264 | 21.8 |
| 0.01 | 63.4 | 0.198 | 19.8 |
| 0.005 | 83.2 | 0.080 | 16.0 |
| Total K | | | 107.2 |
| Average K | | | 17.85 |

Composition of Solution:

1 gram of dye
8 grams sodium chloride
Sufficient tap water to make one
liter of solution

The above solution was then diluted to yield the working concentrations listed above.

Monochromatic Filter Used in Colorimeter:

Violet 390 millimicrons

Scale ratio used on Colorimeter

15 Galvanometer Graduations to
10 Transmission Dial Graduations

Summary of computation:

$$D = \log_{10} \frac{100}{T}, \text{ formula (5)}$$

$$K = \frac{D}{CI}, \text{ formula (7)}$$

D and K are pure numbers, without units.

Table 13. Light Transmission for
Pontamine Fast Yellow R1

| Concentration of Dye (grams/liter) (C) | Per Cent Transmission (T) | Optical Density (D) | Absorbancy Index (K) |
|---|---------------------------------|---------------------------|----------------------------|
| 0.03 | 24.5 | 0.611 | 20.4 |
| 0.025 | 28.2 | 0.550 | 22.0 |
| 0.02 | 38.4 | 0.416 | 20.8 |
| 0.015 | 56.3 | 0.250 | 16.75 |
| 0.01 | 65.8 | 0.181 | 18.1 |
| 0.005 | 82.7 | 0.083 | 16.55 |
| Total K | | | 114.60 |
| Average K | | | 19.10 |

Composition of Solution:

1 gram of dye
2 grams ammonium sulphate
Sufficient tap water to make one
liter of solution

The above solution was then diluted to yield the concentrations listed above.

Monochromatic Filter Used in Colorimeter:

Violet 390 millimicrons

Scale ratio used on Colorimeter:

15 Galvanometer Graduations to
10 Transmission Dial Graduations

Table 14. Light Transmission for
Pontamine Fast Yellow RL

| Concentration of Dye (grams/liter) (C) | Per Cent Transmission (T) | Optical Density (D) | Absorbancy Index (K) |
|---|---------------------------------|---------------------------|----------------------------|
| 0.03 | 25.7 | 0.590 | 19.65 |
| 0.025 | 27.1 | 0.567 | 23.05 |
| 0.02 | 35.5 | 0.450 | 22.50 |
| 0.015 | 54.2 | 0.266 | 17.71 |
| 0.01 | 66.7 | 0.176 | 17.60 |
| 0.005 | 87.7 | 0.056 | 11.2 |
| Total K | | | 111.71 |
| Average K | | | 18.62 |

Composition of Solution:

1 gram of dye
2 grams of sodium acetate
Sufficient tap water to give one
liter of solution

The above solution was then diluted to give the concentrations listed above.

Monochromatic Filter Used in Colorimeter:

Violet 390 millimicrons

Scale ratio used on Colorimeter:

15 Galvanometer Graduations to
10 Transmission Dial Graduations

Table 15. Light Transmission for
Pontamine Fast Yellow RL

| Concentration of Dye (grams/liter) (C) | Per Cent Transmission (T) | Optical Density (D) | Absorbancy Index (K) |
|---|---------------------------------|---------------------------|----------------------------|
| 0.03 | 21.5 | 0.668 | 22.30 |
| 0.025 | 32.2 | 0.492 | 19.70 |
| 0.02 | 34.2 | 0.465 | 23.22 |
| 0.015 | 56.0 | 0.252 | 16.81 |
| 0.01 | 64.7 | 0.189 | 18.90 |
| 0.005 | 84.1 | 0.075 | 15.00 |
| Total K | | | 100.93 |
| Average K | | | 18.60 |

Composition of Solution:

1 gram of dye
2 grams of ammonium phosphate
Sufficient water to give one
liter of solution

The above solution was then diluted to give concentrations listed above.

Monochromatic Filter Used in Colorimeter:

Violet 390 millimicrons

Scale ratio used on Colorimeter:

15 Galvanometer Graduations to
10 Transmission Dial Graduations

Table 16. Light Transmission for
Pontamine Fast Yellow RL

| Concentration of Dye (grams/liter) (C) | Per Cent Transmission (T) | Optical Density (D) | Absorbancy Index (K) |
|---|---------------------------------|---------------------------|----------------------------|
| 0.03 | 27.9 | 0.555 | 18.50 |
| 0.025 | 33.0 | 0.481 | 19.25 |
| 0.02 | 36.6 | 0.439 | 20.95 |
| 0.015 | 56.8 | 0.246 | 16.40 |
| 0.01 | 66.8 | 0.175 | 17.50 |
| 0.005 | 84.5 | 0.073 | 14.65 |
| Total K | | | 92.6 |
| Average K | | | 18.52 |

Composition of Solution:

1 gram of dye
Sufficient tap water to make one
liter of solution

The above solution was then diluted to give concentrations listed above.

Monochromatic Filter Used in Colorimeter:

Violet 390 millimicrons

Scale ratio used on Colorimeter:

15 Galvanometer Graduations to
10 Transmission Dial Graduations

Table 17. Light Transmission for
Pontamine Fast Yellow RL

| Concentration of Dye (grams/liter) (C) | Per Cent Transmission (T) | Optical Density (D) | Absorbancy Index (K) |
|---|---------------------------------|---------------------------|----------------------------|
| 0.030 | 22.8 | 0.642 | 21.21 |
| 0.025 | 30.5 | 0.516 | 20.65 |
| 0.020 | 45.6 | 0.342 | 17.20 |
| 0.015 | 58.2 | 0.235 | 15.65 |
| 0.010 | 69.1 | 0.160 | 16.00 |
| 0.005 | 83.6 | 0.079 | 15.80 |
| Total K | | | 106.51 |
| Average K | | | 17.75 |

Composition of Solution:

1 gram of dye
2 grams ammonium sulphate
8 grams sodium chloride
Sufficient tap water to make one
liter of solution

The above solution was then diluted to give concentrations listed above.

Monochromatic Filter Used in Colorimeter:

Violet 390 millimicrons

Scale ratio used on Colorimeter:

15 Galvanometer Graduations to
10 Transmission Dial Graduations

Table 18. Light Transmission for
Pontamine Fast Yellow RL

| Concentration of Dye (grams/liter) (C) | Per Cent Transmission (T) | Optical Density (D) | Absorbancy Index (K) |
|---|---------------------------------|---------------------------|----------------------------|
| 0.030 | 23.4 | 0.631 | 21.02 |
| 0.025 | 27.8 | 0.559 | 22.35 |
| 0.020 | 39.5 | 0.404 | 20.20 |
| 0.015 | 58.1 | 0.236 | 15.75 |
| 0.010 | 66.4 | 0.178 | 17.80 |
| 0.005 | 82.8 | 0.082 | 16.40 |
| Total K | | | 113.52 |
| Average K | | | 18.92 |

Composition of Solution:

1 gram of dye
2 grams sodium acetate
8 grams sodium chloride
Sufficient tap water to make one
liter of solution

The above solution was then diluted to give dye concentrations listed above.

Monochromatic Filter Used in Colorimeter:

Violet 390 millimicrons

Scale ratio used on Colorimeter:

15 Galvanometer Graduations to
10 Transmission Dial Graduations

Table 19. Light Transmission for
Pontamine Fast Yellow RL

| Concentration of Dye (grams/liter) (C) | Per Cent Transmission (T) | Optical Density (D) | Absorbancy Index (K) |
|---|---------------------------------|---------------------------|----------------------------|
| 0.030 | 22.0 | 0.658 | 21.95 |
| 0.025 | 26.7 | 0.574 | 22.95 |
| 0.020 | 36.5 | 0.438 | 21.90 |
| 0.015 | 51.1 | 0.291 | 19.42 |
| 0.010 | 67.0 | 0.174 | 17.40 |
| 0.005 | 82.4 | 0.084 | 16.80 |
| Total K | | | 120.42 |
| Average K | | | 20.02 |

Composition of Solution:

1 gram of dye
2 grams of ammonium phosphate
8 grams of sodium chloride
Sufficient tap water to make one
liter of solution

The above solution was then diluted to give dye concentrations listed above.

Monochromatic Filter Used in Colorimeter:

Violet 390 millimicrons

Scale ratio used on Colorimeter:

15 Galvanometer Graduations to
10 Transmission Dial Graduations

Table 20. Light Transmission for
Pontamine Fast Orange EGL

| Concentration of Dye (grams/liter) (C) | Per Cent Transmission (T) | Optical Density (D) | Absorbancy Index (K) |
|---|---------------------------------|---------------------------|----------------------------|
| .03 | 20.2 | 0.695 | 23.19 |
| .025 | 27.2 | 0.566 | 22.61 |
| .02 | 34.1 | 0.455 | 22.75 |
| .015 | 46.5 | 0.333 | 22.15 |
| .01 | 59.0 | 0.229 | 22.90 |
| .005 | 77.2 | 0.113 | 22.60 |
| Total K | | | 136.20 |
| Average K | | | 22.70 |

Composition of Solution:

1 gram of dye
8 grams of sodium chloride
Sufficient tap water to make one
liter of solution

The above solution was then diluted to yield the working concentrations listed above.

Monochromatic Filter Used in Colorimeter:

Blue 420 millimicrons

Scale ratio used on Colorimeter:

15 Galvanometer Graduations to
10 Transmission Dial Graduations

Table 21. Light Transmission for
Pontamine Fast Orange EGL

| Concentration of Dye (grams/liter) (C) | Per Cent Transmission (T) | Optical Density (D) | Absorbancy Index (K) |
|---|---------------------------------|---------------------------|----------------------------|
| 0.030 | 19.7 | 0.706 | 23.50 |
| 0.025 | 26.0 | 0.585 | 23.40 |
| 0.020 | 33.5 | 0.475 | 23.75 |
| 0.015 | 51.4 | 0.289 | 19.25 |
| 0.010 | 59.8 | 0.223 | 22.30 |
| 0.005 | 77.8 | 0.109 | 21.80 |
| Total K | | | 134.00 |
| Average K | | | 22.33 |

Composition of Solution:

1 gram of dye
2 grams ammonium sulphate
Sufficient water to make one
liter of solution

The above solution was then diluted to give the dye concentrations listed above.

Monochromatic Filter Used in Colorimeter:

Blue 420 millimicrons

Scale ratio used on Colorimeter:

15 Galvanometer Graduations to
10 Transmission Dial Graduations

Table 22. Light Transmission for
Pontamine Fast Orange EGL

| Concentration of Dye (grams/liter) (C) | Per Cent Transmission (T) | Optical Density (D) | Absorbancy Index (K) |
|---|---------------------------------|---------------------------|----------------------------|
| 0.030 | 19.3 | 0.714 | 23.80 |
| 0.025 | 30.1 | 0.522 | 20.92 |
| 0.020 | 34.3 | 0.463 | 23.20 |
| 0.015 | 50.2 | 0.299 | 19.95 |
| 0.010 | 59.6 | 0.225 | 22.50 |
| 0.005 | 78.8 | 0.103 | 20.60 |
| Total K | | | 130.97 |
| Average K | | | 21.83 |

Composition of Solution:

1 gram of dye
2 grams of sodium acetate
Sufficient tap water to make one
liter of solution

The above solution was then diluted to give the dye concentrations listed above.

Monochromatic Filter Used in Colorimeter:

Blue 420 millimicrons

Scale ratio used on Colorimeter:

15 Galvanometer Graduations to
10 Transmission Dial Graduations

Table 23. Light Transmission for
Pontamine Fast Orange EGL

| Concentration of Dye (grams/liter) (C) | Per Cent Transmission (T) | Optical Density (D) | Absorbancy Index (K) |
|---|---------------------------------|---------------------------|----------------------------|
| 0.030 | 19.4 | 0.713 | 23.78 |
| 0.025 | 25.2 | 0.599 | 23.94 |
| 0.020 | 35.6 | 0.448 | 22.42 |
| 0.015 | 45.0 | 0.347 | 23.15 |
| 0.010 | 60.0 | 0.222 | 22.20 |
| 0.005 | 77.2 | 0.113 | 22.59 |
| Total K | | | 138.08 |
| Average K | | | 23.01 |

Composition of Solution:

1 gram of dye
2 grams of ammonium phosphate
Sufficient tap water to make one
liter of solution

The above solution was then diluted to give the concentrations listed above.

Monochromatic Filter Used in Colorimeter:

Blue 420 millimicrons

Scale ratio used on Colorimeter:

15 Galvanometer Graduations to
10 Transmission Dial Graduations

Table 24. Light Transmission for
Pontamine Fast Orange EGL

| Concentration of Dye (grams/liter) (C) | Per Cent Transmission (T) | Optical Density (D) | Absorbancy Index (K) |
|---|---------------------------------|---------------------------|----------------------------|
| 0.030 | 19.8 | 0.704 | 23.45 |
| 0.025 | 28.6 | 0.544 | 21.78 |
| 0.020 | 33.6 | 0.473 | 23.65 |
| 0.015 | 48.9 | 0.311 | 20.75 |
| 0.010 | 59.9 | 0.223 | 22.30 |
| 0.005 | 77.6 | 0.110 | 22.00 |
| Total K | | | 133.93 |
| Average K | | | 22.32 |

Composition of Solution:

1 gram of dye
Sufficient tap water to make one
liter of solution

The above solution was then diluted to give the dye concentrations listed above.

Monochromatic Filter Used in Colorimeter:

Blue 420 millimicrons

Scale ratio used on Colorimeter:

15 Galvanometer Graduations to
10 Transmission Dial Graduations

Table 25. Light Transmission for
Pontamine Fast Orange EGL

| Concentration of Dye (grams/liter) (C) | Per Cent Transmission (T) | Optical Density (D) | Absorbancy Index (K) |
|---|---------------------------------|---------------------------|----------------------------|
| 0.030 | 19.7 | 0.706 | 23.51 |
| 0.025 | 26.1 | 0.583 | 23.35 |
| 0.020 | 34.0 | 0.468 | 23.41 |
| 0.015 | 44.0 | 0.357 | 23.80 |
| 0.010 | 58.1 | 0.236 | 23.60 |
| 0.005 | 76.1 | 0.119 | 23.81 |
| Total K | | | 141.48 |
| Average K | | | 23.58 |

Composition of Solution:

1 gram of dye
2 grams of ammonium sulphate
8 grams of sodium chloride
Sufficient tap water to make one
liter of solution

The above solution was then diluted to give the dye concentrations listed above.

Monochromatic Filter Used in Colorimeter:

Blue 420 millimicrons

Scale ratio used on Colorimeter:

15 Galvanometer Graduations to
10 Transmission Dial Graduations

Table 26. Light Transmission for
Pontamine Fast Orange EGL

| Concentration of Dye (grams/liter) (C) | Per Cent Transmission (T) | Optical Density (D) | Absorbancy Index (K) |
|---|---------------------------------|---------------------------|----------------------------|
| 0.030 | 19.2 | 0.717 | 23.90 |
| 0.025 | 24.2 | 0.616 | 24.61 |
| 0.020 | 34.9 | 0.457 | 22.90 |
| 0.015 | 43.4 | 0.363 | 24.25 |
| 0.010 | 59.0 | 0.229 | 22.90 |
| 0.005 | 76.5 | 0.117 | 23.40 |
| Total K | | | 141.96 |
| Average K | | | 23.66 |

Composition of Solution:

1 gram of dye
2 grams of sodium acetate
8 grams of sodium chloride
Sufficient tap water to make one
liter of solution

The above solution was then diluted to give dye concentrations listed above.

Monochromatic Filter Used in Colorimeter:

Blue 420 millimicrons

Scale ratio used on Colorimeter:

15 Galvanometer Graduations to
10 Transmission Dial Graduations

Table 27. Light Transmission for
Pontamine Fast Orange EGL

| Concentration of Dye (grams/liter) (C) | Per Cent Transmission (T) | Optical Density (D) | Absorbancy Index (K) |
|---|---------------------------------|---------------------------|----------------------------|
| 0.030 | 19.4 | 0.712 | 23.75 |
| 0.025 | 23.9 | 0.622 | 24.85 |
| 0.020 | 32.3 | 0.491 | 24.50 |
| 0.015 | 44.1 | 0.356 | 23.75 |
| 0.010 | 56.9 | 0.245 | 24.50 |
| 0.005 | 75.0 | 0.125 | 25.00 |
| Total K | | | 146.35 |
| Average K | | | 24.39 |

Composition of Solution:

1 gram of dye
2 grams of ammonium phosphate
8 grams of sodium chloride
Sufficient tap water to make one
liter of solution

The above solution was then diluted to give dye concentrations listed above.

Monochromatic Filter Used in Colorimeter:

Blue 420 millimicrons

Scale ratio used on Colorimeter:

15 Galvanometer Graduations to
10 Transmission Dial Graduations

Table 28. Light Transmission for
Pontamine Blue AX Conc.

| Concentration of Dye (grams/liter) (C) | Per Cent Transmission (T) | Optical Density (D) | Absorbancy Index (K) |
|---|---------------------------------|---------------------------|----------------------------|
| .03 | 5.0 | 1.301 | 43.4 |
| .025 | 8.0 | 1.097 | 43.8 |
| .02 | 13.8 | 0.840 | 42.0 |
| .015 | 22.9 | 0.640 | 42.7 |
| .01 | 36.8 | 0.433 | 43.3 |
| .0075 | 47.5 | 0.324 | 43.3 |
| .005 | 61.2 | 0.215 | 43.1 |
| .003 | 73.9 | 0.131 | 43.6 |
| .0025 | 78.8 | 0.103 | 41.3 |
| .002 | 81.5 | 0.088 | 44.0 |
| .001 | 90.0 | 0.046 | 46.0 |
| Total K | | | 430.5 |
| Average K | | | 43.05 |

Composition of Solution:

1 gram of dye
8 grams of sodium chloride
Sufficient tap water to make one
liter of solution

The above solution was then diluted to yield the working concentrations listed above.

Monochromatic Filter Used in Colorimeter:

Green 550 millimicrons

Scale ratio used on Colorimeter:

15 Galvanometer Graduations to
10 Transmission Dial Graduations

Table 29. Light Transmission for
Pontamine Blue AX Conc.

| Concentration of Dye (grams/liter) (C) | Per Cent Transmission (T) | Optical Density (D) | Absorbancy Index (K) |
|---|---------------------------------|---------------------------|----------------------------|
| 0.030 | 5.3 | 1.276 | 42.2 |
| 0.025 | 9.5 | 1.022 | 40.9 |
| 0.020 | 15.2 | 0.817 | 40.8 |
| 0.015 | 26.2 | 0.582 | 38.9 |
| 0.010 | 41.1 | 0.386 | 38.6 |
| 0.005 | 60.2 | 0.221 | 44.2 |
| 0.001 | 89.5 | 0.049 | 49.0 |
| Total K | | | 245.6 |
| Average K | | | 40.93 |

Composition of Solution:

1 gram of dye
2 grams of ammonium sulphate
Sufficient tap water to make one
liter of solution

The above solution was then diluted to give concentrations listed above.

Monochromatic Filter Used in Colorimeter:

Green 550 millimicrons

Scale ratio used on Colorimeter:

15 Galvanometer Graduations to
10 Transmission Dial Graduations

Table 30. Light Transmission for
Pontamine Blue AX Conc.

| Concentration of Dye (grams/liter) (C) | Per Cent Transmission (T) | Optical Density (D) | Absorbancy Index (K) |
|---|---------------------------------|---------------------------|----------------------------|
| 0.030 | 5.5 | 1.260 | 42.0 |
| 0.025 | 8.7 | 1.060 | 42.4 |
| 0.020 | 15.5 | 0.810 | 40.5 |
| 0.015 | 25.1 | 0.600 | 40.0 |
| 0.010 | 37.5 | 0.426 | 42.6 |
| 0.005 | 62.8 | 0.202 | 40.4 |
| 0.001 | 90.5 | 0.044 | 42.0 |
| Total K | | | 289.90 |
| Average K | | | 41.41 |

Composition of Solution:

1 gram of dye
2 grams sodium acetate
Sufficient tap water to make one
liter of solution

The above solution was then diluted to give concentrations listed above.

Monochromatic Filter Used in Colorimeter:

Green 550 millimicrons

Scale ratio used on Colorimeter:

15 Galvanometer Graduations to
10 Transmission Dial Graduations

Table 31. Light Transmission for
Pontamine Blue AX Conc.

| Concentration of Dye (grams/liter) (C) | Per Cent Transmission (T) | Optical Density (D) | Absorbancy Index (K) |
|---|---------------------------------|---------------------------|----------------------------|
| 0.030 | 5.4 | 1.268 | 42.3 |
| 0.025 | 8.7 | 1.060 | 41.2 |
| 0.020 | 15.2 | 0.818 | 40.9 |
| 0.015 | 27.5 | 0.563 | 37.6 |
| 0.010 | 39.9 | 0.399 | 39.9 |
| 0.005 | 60.4 | 0.219 | 43.8 |
| 0.001 | 90.0 | 0.046 | 46.0 |
| Total K | | | 291.7 |
| Average K | | | 41.67 |

Composition of Solution:

1 gram of dye
2 grams of ammonium phosphate
Sufficient tap water to make one
liter of solution

The above solution was then diluted to the concentrations listed above.

Monochromatic Filter Used in Colorimeter:

Green 550 millimicrons

Scale ratio used on Colorimeter:

15 Galvanometer Graduations to
10 Transmission Dial Graduations

Table 32. Light Transmission for
Pontamine Blue AX Conc.

| Concentration of Dye (grams/liter) (C) | Per Cent Transmission (T) | Optical Density (D) | Absorbancy Index (K) |
|---|---------------------------------|---------------------------|----------------------------|
| 0.030 | 5.2 | 1.284 | 42.8 |
| 0.025 | 9.7 | 1.013 | 40.5 |
| 0.020 | 14.7 | 0.803 | 40.2 |
| 0.015 | 23.6 | 0.625 | 41.7 |
| 0.010 | 38.0 | 0.420 | 42.0 |
| 0.005 | 61.0 | 0.215 | 43.0 |
| 0.001 | 87.1 | 0.060 | 41.6 |
| Total K | | | 291.8 |
| Average K | | | 41.68 |

Composition of Solution:

1 gram of dye
Sufficient tap water to make one
liter of solution

The above solution was then diluted to give the dye concentrations listed above.

Monochromatic Filter Used in Colorimeter:

Green 550 millimicrons

Scale ratio used on Colorimeter:

15 Galvanometer Graduations to
10 Transmission Dial Graduations

Table 33. Light Transmission for
Pontamine Blue AX Conc.

| Concentration of Dye (grams/liter) (C) | Per Cent Transmission (T) | Optical Density (D) | Absorbancy Index (K) |
|---|---------------------------------|---------------------------|----------------------------|
| 0.030 | 8.5 | 1.070 | 35.7 |
| 0.025 | 10.8 | 0.977 | 39.0 |
| 0.020 | 19.5 | 0.701 | 35.1 |
| 0.015 | 24.7 | 0.607 | 40.5 |
| 0.010 | 42.2 | 0.375 | 37.5 |
| 0.005 | 64.6 | 0.190 | 38.0 |
| 0.001 | 90.2 | 0.045 | 45.0 |
| Total K | | | 225.8 |
| Average K | | | 37.63 |

Composition of Solution:

1 gram of dye
2 grams ammonium sulphate
8 grams sodium chloride
Sufficient tap water to make one
liter of solution

The above solution was then diluted to give the dye concentrations listed above.

Monochromatic Filter Used in Colorimeter:

Green 550 millimicrons

Scale ratio used on Colorimeter:

15 Galvanometer Graduations to
10 Transmission Dial Graduations

Table 34. Light Transmission for
Pontamine Blue AX Conc.

| Concentration of Dye (grams/liter) (C) | Per Cent Transmission (T) | Optical Density (D) | Absorbancy Index (K) |
|---|---------------------------------|---------------------------|----------------------------|
| 0.030 | 6.3 | 1.201 | 40.2 |
| 0.025 | 9.7 | 1.013 | 40.6 |
| 0.020 | 17.4 | 0.760 | 38.0 |
| 0.015 | 24.0 | 0.620 | 41.4 |
| 0.010 | 41.5 | 0.382 | 38.2 |
| 0.005 | 62.0 | 0.208 | 41.6 |
| 0.001 | 89.6 | 0.049 | 49.0 |
| Total K | | | 240.0 |
| Average K | | | 40.0 |

Composition of Solution:

1 gram of dye
2 grams of sodium acetate
8 grams of sodium chloride
Sufficient tap water to make one
liter of solution

The above solution was then diluted to the dye concentrations listed above.

Monochromatic Filter Used in Colorimeter:

Green 550 millimicrons

Scale ratio used on Colorimeter:

15 Galvanometer Graduations to
10 Transmission Dial Graduations

Table 35. Light Transmission for
Pontamine Blue AX Conc.

| Concentration of Dye (grams/liter) (C) | Per Cent Transmission (T) | Optical Density (D) | Absorbancy Index (K) |
|---|---------------------------------|---------------------------|----------------------------|
| 0.030 | 7.1 | 1.155 | 38.5 |
| 0.025 | 10.8 | 0.988 | 39.5 |
| 0.020 | 17.5 | 0.757 | 37.9 |
| 0.015 | 25.9 | 0.587 | 39.1 |
| 0.010 | 42.0 | 0.377 | 37.7 |
| 0.005 | 62.5 | 0.205 | 41.0 |
| 0.001 | 91.0 | 0.041 | 41.0 |
| Total K | | | 274.70 |
| Average K | | | 39.24 |

Composition of Solution:

1 gram of dye
2 grams ammonium phosphate
8 grams sodium chloride
Sufficient tap water to make one
liter of solution

The above solution was then diluted to give concentrations listed above.

Monochromatic Filter Used in Colorimeter:

Green 550 millimicrons

Scale ratio used on Colorimeter:

15 Galvanometer Graduations to
10 Transmission Dial Graduations

Table 36. Summary of Absorption Indices
Computed in Tables 12 through 35.

| Dye, Buffer Combination | Absorption Index (K) | Absorption Index of Same Dye and Buffer but with Salt Added (K) |
|--|----------------------------|---|
| Pontamine Fast Yellow RL | 18.52 | 17.85 |
| Pontamine Fast Yellow RL with Ammonium Sulphate | 19.10 | 17.75 |
| Pontamine Fast Yellow RL with Sodium Acetate | 18.62 | 18.92 |
| Pontamine Fast Yellow RL with Ammonium Phosphate | 18.60 | 20.02 |
| Pontamine Fast Orange EGL | 22.32 | 22.70 |
| Pontamine Fast Orange EGL with Ammonium Sulphate | 22.33 | 23.58 |
| Pontamine Fast Orange EGL with Sodium Acetate | 21.83 | 23.66 |
| Pontamine Fast Orange EGL with Ammonium Phosphate | 23.01 | 24.39 |
| Pontamine Blue AX Conc. | 41.68 | 43.05 |
| Pontamine Blue AX Conc. with Ammonium Sulphate | 40.93 | 37.63 |
| Pontamine Blue AX Conc. with Sodium Acetate | 41.41 | 40.00 |
| Pontamine Blue AX Conc. with Ammonium Phosphate | 41.67 | 39.24 |

Table 37. Dyeing Cycle Data of Pontamine
Fast Orange EGL at
Normal Temperature

Run 1

Yarn Sample 1

Weight of Yarn 401.5 grams
Weight of Dye 8.46 grams
Weight of Sodium Chloride 65.0 grams
Volume of Dye Bath 15 liters

| Dyebath Sample Number | Time in Minutes | Temp. Degrees F. | Remarks | pH of Bath | Per Cent Transmission Filter 420 mm (T) | Optical Density (D) | Conc. of Dyebath (grams/liter) (C) |
|-----------------------------|-----------------------|------------------------|--------------------------|------------------|--|---------------------------|---|
| 0 | 0 | 90 | Initial conc. | | | | 0.565 |
| 1 | 5 | 180 | Dye only | 8.2 | 61.8 | 0.209 | 0.465 |
| 2 | 10 | 190 | $\frac{1}{2}$ Salt added | | 62.5 | 0.204 | 0.448 |
| 3 | 15 | 190 | | 8.4 | 63.5 | 0.197 | 0.433 |
| 4 | 20 | 190 | $\frac{1}{2}$ Salt added | | 69.2 | 0.159 | 0.351 |
| 5 | 30 | 200 | | 9.2 | 72.6 | 0.139 | 0.307 |

Total Dyebath Exhaustion - 45.8%

Table 38. Dyeing Cycle Data of Pontamine
Fast Orange EGL at
Normal Temperature

Run 2

Yarn Sample 2

Weight of Yarn 454.1 grams
Weight of Dye 9.08 grams
Weight of Sodium Chloride 68.0 grams
Volume of Dye Bath 15.0 liters

| Dyebath Sample Number | Time in Minutes | Temp. Degrees F. | Remarks | pH of Bath | Per Cent Transmission Filter 420 mm (T) | Optical Density (D) | Conc. of Dyebath (grams/liter) (C) |
|-----------------------------|-----------------------|------------------------|--------------------------|------------------|--|---------------------------|---|
| 0 | 0 | 90 | Initial conc. | | | | 0.606 |
| 1 | 5 | 100 | Dye only | 8.2 | 52.8 | 0.277 | 0.621 |
| 2 | 10 | 185 | | | 54.0 | 0.267 | 0.589 |
| 3 | 15 | 212 | $\frac{1}{2}$ Salt added | | 62.2 | 0.206 | 0.454 |
| 4 | 20 | 208 | | 8.4 | 64.8 | 0.188 | 0.414 |
| 5 | 25 | 210 | | | 64.5 | 0.190 | 0.417 |
| 6 | 30 | 210 | $\frac{1}{2}$ Salt added | | 70.0 | 0.155 | 0.341 |
| 7 | 35 | 212 | | | 71.0 | 0.149 | 0.327 |
| 8 | 40 | 212 | | 9.2 | 72.0 | 0.143 | 0.315 |

Total Dyebath Exhaustion - 48.0%

Table 39. Dyeing Cycle Data of Pontamine
Fast Yellow RL at
Normal Temperature

Run 3

Yarn Sample 3

Weight of Yarn 401.5 grams
Weight of Dye 8.03 grams
Weight of Sodium Chloride 60.2 grams
Volume of Dye Bath 15 liters

| Dyebath Sample Number | Time in Minutes | Temp. Degrees F. | Remarks | pH of Bath | Per Cent Transmission Filter 390 mm (T) | Optical Density (D) | Conc. of Dyebath (grams/liter) (C) |
|-----------------------------|-----------------------|------------------------|--------------------------|------------------|--|---------------------------|---|
| 0 | 0 | 90 | Initial conc. | | | | 0.536 |
| 1 | 5 | 90 | Dye only | 8.4 | 68.0 | 0.167 | 0.452 |
| 2 | 10 | 160 | | | 68.0 | 0.167 | 0.452 |
| 3 | 15 | 210 | $\frac{1}{2}$ Salt added | | 69.6 | 0.157 | 0.467 |
| 4 | 20 | 208 | | 8.8 | 69.7 | 0.158 | 0.443 |
| 5 | 25 | 208 | $\frac{1}{2}$ Salt added | | 70.6 | 0.151 | 0.424 |
| 6 | 30 | 210 | | | 72.9 | 0.137 | 0.384 |
| 7 | 35 | 210 | | | 72.9 | 0.137 | 0.384 |
| 8 | 40 | 210 | | 9.0 | 74.1 | 0.130 | 0.364 |

Total Dyebath Exhaustion - 32.2%

Table 40. Dyeing Cycle Data of Pontamine
Fast Yellow RL at
Normal Temperature

Run 4

Yarn Sample 4

Weight of Yarn 408.6 grams
Weight of Dye 8.17 grams
Weight of Sodium Chloride 61.23 grams
Volume of Dye Bath 15 liters

| Dyebath Sample Number | Time in Minutes | Temp. Degrees F. | Remarks | pH of Bath | Per Cent Transmission Filter 390 mm (T) | Optical Density (D) | Conc. of Dyebath (grams/liter) (C) |
|-----------------------------|-----------------------|------------------------|--------------------------|------------------|--|---------------------------|---|
| 0 | 0 | 90 | Initial conc. | | | | 0.545 |
| 1 | 5 | 90 | Dye only | 8.5 | 71.9 | 0.143 | 0.387 |
| 2 | 10 | 170 | | | 71.0 | 0.149 | 0.402 |
| 3 | 15 | 190 | | | 70.5 | 0.152 | 0.410 |
| 4 | 20 | 208 | $\frac{1}{2}$ Salt added | 8.8 | 72.4 | 0.140 | 0.393 |
| 5 | 25 | 200 | | | 72.6 | 0.139 | 0.380 |
| 6 | 30 | 210 | | | 72.7 | 0.139 | 0.380 |
| 7 | 35 | 200 | $\frac{1}{2}$ Salt added | | 75.6 | 0.122 | 0.341 |
| 8 | 40 | 208 | | | 74.4 | 0.128 | 0.358 |
| 9 | 45 | 210 | | 9.1 | 72.7 | 0.139 | 0.389 |

Total Dyebath Exhaustion - 28.5%

Table 41. Dyeing Cycle Data of Pontamine
Blue AX Conc. at
Normal Temperature

Run 5

Yarn Sample 5

Weight of Yarn 419.1 grams
Weight of Dye 8.38 grams
Weight of Sodium Chloride 62.86 grams
Volume of Dye Bath 15 liters

| Dyebath Sample Number | Time in Minutes | Temp. Degrees F. | Remarks | pH of Bath | Per Cent Transmission Filter 550 mm (T) | Optical Density (D) | Conc. of Dyebath (grams/liter) (C) |
|-----------------------------|-----------------------|------------------------|--------------------------|------------------|--|---------------------------|---|
| 0 | 0 | 90 | Initial conc. | | | | 0.558 |
| 1 | 5 | 90 | | 8.4 | 43.2 | 0.365 | 0.438 |
| 2 | 10 | 150 | | | 36.0 | 0.444 | 0.532 |
| 3 | 15 | 200 | | | 37.0 | 0.432 | 0.518 |
| 4 | 20 | 210 | $\frac{1}{2}$ Salt added | | 49.1 | 0.309 | 0.359 |
| 5 | 25 | 212 | | 8.3 | 54.0 | 0.268 | 0.312 |
| 6 | 30 | 210 | | | 55.0 | 0.260 | 0.302 |
| 7 | 35 | 200 | $\frac{1}{2}$ Salt added | | 63.5 | 0.197 | 0.229 |
| 8 | 40 | 210 | | | 66.3 | 0.178 | 0.207 |
| 9 | 45 | 212 | | 8.8 | 67.0 | 0.174 | 0.202 |

Total Dyebath Exhaustion - 63.8%

Table 42. Dyeing Cycle Data of Pontamine
Blue AX Conc. at
Normal Temperature

Run 6

Yarn Sample 6

Weight of Yarn 416.6 grams
Weight of Dye 8.33 grams
Weight of Sodium Chloride 62.5 grams
Volume of Dye Bath 15 liters

| Dyebath Sample Number | Time in Minutes | Temp. Degrees F. | Remarks | pH of Bath | Per Cent Transmission Filter 550 mm (T) | Optical Density (D) | Conc. of Dyebath (grams/liter) (C) |
|-----------------------------|-----------------------|------------------------|--------------------------|------------------|--|---------------------------|---|
| 0 | 0 | 90 | Initial conc. | | | | 0.555 |
| 1 | 5 | 90 | | 9.6 | 44.5 | 0.352 | 0.423 |
| 2 | 10 | 185 | | | 36.9 | 0.433 | 0.518 |
| 3 | 15 | 200 | | | 36.5 | 0.438 | 0.526 |
| 4 | 20 | 210 | $\frac{1}{2}$ Salt added | 9.4 | 46.5 | 0.333 | 0.387 |
| 5 | 25 | 210 | | | 50.9 | 0.293 | 0.341 |
| 6 | 30 | 210 | | | 54.7 | 0.262 | 0.304 |
| 7 | 35 | 210 | $\frac{1}{2}$ Salt added | | 62.2 | 0.206 | 0.239 |
| 8 | 40 | 210 | | | 66.5 | 0.177 | 0.206 |
| 9 | 45 | 210 | | 9.3 | 67.5 | 0.171 | 0.197 |

Total Dyebath Exhaustion - 64.2%

Table 43. Dyeing Cycle Data of Pontamine
Fast Yellow RL - Dye Only
Test for Heat Stability

Weight of Dye 8.5 grams
Weight of Sodium Chloride 65 grams
Volume of Dye Bath 15 liters

| Dyebath Sample Number | Time in Minutes | Temperature Degrees F. | pH of Bath |
|-----------------------------|-----------------------|------------------------------|------------------|
| 0 | 0 | 90 | |
| 1 | 5 | 150 | 7.6 |
| 2 | 10 | 212 | |
| 3 | 40 | 212 | 7.4 |
| 4 | 45 | 190 | |
| 5 | 60 | 245 | |
| 6 | 95 | 250 | |
| 7 | 125 | 255 | 7.6 |
| 8 | 155 | 255 | |
| 9 | 180 | 255 | |

Table 44. Test for Heat Stability for
Pontamine Fast Yellow RL

Per cent transmission of light through various wave length filters for
dye bath samples listed in Table 43.

| Monochromatic Filter Number (millimicrons) | Dye Bath Sample Number | | |
|---|---|------|------|
| | 1 | 4 | 9 |
| | Per Cent Transmission at Wave Length Indicated | | |
| 390 | 62.5 | 64.0 | 59.9 |
| 420 | 67.3 | 69.0 | 61.0 |
| 440 | 74.8 | 76.0 | 65.0 |
| 465 | 84.8 | 84.6 | 73.6 |
| 490 | 92.3 | 92.4 | 84.6 |
| 515 | 94.6 | 94.6 | 89.0 |
| 550 | 98.7 | 98.7 | 97.8 |
| 575 | 98.75 | 98.8 | 98.9 |
| 595 | 98.8 | 98.8 | 98.9 |
| 620 | 98.9 | 98.9 | 99.5 |
| 640 | 99.2 | 99.2 | 99.0 |
| 660 | 99.4 | 99.3 | 99.1 |

Table 45. Dyeing Cycle Data for Pontamine
Fast Orange EGL - Dye Only
Test for Heat Stability

Weight of Dye 8.5 grams
Weight of Sodium Chloride 65.0 grams
Volume of Dye Bath 15 liters

| Dyebath Sample Number | Time in Minutes | Temperature Degrees F. | pH of Bath |
|-----------------------------|-----------------------|------------------------------|------------------|
| 1 | 5 | 180 | 8.5 |
| 2 | 35 | 212 | 8.5 |
| 3 | 50 | 250 | 8.6 |
| 4 | 65 | 255 | 7.9 |
| 5 | 95 | 235 | 8.0 |
| 6 | 110 | 190 | 8.7 |

Table 46. Test for Heat Stability for
Pontamine Fast Orange EGL

Per cent transmission of light through various wave length filters for
dye bath samples listed in Table 45.

| Monochromatic Filter Number (millimicrons) | Dye Bath Sample Number | | |
|---|---|------|------|
| | 1 | 2 | 6 |
| | Per Cent Transmission at Wave Length Indicated | | |
| 390 | 58.5 | 57.5 | 57.0 |
| 420 | 58.7 | 58.6 | 57.6 |
| 440 | 62.3 | 62.3 | 61.4 |
| 465 | 72.5 | 72.5 | 72.3 |
| 490 | 82.8 | 82.8 | 82.5 |
| 515 | 87.7 | 87.7 | 87.7 |
| 550 | 97.1 | 97.1 | 97.4 |
| 575 | 99.1 | 99.1 | 99.1 |
| 595 | 99.4 | 99.4 | 99.4 |
| 620 | 99.9 | 99.9 | 99.9 |
| 640 | 99.9 | 99.9 | 99.9 |
| 660 | 99.9 | 99.9 | 99.9 |

Table 47. Dyeing Cycle Data for Pontamine
Blue AX Conc. - Dye Only
Test for Heat Stability

Weight of Dye 8.5 grams
Weight of Sodium Chloride 65.0 grams
Volume of Dye Bath 15 liters

| Dyebath Sample Number | Time in Minutes | Temperature Degrees F. | pH of Bath |
|-----------------------------|-----------------------|------------------------------|------------------|
| 1 | 5 | 160 | 9.2 |
| 2 | 15 | 212 | 9.0 |
| 3 | 40 | 212 | 9.3 |
| 4 | 70 | 250 | 9.2 |
| 5 | 95 | 250 | 9.0 |
| 6 | 110 | 190 | 10.5 |

Table 48. Test for Heat Stability for
Pontamine Blue AX Conc.

Per cent transmission of light through various wave length filters for
dye bath samples listed in Table 47.

| Monochromatic Filter Number (millimicrons) | Dye Bath Sample Number | | |
|---|---|------|------|
| | 1 | 2 | 3 |
| | Per Cent Transmission at Wave Length Indicated | | |
| 390 | 84.0 | 84.6 | 84.9 |
| 420 | 82.5 | 82.5 | 82.1 |
| 440 | 82.3 | 82.3 | 82.3 |
| 465 | 80.4 | 80.4 | 78.5 |
| 490 | 64.6 | 64.6 | 64.1 |
| 515 | 54.9 | 54.9 | 58.3 |
| 550 | 34.5 | 35.5 | 44.7 |
| 575 | 40.2 | 42.1 | 51.8 |
| 595 | 45.0 | 47.5 | 58.0 |
| 620 | 54.6 | 56.9 | 65.8 |
| 640 | 68.0 | 69.8 | 76.5 |
| 660 | 72.5 | 74.0 | 80.5 |

Table 49. Dyeing Cycle Data for Pontamine
Fast Yellow RL - High Temperature

Run 8

Yarn Sample 8

Weight of Yarn 408.6 grams
Weight of Dye 8.17 grams
Weight of Sodium Chloride 61.23 grams
Volume of Dye Bath 15 liters

| Dyebath Sample Number | Time in Minutes | Temp. Degrees F. | Remarks | pH of Bath | Per Cent Transmission Filter 390 (T) | Optical Density (D) | Conc. of Dyebath (grams/liter) (C) |
|-----------------------------|-----------------------|------------------------|---------------|------------------|---|---------------------------|---|
| 0 | 0 | 90 | Initial conc. | | | | 0.546 |
| 1 | 5 | 160 | Dye only | 8.2 | 69.5 | 0.158 | 0.427 |
| 2 | 15 | 205 | | 8.2 | 66.8 | 0.175 | 0.473 |
| 3 | 30 | 230 | | 8.4 | 66.5 | 0.177 | 0.479 |
| 4 | 40 | 235 | | 8.1 | 64.5 | 0.190 | 0.514 |
| 5 | 45 | 240 | | 8.2 | 64.6 | 0.190 | 0.514 |
| 6 | 50 | 244 | | 8.1 | 64.8 | 0.188 | 0.508 |
| 7 | 55 | 248 | | 8.1 | 64.7 | 0.189 | 0.511 |
| 8 | 70 | 248 | | 8.1 | 64.0 | 0.194 | 0.525 |
| 9 | 75 | 190 | | 8.2 | 64.0 | 0.194 | 0.525 |
| 10 | 85 | 200 | Salt added | 8.3 | 66.5 | 0.177 | 0.497 |

Total Dyebath Exhaustion 9.47%
pH Tap-water 8.8

Table 50. Test for Heat Stability for Pontamine
Fast Yellow RL - High Temperature
Run Number 8

Percent transmission of light through various filters for dye bath samples listed in Table 49.

| Monochromatic Filter Number (millimicrons) | Dye Bath Sample Number | | |
|---|---|------|------|
| | 1 | 8 | 10 |
| | Per Cent Transmission at Wave Length Indicated | | |
| 390 | 69.5 | 64.0 | 66.5 |
| 420 | 75.3 | 66.4 | 71.3 |
| 440 | 81.5 | 70.9 | 71.0 |
| 465 | 88.2 | 79.1 | 77.4 |
| 490 | 94.5 | 88.5 | 88.1 |
| 515 | 96.5 | 92.6 | 92.3 |
| 550 | 99.7 | 99.8 | 99.5 |
| 575 | 99.8 | 99.9 | 99.9 |
| 595 | 99.9 | 99.9 | 99.9 |
| 620 | 99.9 | 99.9 | 99.9 |
| 640 | 99.9 | 99.9 | 99.9 |
| 660 | 99.9 | 99.9 | 99.9 |

Table 51. Dyeing Cycle Data for Pontamine
Fast Orange EGL - High Temperature

Run 9

Yarn Sample 9

Weight of Yarn 429.2 grams
Weight of Dye 8.58 grams
Weight of Sodium Chloride 64.38 grams
Volume of Dye Bath 15 liters

| Dyebath Sample Number | Time in Minutes | Temp. Degrees F. | Remarks | pH of Bath | Per Cent Transmission Filter 420 (T) | Optical Density (D) | Conc. of Dyebath (grams/liter) (C) |
|-----------------------------|-----------------------|------------------------|---------------|------------------|---|---------------------------|---|
| 0 | 0 | 90 | Initial conc. | | | | 0.572 |
| 1 | 5 | 135 | Dye only | 8.75 | 55.0 | 0.260 | 0.583 |
| 2 | 10 | 180 | | 8.8 | 55.3 | 0.257 | 0.577 |
| 3 | 15 | 210 | | 8.8 | 55.3 | 0.257 | 0.577 |
| 4 | 27 | 230 | | 8.9 | 55.3 | 0.257 | 0.577 |
| 5 | 33 | 240 | | 9.0 | 55.3 | 0.257 | 0.577 |
| 6 | 37 | 250 | | 9.0 | 54.1 | 0.267 | 0.598 |
| 7 | 46 | 255 | | 9.05 | 54.1 | 0.267 | 0.598 |
| 8 | 60 | 255 | | 8.9 | 54.7 | 0.262 | 0.587 |
| 9 | 65 | 190 | | 8.9 | 56.6 | 0.247 | 0.553 |
| 10 | 80 | 208 | Salt added | 8.7 | 70.5 | 0.152 | 0.335 |
| 11 | 95 | 200 | | 8.9 | 71.8 | 0.144 | 0.317 |

Total Dyebath Exhaustion 44.5%
pH Tap-water 8.9

Table 52. Test for Heat Stability for Pontamine
Fast Orange EGL - High Temperature

Per cent transmission of light through various filters for dye bath samples listed in Table 51.

| Monochromatic Filter Number (millimicrons) | Dye Bath Sample Number | | |
|---|---|------|------|
| | 1 | 8 | |
| | Per Cent Transmission at Wave Length Indicated | | |
| 390 | 55.0 | 54.5 | 70.0 |
| 420 | 55.0 | 54.7 | 71.8 |
| 440 | 59.2 | 58.6 | 75.2 |
| 465 | 70.8 | 70.1 | 83.0 |
| 490 | 82.1 | 81.3 | 89.4 |
| 515 | 86.6 | 86.0 | 92.4 |
| 550 | 97.4 | 97.4 | 98.7 |
| 575 | 99.4 | 99.1 | 99.2 |
| 595 | 99.5 | 99.9 | 99.6 |
| 620 | 99.9 | 99.9 | 99.9 |
| 640 | 99.9 | 99.9 | 99.9 |
| 660 | 99.9 | 99.9 | 99.9 |

Table 53. Dyeing Cycle Data for Pontamine
Fast Orange EGL - High Temperature

Run 10

Yarn Sample 10

Weight of Yarn 407.0 grams
Weight of Dye 8.14 grams
Weight of Sodium Chloride 61.05 grams
Volume of Dye Bath 15 liters

| Dyebath Sample Number | Time in Minutes | Temp. Degrees F. | Remarks | pH of Bath | Per Cent Transmission Filter 420 (T) | Optical Density (D) | Conc. of Dyebath (grams/liter) (C) |
|-----------------------------|-----------------------|------------------------|---------------|------------------|---|---------------------------|---|
| 0 | 0 | 90 | Initial conc. | | | | 0.542 |
| 1 | 5 | 160 | Dye only | 8.8 | 58.0 | 0.237 | 0.530 |
| 2 | 10 | 200 | | 8.9 | 58.0 | 0.237 | 0.530 |
| 3 | 20 | 220 | | 8.95 | 58.7 | 0.230 | 0.515 |
| 4 | 30 | 230 | | 8.95 | 58.1 | 0.236 | 0.528 |
| 5 | 33 | 240 | | 8.7 | 57.8 | 0.238 | 0.534 |
| 6 | 43 | 250 | | 8.8 | 57.8 | 0.238 | 0.534 |
| 7 | 58 | 250 | | 9.0 | 57.8 | 0.238 | 0.534 |
| 8 | 73 | 250 | | 9.1 | 58.1 | 0.236 | 0.528 |
| 9 | 75 | 190 | | 9.1 | 60.0 | 0.232 | 0.498 |
| 10 | 90 | 200 | Salt added | 9.0 | 71.9 | 0.143 | 0.315 |
| 11 | 105 | 200 | | 9.0 | 72.8 | 0.138 | 0.309 |

Total Dyebath Exhaustion 46.0%
pH Tap-water 8.85

Table 54. Test for Heat Stability for Pontamine
Fast Orange EGL - High Temperature

Per cent transmission of light through various filters for dye bath samples listed in Table 53.

| Monochromatic Filter Number (millimicrons) | Dye Bath Sample Number | | |
|---|---|------|------|
| | 1 | 8 | 11 |
| | Per Cent Transmission at Wave Length Indicated | | |
| 390 | 58.5 | 57.8 | 72.8 |
| 420 | 58.0 | 58.1 | 74.8 |
| 440 | 62.3 | 62.2 | 78.0 |
| 465 | 72.8 | 73.0 | 85.1 |
| 490 | 83.4 | 83.6 | 92.0 |
| 515 | 88.0 | 88.1 | 93.2 |
| 550 | 97.8 | 98.0 | 98.7 |
| 575 | 99.5 | 99.7 | 99.5 |
| 595 | 99.9 | 99.9 | 99.9 |
| 620 | 99.9 | 99.9 | 99.9 |
| 640 | 99.9 | 99.9 | 99.9 |
| 660 | 99.9 | 99.9 | 99.9 |

Table 55. Dyeing Cycle Data for Pontamine
Blue AX Conc. - High Temperature

Run 12

Yarn Sample 12

Weight of Yarn 410.0 grams
Weight of Dye 8.22 grams
Weight of Sodium Chloride 61.5 grams
Volume of Dye Bath 15 liters

| Dyebath Sample Number | Time in Minutes | Temp. Degrees F. | Remarks | pH of Bath | Per Cent Transmission Filter 550 (T) | Optical Density (D) | Conc. of Dyebath (grams/liter) (C) |
|-----------------------------|-----------------------|------------------------|---------------|------------------|---|---------------------------|---|
| 0 | 0 | 90 | Initial conc. | | | | 0.548 |
| 1 | 5 | 160 | | 9.6 | 39.4 | 0.405 | 0.487 |
| 2 | 10 | 190 | | 9.7 | 40.5 | 0.393 | 0.473 |
| 3 | 15 | 210 | | 9.7 | 41.8 | 0.379 | 0.455 |
| 4 | 22 | 222 | | 9.8 | 42.2 | 0.375 | 0.451 |
| 5 | 25 | 235 | | 9.7 | 42.5 | 0.372 | 0.447 |
| 6 | 30 | 250 | | 9.7 | 43.2 | 0.365 | 0.438 |
| 7 | 45 | 250 | | 9.7 | 44.1 | 0.356 | 0.427 |
| 8 | 50 | 190 | | 9.7 | 46.7 | 0.331 | 0.398 |
| 9 | 65 | 200 | Salt added | 9.4 | 71.3 | 0.147 | 0.171 |
| 10 | 75 | 200 | | 9.4 | 74.5 | 0.128 | 0.148 |

Total Dyebath Exhaustion 73.0%
pH Tap-water 8.75

Table 56. Test for Heat Stability of Pontamine
Blue AX Conc. - High Temperature

Per cent transmission of light through various filters for dye bath samples listed in Table 55.

| Monochromatic Filter Number (millimicrons) | Dye Bath Sample Number | | |
|---|---|------|------|
| | 1 | 7 | 9 |
| | Per Cent Transmission at Wave Length Indicated | | |
| 390 | 86.0 | 87.2 | 92.8 |
| 420 | 85.0 | 87.0 | 93.0 |
| 440 | 84.5 | 86.4 | 93.0 |
| 465 | 83.0 | 84.6 | 92.3 |
| 490 | 67.76 | 70.9 | 85.8 |
| 515 | 58.5 | 62.9 | 81.9 |
| 550 | 39.4 | 44.1 | 71.3 |
| 575 | 46.0 | 51.0 | 75.6 |
| 595 | 50.7 | 55.0 | 78.1 |
| 620 | 60.0 | 63.7 | 83.4 |
| 640 | 71.5 | 75.1 | 88.7 |
| 660 | 75.7 | 78.8 | 90.4 |

Table 57. Dyeing Cycle Data for Pontamine
Blue AX Conc. - High Temperature

Run 13

Yarn Sample 13

Weight of Yarn 459.4 grams
Weight of Dye 9.188 grams
Weight of Sodium Chloride 68.9 grams
Volume of Dye Bath 15 liters

| Dyebath Sample Number | Time in Minutes | Temp. Degrees F. | Remarks | pH of Bath | Per Cent Transmission Filter 550 (T) | Optical Density (D) | Conc. of Dyebath (grams/liter) (C) |
|-----------------------------|-----------------------|------------------------|---------------|------------------|---|---------------------------|---|
| 0 | 0 | 90 | Initial conc. | | | | 0.612 |
| 1 | 5 | 160 | | 9.5 | 32.5 | 0.488 | 0.583 |
| 2 | 8 | 190 | | 9.6 | 33.1 | 0.480 | 0.576 |
| 3 | 12 | 210 | | 9.6 | 34.7 | 0.460 | 0.552 |
| 4 | 25 | 210 | | 9.6 | 35.8 | 0.446 | 0.535 |
| 5 | 32 | 220 | | 9.7 | 36.5 | 0.438 | 0.526 |
| 6 | 37 | 230 | | 9.6 | 36.5 | 0.438 | 0.526 |
| 7 | 40 | 240 | | 9.6 | 36.5 | 0.438 | 0.526 |
| 8 | 45 | 250 | | 9.6 | 36.1 | 0.443 | 0.532 |
| 9 | 60 | 252 | | 8.8 | 37.7 | 0.424 | 0.507 |
| 10 | 80 | 195 | | 9.1 | 37.0 | 0.432 | 0.518 |
| 11 | 95 | 200 | Salt added | 8.8 | 71.8 | 0.144 | 0.167 |
| 12 | 110 | 200 | | 9.0 | 75.5 | 0.122 | 0.142 |

Total Dyebath Exhaustion 76.8%
pH Tap-water 9.0

Table 58. Test for Heat Stability of Pontamine
Blue AX Conc. - High Temperature

Per cent transmission of light through various filters for dye bath samples listed in Table 57.

| Monochromatic Filter Number (millimicrons) | Dye Bath Sample Number | | |
|---|---|------|------|
| | 1 | 9 | 12 |
| | Per Cent Transmission at Wave Length Indicated | | |
| 390 | 83.0 | 84.6 | 93.3 |
| 420 | 82.1 | 84.0 | 93.2 |
| 440 | 81.7 | 83.5 | 93.5 |
| 465 | 79.5 | 81.4 | 91.9 |
| 490 | 62.5 | 65.2 | 85.0 |
| 515 | 53.7 | 56.8 | 82.2 |
| 550 | 32.5 | 37.7 | 71.8 |
| 575 | 39.5 | 44.3 | 76.4 |
| 595 | 44.0 | 48.8 | 79.5 |
| 620 | 53.7 | 57.7 | 84.0 |
| 640 | 67.1 | 70.0 | 89.3 |
| 660 | 71.5 | 75.0 | 90.8 |

Table 59. Dyeing Cycle Data for Pontamine
Fast Yellow RL - High Temperature
Neutral pH

Run 14

Yarn Sample 14

Weight of Yarn 432.2 grams
Weight of Dye 8.64 grams
Weight of Sodium Chloride 64.8 grams
Weight of Ammonium Sulphate 15 grams
Volume of Dye Bath 15 liters

| Dyebath Sample Number | Time in Minutes | Temp. Degrees F. | Remarks | pH of Bath | Per Cent Transmission Filter 390 (T) | Optical Density (D) | Conc. of Dyebath (grams/liter) (C) |
|-----------------------------|-----------------------|------------------------|---------------|------------------|---|---------------------------|---|
| 0 | 0 | 90 | Initial conc. | | | | 0.575 |
| 1 | 10 | 110 | Dye & Buffer | 7.6 | 72.2 | 0.142 | 0.371 |
| 2 | 20 | 190 | | 7.9 | 67.0 | 0.174 | 0.456 |
| 3 | 30 | 200 | | 7.9 | 70.7 | 0.151 | 0.395 |
| 4 | 35 | 220 | | 8.0 | 65.0 | 0.187 | 0.490 |
| 5 | 37 | 230 | | 8.1 | 66.3 | 0.179 | 0.468 |
| 6 | 43 | 240 | | 8.1 | 63.7 | 0.196 | 0.514 |
| 7 | 49 | 250 | | 8.1 | 66.8 | 0.175 | 0.458 |
| 8 | 56 | 252 | | 8.0 | 64.6 | 0.190 | 0.497 |
| 9 | 60 | 252 | | 8.0 | 63.0 | 0.201 | 0.525 |
| 10 | 70 | 190 | | 8.0 | 63.6 | 0.197 | 0.515 |
| 11 | 80 | 200 | Salt added | 8.1 | 66.2 | 0.179 | 0.504 |
| 12 | 85 | 200 | | 8.1 | 66.5 | 0.177 | 0.498 |

Total Dyebath Exhaustion 13.7%
pH Tap-water 8.9

Table 60. Test for Heat Stability of Pontamine
Fast Yellow RL - High Temperature
Neutral pH

Per cent transmission of light through various filters for dye bath samples listed in Table 59.

| Monochromatic Filter Number (millimicrons) | Dye Bath Sample Number | | |
|---|---|------|------|
| | 1 | 9 | 12 |
| | Per Cent Transmission at Wave Length Indicated | | |
| 390 | 72.2 | 63.0 | 66.5 |
| 420 | 77.3 | 67.0 | 68.5 |
| 440 | 82.0 | 69.8 | 72.4 |
| 465 | 88.2 | 79.3 | 78.5 |
| 490 | 94.6 | 89.0 | 89.4 |
| 515 | 96.8 | 93.0 | 93.2 |
| 550 | 99.9 | 99.9 | 99.9 |
| 575 | 99.9 | 99.9 | 99.9 |
| 590 | 99.9 | 99.9 | 99.9 |
| 620 | 99.9 | 99.9 | 99.9 |
| 640 | 99.9 | 99.9 | 99.9 |
| 660 | 99.9 | 99.9 | 99.9 |

Table 61. Dyeing Cycle Data for Pontamine
Fast Yellow RL - High Temperature
Acid pH

Run 17

Yarn Sample 17

Weight of Yarn 440.9 grams
Weight of Dye 8.81 grams
Weight of Sodium Chloride 66.13 grams
Weight of Ammonium Phosphate 15 grams
Volume of Dye Bath 15 liters

| Dyebath Sample Number | Time in Minutes | Temp. Degrees F. | Remarks | pH of Bath | Per Cent Transmission Filter 390 (T) | Optical Density (D) | Conc. of Dyebath (grams/liter) (C) |
|-----------------------------|-----------------------|------------------------|---------------|------------------|---|---------------------------|---|
| 0 | 0 | 90 | Initial conc. | | | | 0.587 |
| 1 | 2 | 100 | Dye only | 8.5 | 63.8 | 0.195 | 0.523 |
| 2 | 5 | 120 | Buffer added | 6.2 | 64.2 | 0.193 | 0.519 |
| 3 | 8 | 180 | | 6.15 | 58.8 | 0.230 | 0.618 |
| 4 | 11 | 195 | | 6.2 | 64.0 | 0.194 | 0.522 |
| 5 | 17 | 220 | | 6.15 | 55.0 | 0.260 | 0.700 |
| 6 | 23 | 240 | | 6.2 | 55.7 | 0.254 | 0.683 |
| 7 | 25 | 250 | | 6.1 | 56.0 | 0.252 | 0.687 |
| 8 | 33 | 252 | | 6.0 | 56.1 | 0.251 | 0.676 |
| 9 | 38 | 190 | | 6.05 | 61.0 | 0.215 | 0.578 |
| 10 | 45 | 200 | Salt added | 5.9 | 67.4 | 0.171 | 0.425 |

Total Dyebath Exhaustion 27.5%
pH Tap-water 8.9

Table 62. Test for Stability of Pontamine
Fast Yellow RL - High Temperature
Acid pH

Per cent transmission of light through various filters for dye bath samples listed in Table 61.

| Monochromatic Filter Number (millimicrons) | Dye Bath Sample Number | | |
|---|---|------|------|
| | 1 | 8 | 10 |
| | Per Cent Transmission at Wave Length Indicated | | |
| 390 | 62.0 | 56.1 | 67.4 |
| 420 | 70.4 | 61.8 | 68.9 |
| 440 | 78.6 | 69.1 | 73.2 |
| 465 | 86.1 | 79.3 | 81.1 |
| 490 | 94.3 | 89.4 | 91.5 |
| 515 | 96.5 | 94.0 | 93.5 |
| 550 | 99.9 | 99.9 | 99.9 |
| 575 | 99.9 | 99.9 | 99.9 |
| 595 | 99.9 | 99.9 | 99.9 |
| 620 | 99.9 | 99.9 | 99.9 |
| 640 | 99.9 | 99.9 | 99.9 |
| 660 | 99.9 | 99.9 | 99.9 |

Table 63. Dyeing Cycle Data for Pontamine
Fast Yellow RL - High Temperature
Alkaline pH

Run 18

Yarn Sample 18

Weight of Yarn 449.2 grams
Weight of Dye 8.984 grams
Weight of Sodium Chloride 67.38 grams
Weight of Sodium Acetate 15 grams
Volume of Dye Bath 15 liters

| Dyebath Sample Number | Time in Minutes | Temp. Degrees F. | Remarks | pH of Bath | Per Cent Transmission Filter 394 (T) | Optical Density (D) | Conc. of Dyebath (grams/liter) (C) |
|-----------------------------|-----------------------|------------------------|---------------|------------------|---|---------------------------|---|
| 0 | 0 | 90 | Initial conc. | | | | 0.598 |
| 1 | 2 | 128 | Dye only | 8.4 | 62.0 | 0.208 | 0.560 |
| 2 | 5 | 170 | Buffer added | 8.8 | 61.5 | 0.211 | 0.566 |
| 3 | 10 | 190 | | 8.8 | 60.0 | 0.222 | 0.596 |
| 4 | 20 | 220 | | 9.0 | 60.0 | 0.222 | 0.596 |
| 5 | 26 | 290 | | 8.8 | 58.5 | 0.233 | 0.628 |
| 6 | 32 | 250 | | 8.5 | 58.4 | 0.234 | 0.629 |
| 7 | 40 | 250 | | 8.5 | 59.8 | 0.226 | 0.611 |
| 8 | 45 | 190 | | 8.4 | 59.8 | 0.223 | 0.600 |
| 9 | 55 | 200 | Salt added | 8.4 | 63.4 | 0.198 | 0.523 |
| 10 | 60 | 190 | | 8.4 | 65.4 | 0.184 | 0.486 |

Total Dyebath Exhaustion 19.0%
pH Tap-water 9.0

Table 64. Test for Stability of Pontamine
Fast Yellow RL - High Temperature
Alkaline pH

Per cent transmission of light through various filters for dye bath samples listed in Table 63.

| Monochromatic Filter Number (millimicrons) | Dye Bath Sample Number | | |
|---|---|------|------|
| | 1 | 7 | 10 |
| | Per Cent Transmission at Wave Length Indicated | | |
| 390 | 62.0 | 59.8 | 65.4 |
| 420 | 70.3 | 61.9 | 66.6 |
| 440 | 78.6 | 67.0 | 70.2 |
| 465 | 86.2 | 75.9 | 78.2 |
| 490 | 94.4 | 86.1 | 87.4 |
| 515 | 96.5 | 90.6 | 91.6 |
| 550 | 99.9 | 98.2 | 99.0 |
| 575 | 99.9 | 99.2 | 99.5 |
| 595 | 99.9 | 99.6 | 99.7 |
| 620 | 99.9 | 99.7 | 99.7 |
| 640 | 99.9 | 99.7 | 99.7 |
| 660 | 99.9 | 99.7 | 99.7 |

Table 65. Dyeing Cycle Data for Pontamine
Fast Orange EGL - High Temperature
Neutral pH

Run 19

Yarn Sample 19

Weight of Yarn 438.9 grams
Weight of Dye 8.778 grams
Weight of Sodium Chloride 65.58 grams
Weight of Ammonium Sulphate 15 grams
Volume of Dye Bath 15 liters

| Dyebath Sample Number | Time in Minutes | Temp. Degrees F. | Remarks | pH of Bath | Per Cent Transmission Filter 420 (T) | Optical Density (D) | Conc. of Dyebath (grams/liter) (C) |
|-----------------------------|-----------------------|------------------------|--------------|------------------|---|---------------------------|---|
| 0 | 0 | 90 | | | | | 0.585 |
| 1 | 2 | 120 | Dye only | 8.7 | 55.0 | 0.260 | 0.584 |
| 2 | 4 | 145 | Buffer added | 7.9 | 58.1 | 0.236 | 0.524 |
| 3 | 6 | 190 | | 8.0 | 59.0 | 0.229 | 0.514 |
| 4 | 10 | 208 | | 7.9 | 60.5 | 0.218 | 0.489 |
| 5 | 16 | 220 | | 8.1 | 60.4 | 0.219 | 0.491 |
| 6 | 20 | 230 | | 8.2 | 59.2 | 0.228 | 0.511 |
| 7 | 23 | 240 | | 8.2 | 58.9 | 0.230 | 0.515 |
| 8 | 26 | 250 | | 8.2 | 58.1 | 0.236 | 0.528 |
| 9 | 36 | 250 | | 7.9 | 58.0 | 0.236 | 0.528 |
| 10 | 40 | 190 | | 8.1 | 64.0 | 0.194 | 0.435 |
| 11 | 50 | 195 | Salt added | 8.0 | 79.4 | 0.100 | 0.212 |
| 12 | 55 | 195 | | 7.95 | 78.4 | 0.106 | 0.225 |

Total Dyebath Exhaustion 61.5%
pH Tap-water 9.0

Table 66. Test for Stability of Pontamine
Fast Orange EGL - High Temperature
Neutral pH

Per cent transmission of light through various filters for dye bath samples listed in Table 65.

| Monochromatic Filter Number (millimicrons) | Dye Bath Sample Number | | |
|---|---|------|------|
| | 1 | 9 | 12 |
| | Per Cent Transmission at Wave Length Indicated | | |
| 390 | 55.5 | 58.0 | 76.0 |
| 420 | 55.0 | 58.0 | 78.4 |
| 440 | 59.0 | 62.3 | 81.6 |
| 465 | 70.7 | 73.5 | 88.0 |
| 490 | 81.7 | 83.3 | 93.0 |
| 515 | 86.7 | 87.7 | 95.1 |
| 550 | 97.1 | 97.6 | 99.0 |
| 575 | 99.5 | 99.7 | 99.5 |
| 595 | 99.9 | 99.9 | 99.9 |
| 620 | 99.9 | 99.9 | 99.9 |
| 640 | 99.9 | 99.9 | 99.9 |
| 660 | 99.9 | 99.9 | 99.9 |

Table 67. Dyeing Cycle Data for Pontamine
Fast Orange EGL - High Temperature
Alkaline pH

Run 20

Yarn Sample 20

Weight of Yarn 430.5 grams
Weight of Dye 8.61 grams
Weight of Sodium Chloride 64.57 grams
Weight of Sodium Acetate 15 grams
Volume of Dye Bath 15 liters

| Dyebath Sample Number | Time in Minutes | Temp. Degrees F. | Remarks | pH of Bath | Per Cent Transmission Filter 420 (T) | Optical Density (D) | Conc. of Dyebath (grams/liter) (C) |
|-----------------------------|-----------------------|------------------------|---------------|------------------|---|---------------------------|---|
| 0 | 0 | 90 | Initial conc. | | | | 0.575 |
| 1 | 2 | 130 | Dye only | 8.6 | 55.3 | 0.257 | 0.576 |
| 2 | 4 | 144 | Buffer added | 8.3 | 57.1 | 0.243 | 0.557 |
| 3 | 8 | 180 | | 8.2 | 57.8 | 0.238 | 0.545 |
| 4 | 11 | 195 | | 8.8 | 58.0 | 0.237 | 0.544 |
| 5 | 17 | 220 | | 8.6 | 58.1 | 0.236 | 0.541 |
| 6 | 20 | 230 | | 9.1 | 57.8 | 0.238 | 0.545 |
| 7 | 23 | 240 | | 9.1 | 56.8 | 0.246 | 0.564 |
| 8 | 27 | 250 | | 8.6 | 56.8 | 0.246 | 0.564 |
| 9 | 37 | 252 | | 8.5 | 56.0 | 0.252 | 0.578 |
| 10 | 42 | 190 | | 8.7 | 60.6 | 0.218 | 0.500 |
| 11 | 52 | 190 | Salt added | 8.8 | 74.0 | 0.131 | 0.277 |
| 12 | 57 | 190 | | 8.8 | 73.6 | 0.133 | 0.282 |

Total Dyebath Exhaustion 50.8%
pH Tap-water 9.0

Table 68. Test for Stability of Pontamine
Fast Orange EGL - High Temperature
Alkaline pH

Per cent transmission of light through various filters for dye bath samples listed in Table 67.

| Monochromatic Filter Number (millimicrons) | Dye Bath Sample Number | | |
|---|---|------|------|
| | 1 | 9 | 12 |
| | Per Cent Transmission at Wave Length Indicated | | |
| 390 | 55.5 | 56.3 | 72.1 |
| 420 | 55.3 | 56.0 | 73.6 |
| 440 | 59.0 | 60.0 | 77.3 |
| 465 | 70.6 | 71.3 | 84.6 |
| 490 | 81.7 | 82.1 | 90.7 |
| 515 | 86.7 | 87.0 | 93.3 |
| 550 | 97.0 | 97.2 | 98.7 |
| 575 | 99.6 | 99.5 | 99.6 |
| 595 | 99.9 | 99.5 | 99.2 |
| 620 | 99.9 | 99.9 | 99.9 |
| 640 | 99.9 | 99.3 | 99.9 |
| 660 | 99.9 | 99.6 | 99.7 |

Table 69. Dyeing Cycle Data for Pontamine
Fast Orange EGL - High Temperature
Acid pH

Run 21

Yarn Sample 21

Weight of Yarn 446.2 grams
Weight of Dye 8.92 grams
Weight of Sodium Chloride 66.93 grams
Weight of Ammonium Phosphate 15.0 grams
Volume of Dye Bath 15 liters

| Dyebath Sample Number | Time in Minutes | Temp. Degrees F. | Remarks | pH of Bath | Per Cent Transmission Filter 420 (T) | Optical Density (D) | Conc. of Dyebath (grams/liter) (C) |
|-----------------------------|-----------------------|------------------------|---------------|------------------|---|---------------------------|---|
| 0 | 0 | 90 | Initial conc. | | | | 0.596 |
| 1 | 2 | 130 | Dye only | 8.7 | 54.2 | 0.266 | 0.596 |
| 2 | 5 | 170 | Buffer added | 6.1 | 56.5 | 0.248 | 0.539 |
| 3 | 9 | 190 | | 6.1 | 57.6 | 0.240 | 0.522 |
| 4 | 12 | 200 | | 6.1 | 58.4 | 0.234 | 0.508 |
| 5 | 17 | 220 | | 6.1 | 58.1 | 0.236 | 0.513 |
| 6 | 22 | 230 | | 6.1 | 57.7 | 0.239 | 0.519 |
| 7 | 25 | 240 | | 6.05 | 57.0 | 0.244 | 0.530 |
| 8 | 28 | 250 | | 6.1 | 57.0 | 0.244 | 0.530 |
| 9 | 38 | 254 | | 6.0 | 56.7 | 0.246 | 0.535 |
| 10 | 43 | 180 | | 6.0 | 60.5 | 0.218 | 0.474 |
| 11 | 53 | 195 | Salt added | 5.8 | 72.1 | 0.140 | 0.291 |
| 12 | 58 | 195 | | 5.85 | 73.5 | 0.134 | 0.275 |

Total Dyebath Exhaustion 53.8%
pH Tap-water 8.9

Table 70. Test for Stability of Pontamine
Fast Orange EGL - High Temperature
Acid pH

Per cent transmission of light through various filters for dye bath samples listed in Table 69.

| Monochromatic Filter Number (millimicrons) | Dye Bath Sample Number | | |
|---|---|------|------|
| | 1 | 9 | 12 |
| | Per Cent Transmission at Wave Length Indicated | | |
| 390 | 54.9 | 56.0 | 71.6 |
| 420 | 54.2 | 56.2 | 73.5 |
| 440 | 58.8 | 60.6 | 77.3 |
| 465 | 70.5 | 71.8 | 84.9 |
| 490 | 81.8 | 82.7 | 91.0 |
| 515 | 86.8 | 87.4 | 93.5 |
| 550 | 97.2 | 97.6 | 98.5 |
| 575 | 99.7 | 99.2 | 99.1 |
| 595 | 99.9 | 99.1 | 99.9 |
| 620 | 99.9 | 99.5 | 99.5 |
| 640 | 99.9 | 99.7 | 99.3 |
| 660 | 99.7 | 99.6 | 99.6 |

Table 71. Dyeing Cycle Data for Pontamine
Blue AX Conc. - High Temperature
Neutral pH

Run 22

Yarn Sample 22

Weight of Yarn 428.3 grams
Weight of Dye 8.56 grams
Weight of Sodium Chloride 64.24 grams
Weight of Ammonium Sulphate 20 grams
Volume of Dye Bath 15 liters

| Dyebath Sample Number | Time in Minutes | Temp. Degrees F. | Remarks | pH of Bath | Per Cent Transmission Filter 550 (T) | Optical Density (D) | Conc. of Dyebath (grams/liter) (C) |
|-----------------------------|-----------------------|------------------------|---------------|------------------|---|---------------------------|---|
| 0 | 0 | 90 | Initial conc. | | | | 0.571 |
| 1 | 3 | 130 | Dye only | 9.8 | 35.4 | 0.451 | 0.541 |
| 2 | 5 | 160 | Buffer added | 7.8 | 37.0 | 0.432 | 0.537 |
| 3 | 10 | 180 | | 7.9 | 42.4 | 0.373 | 0.456 |
| 4 | 15 | 198 | | 7.9 | 43.0 | 0.367 | 0.447 |
| 5 | 21 | 215 | | 7.9 | 45.0 | 0.347 | 0.423 |
| 6 | 25 | 230 | | 7.9 | 47.1 | 0.327 | 0.399 |
| 7 | 28 | 240 | | 8.0 | 48.2 | 0.317 | 0.387 |
| 8 | 31 | 250 | | 8.0 | 48.1 | 0.318 | 0.388 |
| 9 | 41 | 252 | | 7.95 | 50.1 | 0.300 | 0.367 |
| 10 | 45 | 190 | | 8.1 | 59.1 | 0.228 | 0.278 |
| 11 | 55 | 195 | Salt added | 8.1 | 75.9 | 0.120 | 0.159 |
| 12 | 60 | 200 | | 8.1 | 79.0 | 0.102 | 0.135 |

Total Dyebath Exhaustion 76.3%
pH Tap-water

Table 72. Test for Stability of Pontamine
Blue Ax Conc. - High Temperature
Neutral pH

Per cent transmission of light through various filters for dye bath samples listed in Table 71.

| Monochromatic Filter Number (millimicrons) | Dye Bath Sample Number | | |
|---|---|------|------|
| | 1 | 9 | 12 |
| | Per Cent Transmission at Wave Length Indicated | | |
| 390 | 84.1 | 88.2 | 95.0 |
| 420 | 83.2 | 88.0 | 94.7 |
| 440 | 82.6 | 87.8 | 95.0 |
| 465 | 80.8 | 86.2 | 94.4 |
| 490 | 64.5 | 74.0 | 89.5 |
| 515 | 56.1 | 67.4 | 86.7 |
| 550 | 35.4 | 50.1 | 79.0 |
| 575 | 42.5 | 56.6 | 82.2 |
| 595 | 47.0 | 60.8 | 84.7 |
| 620 | 56.0 | 68.2 | 87.8 |
| 640 | 68.0 | 78.1 | 92.6 |
| 660 | 72.8 | 81.7 | 93.5 |

Table 73. Dyeing Cycle Data for Pontamine
Blue AX Conc. - High Temperature
Alkaline pH

Run 23

Yarn Sample 23

Weight of Yarn 435.5 grams
Weight of Dye 8.710 grams
Weight of Sodium Chloride 65.28 grams
Weight of Sodium Acetate 20 grams
Volume of Dye Bath 15 liters

| Dyebath Sample Number | Time in Minutes | Temp. Degrees F. | Remarks | pH of Bath | Per Cent Transmission Filter 550 (T) | Optical Density (D) | Conc. of Dyebath (grams/liter) (C) |
|-----------------------------|-----------------------|------------------------|---------------|------------------|---|---------------------------|---|
| 0 | 0 | 90 | Initial conc. | 9.8 | | | 0.580 |
| 1 | 3 | 120 | Dye only | 9.8 | 35.2 | 0.454 | 0.546 |
| 2 | 5 | 150 | Buffer added | 9.8 | 34.5 | 0.466 | 0.562 |
| 3 | 7 | 170 | | 9.8 | 36.5 | 0.438 | 0.529 |
| 4 | 12 | 200 | | 9.8 | 39.1 | 0.408 | 0.472 |
| 5 | 20 | 220 | | 9.85 | 40.3 | 0.395 | 0.477 |
| 6 | 25 | 240 | | 9.85 | 41.5 | 0.382 | 0.462 |
| 7 | 28 | 250 | | 9.8 | 41.5 | 0.382 | 0.462 |
| 8 | 38 | 256 | | 9.7 | 41.1 | 0.386 | 0.466 |
| 9 | 44 | 190 | | 9.6 | 46.5 | 0.333 | 0.401 |
| 10 | 54 | 190 | Salt added | 9.5 | 65.7 | 0.182 | 0.227 |
| 11 | 65 | 200 | | 9.5 | 70.2 | 0.154 | 0.192 |

Total Dyebath Exhaustion 66.9%
pH Tap-water 8.9

Table 74. Test for Stability of Pontamine
Blue AX Conc. - High Temperature
Alkaline pH

Per cent transmission of light through various filters for dye bath samples listed in Table 73.

| Monochromatic Filter Number (millimicrons) | Dye Bath Sample Number | | |
|---|---|------|------|
| | 1 | 8 | 11 |
| | Per Cent Transmission at Wave Length Indicated | | |
| 390 | 83.8 | 86.0 | 94.1 |
| 420 | 83.2 | 85.8 | 93.2 |
| 440 | 82.5 | 85.5 | 93.5 |
| 465 | 80.7 | 83.5 | 92.3 |
| 490 | 64.5 | 69.1 | 85.3 |
| 515 | 56.0 | 60.8 | 81.5 |
| 550 | 35.2 | 41.1 | 70.2 |
| 575 | 41.6 | 47.8 | 74.8 |
| 595 | 46.5 | 52.5 | 78.2 |
| 620 | 55.7 | 61.8 | 83.3 |
| 640 | 67.5 | 73.0 | 88.0 |
| 660 | 73.0 | 77.4 | 90.6 |

Table 75. Dyeing Cycle Data for Pontamine
Blue AX Conc. - High Temperature
Acid pH

Run 24

Yarn Sample 24

Weight of Yarn 417.1 grams
Weight of Dye 8.38 grams
Weight of Sodium Chloride 62.86 grams
Weight of Ammonium Phosphate 30 grams
Volume of Dye Bath 15 liters

| Dyebath Sample Number | Time in Minutes | Temp. Degrees F. | Remarks | pH of Bath | Per Cent Transmission Filter 550 (T) | Optical Density (D) | Conc. of Dyebath (grams/liter) (C) |
|-----------------------------|-----------------------|------------------------|---------------|------------------|---|---------------------------|---|
| 0 | 0 | 90 | Initial conc. | | | | 0.557 |
| 1 | 3 | 120 | Dye only | 9.9 | 39.2 | 0.407 | 0.487 |
| 2 | 5 | 160 | Buffer added | 6.2 | 36.7 | 0.435 | 0.521 |
| 3 | 18 | 185 | | 6.2 | 43.6 | 0.361 | 0.434 |
| 4 | 22 | 195 | | 6.0 | 45.0 | 0.347 | 0.418 |
| 5 | 27 | 220 | | 6.0 | 46.5 | 0.333 | 0.400 |
| 6 | 32 | 240 | | 6.0 | 49.0 | 0.310 | 0.372 |
| 7 | 37 | 250 | | 6.0 | 50.0 | 0.301 | 0.362 |
| 8 | 47 | 258 | | 5.8 | 49.5 | 0.305 | 0.366 |
| 9 | 52 | 180 | | 5.85 | 57.2 | 0.243 | 0.292 |
| 10 | 62 | 200 | Salt added | 5.75 | 75.0 | 0.125 | 0.159 |
| 11 | 67 | 190 | | 5.9 | 78.6 | 0.105 | 0.134 |

Total Dyebath Exhaustion 76.1%
pH Tap-water 8.85

Table 76. Test for Stability of Pontamine
Blue AX Conc. - High Temperature
Acid pH

Per cent transmission of light through various filters for dye bath samples listed in Table 75.

| Monochromatic Filter Number (millimicrons) | Dye Bath Sample Number | | |
|---|---|------|------|
| | 1 | 8 | 11 |
| | Per Cent Transmission at Wave Length Indicated | | |
| 390 | 85.0 | 88.6 | 96.1 |
| 420 | 84.3 | 88.5 | 95.0 |
| 440 | 84.1 | 88.1 | 95.0 |
| 465 | 82.5 | 86.8 | 94.5 |
| 490 | 67.6 | 74.0 | 89.8 |
| 515 | 59.7 | 67.2 | 86.7 |
| 550 | 39.2 | 49.5 | 78.6 |
| 575 | 45.2 | 56.0 | 82.1 |
| 595 | 49.8 | 60.1 | 84.0 |
| 620 | 58.8 | 68.2 | 87.7 |
| 640 | 70.5 | 78.4 | 92.2 |
| 660 | 75.1 | 81.7 | 93.4 |

BIBLIOGRAPHY

LITERATURE CITED

1. Young, Ernest N., An Evaluation of the Use of High Temperature Procedures for Applying Direct Dyes to Cotton Yarn., A Thesis. Atlanta: Georgia Institute of Technology, 1953, p. 36.
2. "Report of the Committee Appointed by Council to Discuss the Dyeing Properties of Direct Cotton Dyes", The Journal of the Society of Dyers and Colourists, 62 (September 1946), pp. 280-85.
3. Venkataraman, K., The Chemistry of Synthetic Dyes, Vol. I. New York: Academic Press, Inc., 1952, p. 2.
4. Ibid., p. 4.
5. Ibid., p. 5.
6. Ibid., p. 271.
7. Ibid., p. 271.
8. Royer, G. L., and others, "Dyeing Studies at Elevated Temperatures", Textile Research Journal, 18 (October, 1948), pp. 598-614.
9. Ibid., p. 600.
10. Valko, E., "Particle Size in Wool Dyeing", The Journal of the Society of Dyers and Colourists, 55 (April 1939), pp. 173-182.
11. "Report of the Committee to Discuss Direct Dyes", pp. 280-85.
12. "Classification of du Pont Direct and Developed Dyes on Cotton", The Technical Bulletin, Vol. 10, No. 1. Wilmington, Delaware: Published by E. I. du Pont de Nemours and Company, Inc., March 1954, pp. 11-16.
13. Philadelphia Section, American Association of Textile Chemists and Colorists, "Some Phases of High Temperature Dyeing", American Dyestuff Reporter, 38 (January 10, 1949), pp. 9-32.
14. Drijvers, Louis, "The Dyeing of Textile Fibers at High Temperature", American Dyestuff Reporter, 41 (September 1, 1952), pp. 533-540.
15. Vickerstaff, Thomas, The Physical Chemistry of Dyeing. New York: Interscience Publishers, Inc., 1950, p. 68.
16. Steverlynck, B., "Superheated Dyebaths", The Dyer, 109 (March 20, 1953), pp. 389-392, 396.

17. Drijvers, Louis, "The Dyeing of Textile Fibers under Static Pressure", The American Dyestuff Reporter, 43 (April 12, 1954), pp. 243-6.
18. Herrmann, Erich, "Direct Dyestuffs for Dyeing at Temperatures above 100° C.", Melliand Textilberichte, 33 (December, 1952), pp. 1110-13.
19. Drijvers, "Dyeing under Static Pressure", p. 244.
20. Butterworth, K., "The Dyeing of Viscose Rayon at High Temperatures", Journal of the Society of Dyers and Colourists, 69 (October 1953), pp. 357-392.
21. A.S.T.M. Committee D-13 on Textile Materials, A.S.T.M. Standards on Textile Materials. Philadelphia: American Society for Testing Materials, 1952, pp. 337-343.
22. Direct Colors on Cotton, Wilmington: E. I. du Pont de Nemours Co., Inc., Publishers, pp. 102-105.
23. Vickerstaff, op. cit., p. 36.
24. 1954 Technical Manual and Yearbook of the American Association of Textile Chemists and Colorists, Vol. XXX. New York: Howes Publishing Co., Inc., 1954, p. 99.
25. Ibid., p. 82.
26. Dyeing Properties Direct Dyestuffs, Switzerland: Geigy Dyestuff Division of Geigy Chemical Corporation, 1954, p. 6.
27. Vickerstaff, op. cit., p. 29.
28. Ibid., p. 30.
29. Ibid., p. 34.
30. Ibid., p. 30.
31. Ibid., p. 34.
32. Stearns, E. I., "Whats New in Spectrophotometry: Progress of Spectrophotometry in the Textile Industry", Dyestuff Technical Bulletin, No. 820, Bound Brook, New Jersey: American Cyanamid Company, 1954, p. 13.
33. Mellon, M. G., Analytical Absorption Spectroscopy. New York: John Wiley and Sons, Inc., 1950, p. 130.
34. Kienle, R. H., and others, "The Dyeometer: An Instrument for Studying Color Reactions", Textile Research Journal, 16 (December, 1946), pp. 616-626.

35. Simon, F. T., "The Spectrophotometer as an Aid to Dyeing", Textile Research Journal, 19 (September, 1949), pp. 567-74.

OTHER REFERENCES

Boulton, John, "A Unified Theory of Textile Dyeing", Dyestuffs, Vol. 40, No. 8, New York: National Aniline Division of Allied Chemical and Dye, Inc., April 1954, p. 199.

"Classification of du Pont Direct and Developed Dyes on Cotton", The Technical Bulletin, Vol. 10, No. 1, March 1954, Wilmington, Delaware: E. I. du Pont de Nemours Co., Inc.

Fox, M. R., "Dyeing", Review of Textile Progress, Vol. 4, 1952, London: Published jointly by the Textile Institute and the Journal of the Society of Dyers and Colourists, 1952.

McCleary, H. R., "Fundamentals of the Dyeing of Cellulose Fiber", Textile Research Journal, 23 (October 1953), p. 673.

Royer, G. L., and others, "Studies on Rayon Dyeing: Application of the Dyeometer", Textile Research Journal, 17 (August, 1947), p. 438-447.

"Spectrophotometry", The Technical Bulletin, Vol. 5, No. 3. Wilmington, Delaware: The E. I. du Pont de Nemours Co., Inc., September, 1949, pp. 121-148.