

**INSTITUTE OF
PAPER CHEMISTRY**
Appleton Wisconsin

Institute of Paper Science and Technology
Central Files

**CONTINUOUS EVALUATION OF
CORRUGATING MEDIUM**

Project 1108-17

Progress Report Fourteen

to

FOURDRINIER KRAFT BOARD INSTITUTE, INC.

December 1, 1956

THE INSTITUTE OF PAPER CHEMISTRY

Appleton, Wisconsin

CONTINUOUS EVALUATION OF CORRUGATED MEDIUM

Project 1108-17

Progress Report Fourteen

to

FOURDRINIER KRAFT BOARD INSTITUTE, INC.

December 1, 1956

THE INSTITUTE OF PAPER CHEMISTRY

Appleton, Wisconsin

CONTINUOUS EVALUATION OF CORRUGATING MEDIUM

The purpose of this study is to provide a continuous evaluation of the quality and runability of corrugating medium produced by members of the Fourdrinier Kraft Board Institute. The study, as it progresses, will accumulate a backlog of data and experience which will provide two important benefits. First, it will enable each participant to evaluate his position in relation to the rest of the industry. Second, it will provide information essential for the interpretation of any proposed specifications on corrugating medium (on either a company or industry basis).

The procedure for participating in this study involves the submission of two rolls of corrugating medium per week from each machine to The Institute of Paper Chemistry. These rolls are taken from regular production runs on different days. Each roll is 10 to 12 inches wide and contains approximately 2,500 lineal feet of medium (approximately 20 inches in diameter). Each roll as it is received by the Institute is assigned a code letter and number. The rolls are numbered in the sequence in which they are received. Code letters are assigned on the basis of machines and a given machine is assigned a different code letter each month in order to mask the identity of the mills. For purposes of reference, a copy of the outline of the program together with the necessary instructions for sampling was appended to Progress Report One in this series.

During the month of November, sixty-six different sample lots of corrugating medium were submitted from the production of twelve machines to The Institute of Paper Chemistry for evaluation. A tabulation of the samples classified according to machines may be seen in Table I.

TABLE I
DISTRIBUTION OF CORRUGATING MEDIUM SAMPLES

Machine Code	Number of Samples
A	2
B	2
C	9
D	7
E	8
F	9
G	4
H	6
I	0
J	5
K	4
L	8
M	<u>2</u>
Total	66

Each sample of corrugating medium was evaluated for basis weight, caliper, Concora flat crush, H. and D. flat crush (single-faced board), and runability. Runability was measured by corrugating each roll under standardized conditions on the Institute's corrugator into A-flute board at 600 feet per minute. If unsatisfactory runability occurred at this speed, the corrugator was slowed down in increments of 25 f.p.m. until satisfactory runability was obtained (no ruptured flutes). As indicated above, flat crush was determined on the combined board, thereby providing data which may be useful in studying the relationship between Concora flat crush and combined board flat crush for each participant's medium.

As requested by members of the F.K.B.I., the Concora medium test results are calculated on the basis of pounds of load per unit area rather than on the basis of the formula suggested by the Concora manufacturer and are reported as Concora flat crush test results. In Progress Report One and Two, the Concora medium test results were reported on the basis of the formula suggested by the Concora manufacturer.

The average test results obtained on the samples of corrugating medium submitted by each participant during October are shown in Table II and graphically presented in Figures 1 to 4. In addition to a comparison of the test data obtained for the various machines, Table II also presents the current F.K.I. averages, cumulative F.K.I. averages, and the F.K.I. indexes. The current F.K.I. average is the average test results for all machines participating in the study during a given month. The cumulative F.K.I. average is based on the results for the previous months excluding the result for the current period. The F.K.I. index is obtained as follows:

$$\frac{\text{current F.K.I. average}}{\text{cumulative F.K.I. average}} \times 100 = \text{F.K.I. index (\%)}$$



The F.K.I. index provides a ready means of comparing the current quality with previous results. An index greater than 100% indicates that current quality is higher than the average result for the previous periods; an index below 100% indicates that current quality is lower than the average result for the previous periods.

The test results obtained on the sample lots submitted from the production of each of the machines are shown in Table III through XV for



TABLE II
 SUMMARY OF CURRENT MACHINE AVERAGES

November, 1956

Mill Code	Basis Weight, lb.	Caliper, points	Concora Flat Crush, p.s.i.	Single-Face Flat Crush, p.s.i.
A	26.5	10.5	32.1	27.4
B	27.4	11.6	40.7	40.9
C	27.0	9.7	27.7	29.5
D	27.0	10.0	36.4	36.8
E	26.7	10.6	38.3	36.9
F	26.4	10.5	33.7	32.5
G	26.9	9.7	40.6	39.1
H	29.8	11.7	34.4	34.2
I	No samples submitted.			
J	26.6	11.9	36.9	34.7
K	26.0	9.3	35.2	35.7
L	26.8	10.8	42.7	39.5
M	29.3	10.4	37.7	37.9
Current F.K.I. Average	27.2	10.5	36.4	35.4
Cumulative F.K.I. Average	27.1	10.4	33.2	34.5
F.K.I. Index, %	100.4	101.8	109.6	102.6

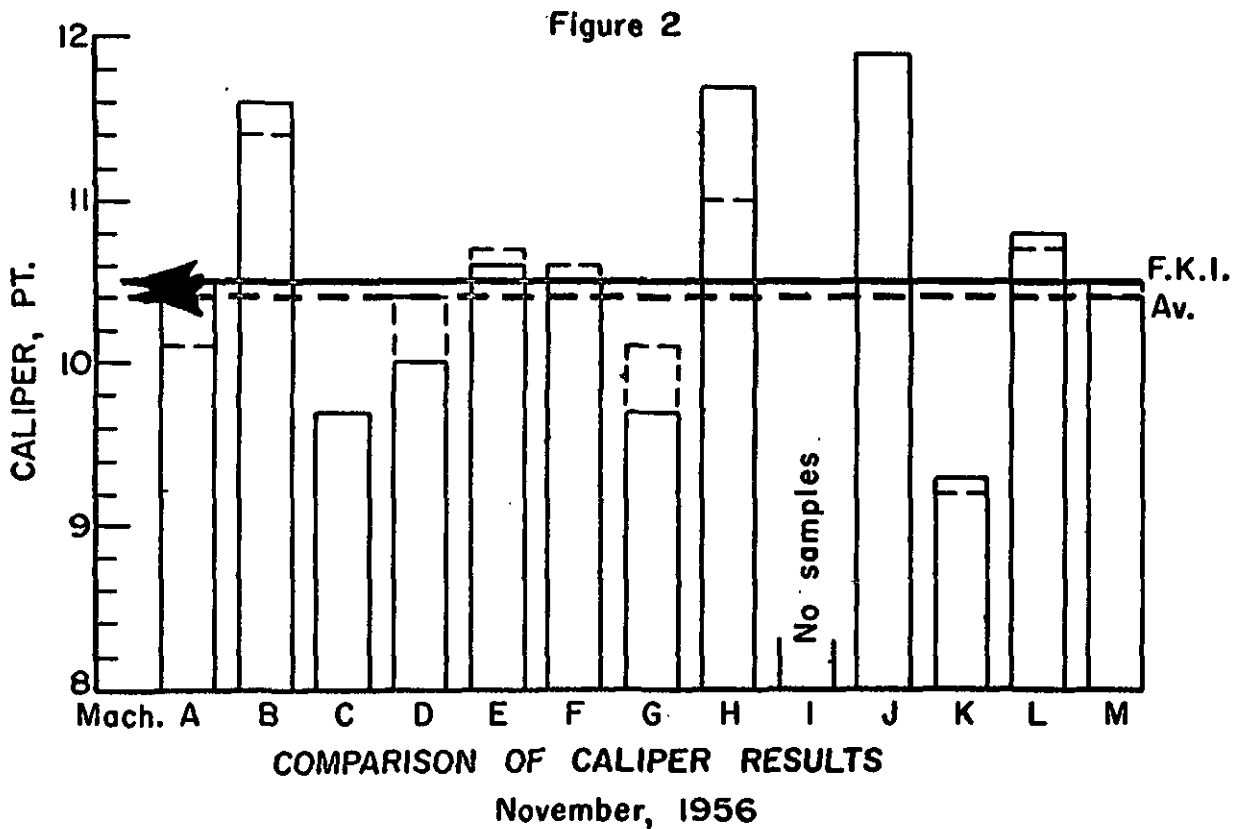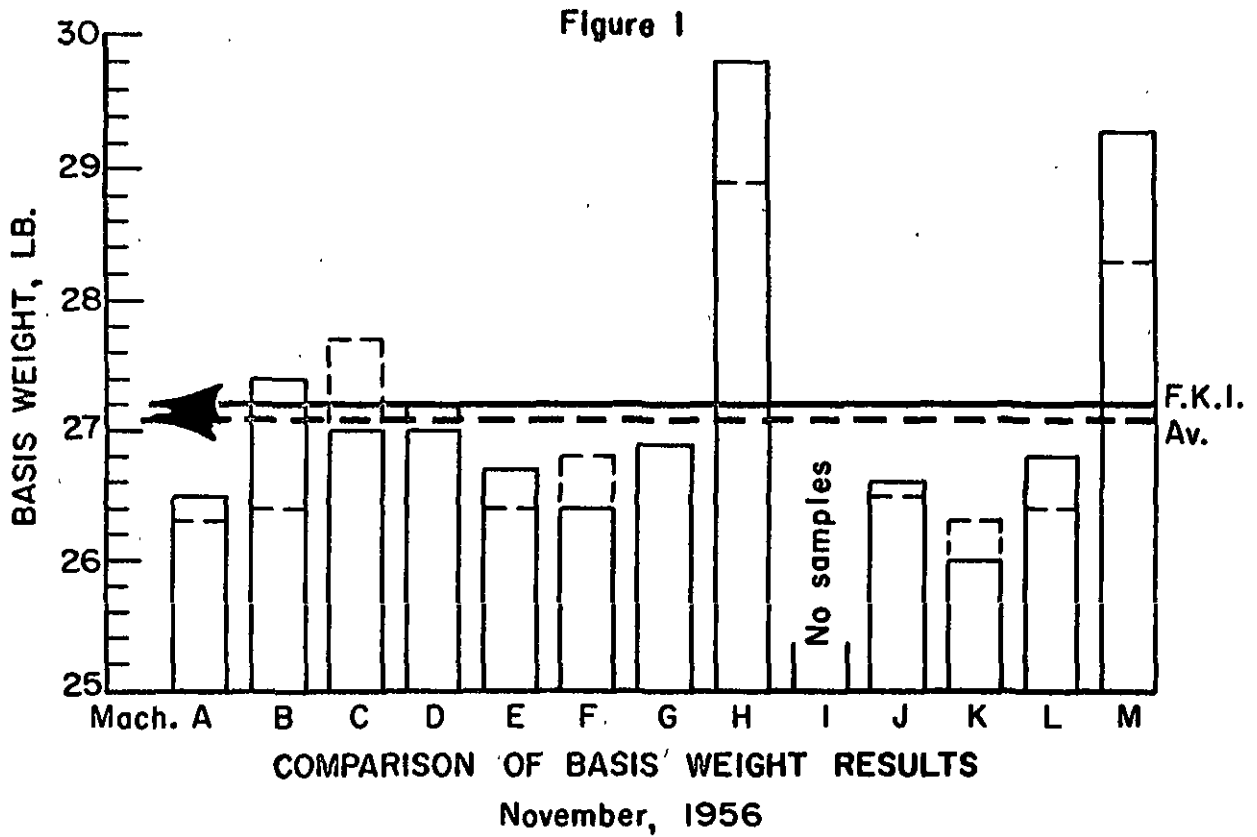

———— Current machine average
----- Cumulative machine average

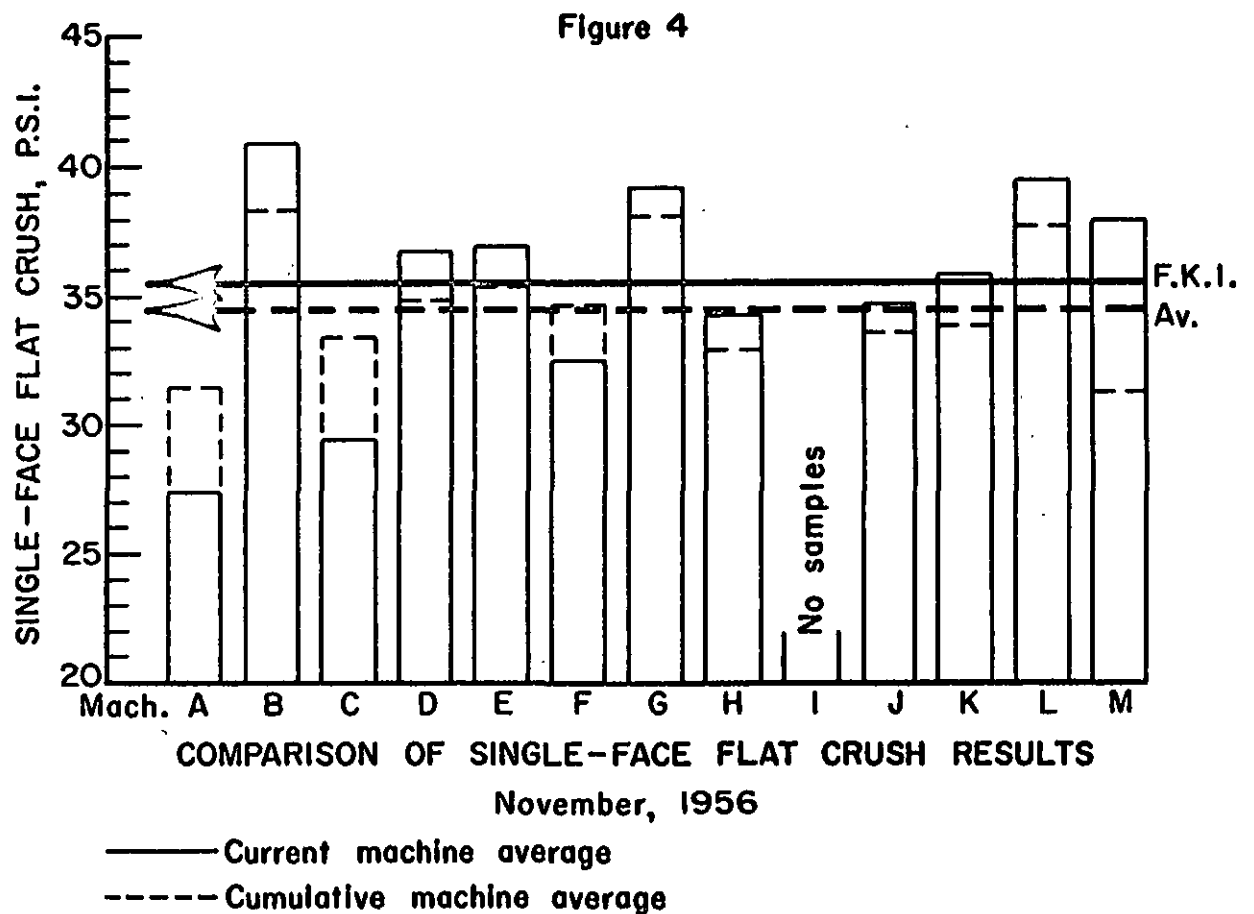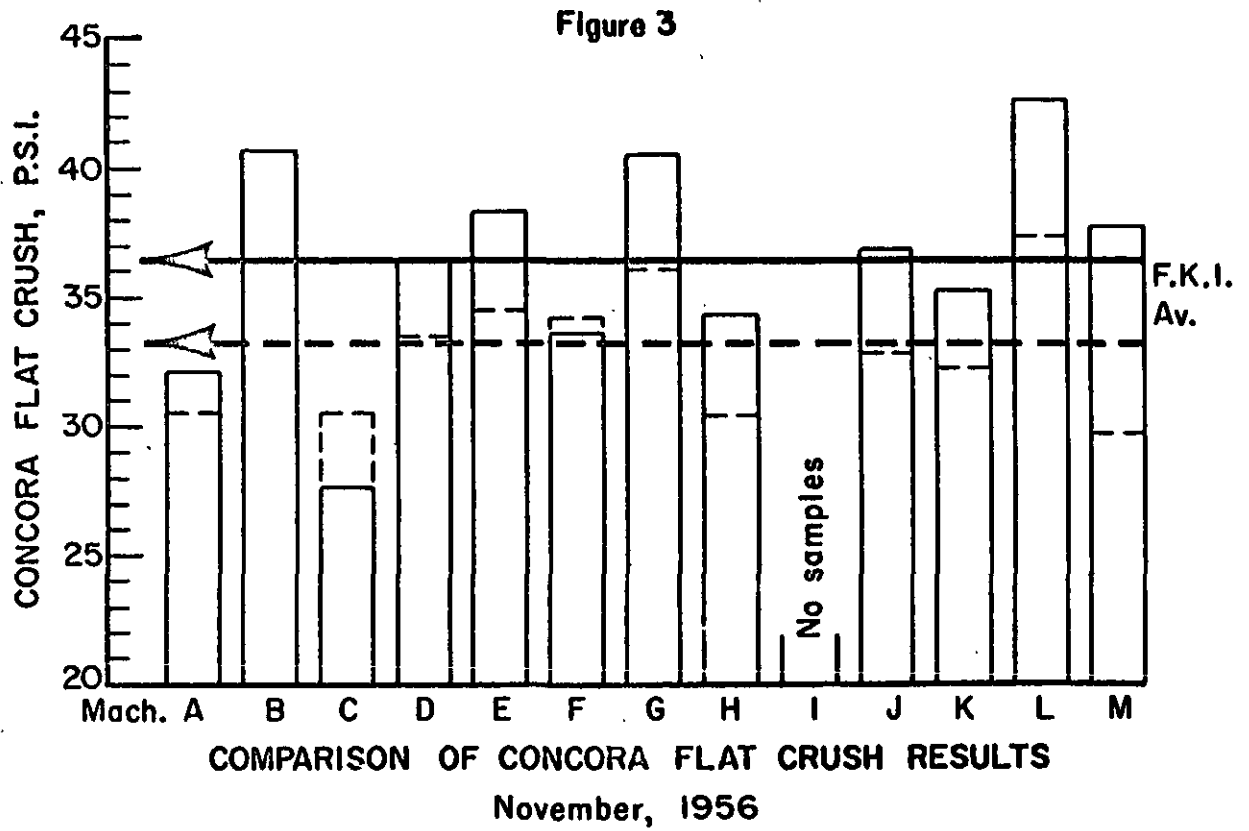

Machines A through M, respectively. The maximum, minimum, and average test results obtained on each sample lot are shown for all tests except basis weight for which only the average is shown; in addition, the over-all average result for all the sample lots submitted for each machine is shown for each test. The latter over-all averages are reported as "current machine averages." A cumulative machine average is also shown and is calculated by averaging the current machine averages for the previous periods (excluding the current period). Also shown for each machine in Tables III to XVI are the machine factor and machine index which are defined as follows:

$$\frac{\text{current machine average}}{\text{cumulative machine average}} \times 100 = \text{machine factor (\%)}$$

$$\frac{\text{current machine average}}{\text{cumulative F.K.I. average}} \times 100 = \text{machine index (\%)}$$

The machine factor and machine index provide a means for comparing the current machine average with either the previous results for that particular machine or with the cumulative results for all machines--i.e., the cumulative F.K.I. average.

In Table II the current machine averages for the month of November are summarized. It may be noted that basis weight varied from a low of 26.0 lb. for Machine K to a high of 29.8 lb. for Machine H. The average basis weight for the twelve participating machines (current F.K.I. average) was 27.2 lb. per 1000 sq. ft., which is slightly higher than the cumulative F.K.I. average of 27.1 lb. as indicated by the F.K.I. index of 100.4%. The average results for all machines satisfy the requirements of Rule 41.

Caliper results varied from a low value of 9.3 for Machine K to a high value of 11.9 for Machine J. The current F.K.I. average for caliper was 10.5 points, slightly higher than the cumulative F.K.I. average of 10.4 points. The average caliper results for all machines meet the Rule 41 specification.

Concora flat crush test results ranged from a minimum of 27.7 p.s.i. for Machine C to a maximum of 42.7 p.s.i. for Machine L. The current F.K.I. average was 36.4 p.s.i., slightly higher than the cumulative F.K.I. average of 33.2 p.s.i. as indicated by the F.K.I. index of 109.6.

Machine B had the highest average single-face flat crush of 40.9 p.s.i. and Machine A had the lowest, 27.4 p.s.i. The current F.K.I. average for flat crush was 35.4 p.s.i., whereas the cumulative F.K.I. average was 34.5 p.s.i., giving an F.K.I. index of 102.6%.

For the current period, the current F.K.I. averages for all tests--basis weight, caliper, Concora flat crush and single-face flat crush--exceeded their respective cumulative averages.

TABLE III
 SUMMARY OF TEST RESULTS FOR MACHINE A
 November, 1956

Code	Date Made	Date Recd.	Mill Roll No.	Basis Weight, lb. per 1000 sq. ft.	Caliper, points			Concora Flat Crush, p.s.i.			Single-Face Flat Crush, p.s.i.			Runability
					Max.	Min.	Av.	Max.	Min.	Av.	Max.	Min.	Av.	
A-1	10-17-56	11-14-56	12	26.3	10.9	9.8	10.4	33.0	30.0	31.7	27.4	22.2	25.6	Satisfactory at 300 f.p.m.
A-2	10-17-56	11-14-56	13	26.8	11.0	10.1	10.5	35.4	31.2	32.5	31.8	27.8	29.2	Satisfactory at 425 f.p.m.
Current Machine Average:				26.5			10.5		32.1				27.4	
Cumulative Machine Average:				26.3			10.1		30.6				31.4	
Machine Factor, %:				101.0			103.9		105.0				87.2	
Machine Index, %:				97.9			100.9		96.8				79.3	

TABLE IV
 SUMMARY OF TEST RESULTS FOR MACHINE B

Code	Date Made	Date Recd.	Mill Roll No.	Basis Weight, lb. per 1000 sq. ft.	Caliper, points			Concora Flat Crush, p.s.i.			Single-face Flat Crush, p.s.i.			Runability
					Max.	Min.	Av.	Max.	Min.	Av.	Max.	Min.	Av.	
B-1	10-5-56	10-26-56	--	27.1	12.1	11.1	11.6	39.0	41.9	41.6	40.8	41.3	41.3	Satisfactory at 600 f.p.m.
B-2	--	10-30-56	--	27.7	12.1	11.1	11.7	34.2	39.5	42.6	39.2	40.4	40.4	Satisfactory at 600 f.p.m.
Current Machine Average				27.4			11.6	40.7				40.9		
Cumulative Machine Average				26.4			11.4	36.4				38.3		
Machine Factor, %				103.8			102.5	111.8				106.6		
Machine Index, %				101.0			112.3	122.6				118.5		

TABLE V
 SUMMARY OF TEST RESULTS FOR MACHINE C

Code	Date Made	Date Recd.	Mill Roll No.	Basis Weight, lb. per 1000 sq. ft.	Caliper, points			Concora Flat Crush, p.s.i.			Single-Face Flat Crush, p.s.i.			Runability
					Max.	Min.	Av.	Max.	Min.	Av.	Max.	Min.	Av.	
C-1	10-19-56	10-26-56	15	23.5	10.1	9.4	9.9	29.4	27.6	28.3	31.4	29.6	30.4	Satisfactory at 600 f.p.m.
C-2	10-19-56	10-26-56	16	28.4	10.1	9.0	9.6	31.2	27.0	29.3	31.3	27.8	29.9	Satisfactory at 600 f.p.m.
C-3	10-20-56	10-26-56	17	26.8	10.5	9.0	9.8	30.0	27.0	28.9	32.2	25.4	28.9	Satisfactory at 600 f.p.m.
C-4	10-20-56	10-26-56	18	26.9	10.1	9.0	9.7	30.0	27.6	28.4	32.6	29.2	30.3	Satisfactory at 600 f.p.m.
C-5	10-29-56	11-13-56	21	26.5	10.0	9.1	9.5	30.0	25.8	27.5	33.0	29.6	31.0	Satisfactory at 600 f.p.m.
C-6	10-29-56	11-13-56	22	26.3	9.8	9.0	9.4	31.2	25.8	29.0	31.2	29.0	30.0	Satisfactory at 600 f.p.m.
C-7	11-10-56	11-19-56	23	27.0	10.1	9.7	9.9	24.6	22.2	23.3	31.0	25.0	28.2	Satisfactory at 600 f.p.m.
C-8	11-10-56	11-19-56	25	26.6	10.0	9.5	9.9	30.0	23.4	27.1	29.0	26.0	27.5	Satisfactory at 600 f.p.m.
C-9	11-10-56	11-20-56	24	26.3	10.0	9.2	9.8	28.8	26.4	27.6	29.4	28.2	23.7	Satisfactory at 600 f.p.m.
Current Machine Average:				27.0		9.7	9.7	27.7		27.7		29.5		29.5
Cumulative Machine Average:				27.7		9.7	9.7	30.6		30.6		33.4		33.4
Machine Factor, %:				97.4		100.0	100.0	90.7		90.7		33.1		33.1
Machine Index, %:				99.7		93.7	93.7	83.6		83.6		35.4		35.4

TABLE VI
SUMMARY OF TEST RESULTS FOR MACHINE D
November, 1956

Code	Date Made	Date Recd.	Mill Roll No.	Basis Weight, lb. per 1000 sq. ft.	Caliper, points		Concora Flat Crush, p.s.i.		Single-Face Flat Crush, p.s.i.		Runability			
					Max.	Min.	Max.	Min.	Max.	Min.		Av.		
D-1	10-15-56	10-29-56	S9	27.4	11.0	9.3	10.5	32.4	23.8	31.3	37.0	31.4	35.2	Satisfactory at 600 p.p.m.
D-2	10-19-56	10-29-56	90	26.5	10.9	9.0	9.3	42.6	35.7	37.8	41.0	35.2	33.3	Satisfactory at 600 p.p.m.
D-3	10-22-56	11-5-56	91	27.1	10.9	10.0	10.5	41.4	33.4	39.7	41.4	37.2	39.3	Satisfactory at 600 p.p.m.
D-4	10-25-56	11-5-56	92	27.3	11.0	9.9	10.3	37.8	31.3	34.6	36.2	34.0	35.5	Satisfactory at 600 p.p.m.
D-5	10-30-56	11-13-56	93	27.4	10.4	9.5	10.0	39.0	35.4	37.2	40.6	37.2	33.1	Satisfactory at 600 p.p.m.
D-6	11-1-56	11-13-56	94	27.1	10.3	9.0	9.7	37.2	34.3	36.1	36.0	31.0	34.4	Satisfactory at 600 p.p.m.
D-7	11-9-56	11-19-56	95	26.6	10.0	9.0	9.5	42.0	35.4	33.3	39.6	34.6	36.9	Satisfactory at 600 p.p.m.
Current Machine Average:				27.0		10.0		36.4		36.4			36.3	
Cumulative Machine Average:				27.2		10.4		33.6		33.6			34.9	
Machine Factor, %:				99.3		96.7		103.5		103.5			105.5	
Machine Index, %:				99.7		96.3		109.3		109.3			106.7	

TABLE VII
 SUMMARY OF TEST RESULTS FOR MACHINE E
 November, 1956

Code	Date Made	Date Recd.	Mill Roll No.	Basis Weight, lb. per 1000 sq. ft.	Caliper, points			Concora Flat Crush, p.s.i.			Single-Face Flat Crush, p.s.i.			Runability
					Max.	Min.	Av.	Max.	Min.	Av.	Max.	Min.	Av.	
E-1	10-23-56	10-29-56	206	26.9	11.1	10.5	10.9	41.4	37.2	38.9	38.4	35.2	36.8	Satisfactory at 600 f.p.m.
E-2	10-26-56	11-2-56	208	27.0	11.4	10.8	11.1	37.2	31.2	33.7	31.0	29.2	30.0	Satisfactory at 575 f.p.m.
E-3	10-31-56	11-5-56	210	25.7	11.0	10.0	10.6	36.0	32.4	34.4	36.0	33.6	34.6	Satisfactory at 450 f.p.m.
E-4	11-3-56	11-8-56	212	26.1	11.7	10.3	10.9	40.8	36.6	33.6	33.6	36.0	30.7	Satisfactory at 550 f.p.m.
E-5	11-6-56	11-13-56	214	27.1	10.8	10.0	10.2	45.2	43.2	44.2	42.4	37.8	39.4	Satisfactory at 600 f.p.m.
E-6	11-10-56	11-15-56	216	26.8	10.5	10.0	10.1	37.8	30.6	34.8	39.4	35.6	37.4	Satisfactory at 600 f.p.m.
E-7	11-14-56	11-19-56	218	26.9	11.0	10.1	10.5	43.2	39.0	42.0	41.3	33.2	39.6	Satisfactory at 600 f.p.m.
E-8	11-16-56	11-23-56	220	27.3	10.9	10.0	10.3	41.4	37.2	39.7	42.8	33.8	40.3	Satisfactory at 575 f.p.m.
Current Machine Average:				26.7			10.6		38.3				36.9	
Cumulative Machine Average:				26.4			10.7		34.6				35.3	
Machine Factor, %				101.3			98.8		110.5				104.5	
Machine Index, %				98.6			101.9		115.4				106.8	

TABLE VIII
SUMMARY OF TEST RESULTS FOR MACHINE F
November, 1956

Code	Date Made	Date Recd.	Mill Roll No.	Basis Weight, lb. per 1000 sq. ft.	Caliper, points			Concora Flat Crush, P.S.I.			Single-Face Flat Crush, P.S.I.			Runability
					Max.	Min.	Av.	Max.	Min.	Av.	Max.	Min.	Av.	
F-1	10-23-56	10-26-56	84	26.0	11.0	10.8	10.9	34.8	32.4	33.7	32.2	30.8	31.6	Satisfactory at 600 f.p.m.
F-2	10-26-56	10-29-56	85	26.3	11.1	10.1	10.5	34.2	31.2	32.6	32.8	31.0	31.9	Satisfactory at 600 f.p.m.
F-3	10-30-56	11-2-56	86	26.3	10.5	10.0	10.2	31.2	27.6	29.9	31.4	28.2	29.8	Satisfactory at 575 f.p.m.
F-4	11-1-56	11-5-56	87	26.5	11.0	10.2	10.6	35.4	34.2	34.9	33.8	32.6	33.2	Satisfactory at 600 f.p.m.
F-5	11-6-56	11-9-56	88	26.6	11.1	10.2	10.8	32.4	29.4	30.8	33.4	31.6	32.5	Satisfactory at 600 f.p.m.
F-6	11-8-56	11-13-56	89	26.2	10.5	9.9	10.2	38.4	36.6	37.4	34.8	31.4	32.7	Satisfactory at 600 f.p.m.
F-7	11-13-56	11-16-56	90	26.8	10.5	10.0	10.3	36.0	33.0	34.9	34.6	32.4	33.5	Satisfactory at 600 f.p.m.
F-8	11-15-56	11-19-56	90	26.3	10.9	10.1	10.5	36.6	32.4	34.6	35.0	32.4	33.6	Satisfactory at 600 f.p.m.
F-9	11-19-56	11-23-56	91	26.3	10.9	10.1	10.5	36.6	31.8	34.0	34.4	31.4	33.3	Satisfactory at 600 f.p.m.
Current Machine Average				26.4			10.5			33.7			32.5	
Cumulative Machine Average				26.8			10.6			34.3			34.7	
Machine Factor, %				98.5			98.5			98.2			93.7	
Machine Index, %				97.2			101.2			101.4			94.1	

TABLE IX
SUMMARY OF TEST RESULTS FOR MACHINE G
November, 1956

Code	Date Made	Date Recd.	Mill Roll No.	Basis Weight, lb. per 1000 sq. ft.	Caliper, points		Concora Flat Crush, P.S.I.		Single-Face Flat Crush, P.S.I.		Runability				
					Max.	Min.	Max.	Min.	Max.	Min.		Av.			
G-1	11-1-56	11-9-56	100	26.8	10.0	9.1	9.5	40.8	37.8	38.8	38.6	32.4	35.8	Satisfactory at 600 f.p.m.	
G-2	11-6-56	11-19-57	101	27.5	10.1	9.8	10.0	43.8	40.8	42.4	42.2	39.0	40.6	Satisfactory at 600 f.p.m.	
G-3	11-8-56	11-19-56	102	26.5	10.1	9.2	9.3	40.8	34.2	38.9	42.0	37.8	39.6	Satisfactory at 600 f.p.m.	
G-4	11-13-56	11-19-56	103	26.8	10.0	9.1	9.5	46.6	37.3	42.4	41.4	38.6	40.3	Satisfactory at 600 f.p.m.	
Current Machine Average				26.9			9.7	40.6				39.1			
Cumulative Machine Average				26.9			10.1	36.0				38.1			
Machine Factor, %				100.0			96.0	112.3				102.7			
Machine Index, %				99.2			93.4	122.3				113.2			

TABLE X
SUMMARY OF TEST RESULTS FOR MACHINE H
November, 1956

Code	Date Made	Date Recd.	Mill Roll No.	Basis Weight, lb. per 1000 sq. ft.	Caliper, points		Concora Flat Crush, P.S.I.		Single-Face Flat Crush, P.S.I.		Runability				
					Max.	Min.	Max.	Min.	Max.	Min.		Av.			
H-1	10-30-56	11-2-56	73	28.5	12.2	11.0	11.6	30.0	27.6	28.9	31.4	29.4	30.1	Satisfactory at 600 f.p.m.	
H-2	11-1-56	11-6-56	74	29.3	11.3	10.3	11.1	36.6	34.8	36.1	38.4	35.2	36.9	Satisfactory at 600 f.p.m.	
H-3	11-9-56	11-13-56	75	29.9	12.1	11.2	11.8	36.0	32.4	34.9	36.6	34.0	35.2	Satisfactory at 600 f.p.m.	
H-4	11-13-56	11-16-56	76	30.3	12.0	10.9	11.6	36.6	31.8	34.4	35.3	31.0	33.1	Satisfactory at 600 f.p.m.	
H-5	11-16-56	11-20-56	77	30.7	12.1	11.5	11.9	37.8	34.2	35.9	36.3	32.8	35.0	Satisfactory at 600 f.p.m.	
H-6	11-20-56	11-23-56	78	30.4	12.3	11.5	11.9	33.4	34.2	36.0	36.6	33.8	35.1	Satisfactory at 600 f.p.m.	
Current Machine Average				29.3			11.7	34.4				34.2			
Cumulative Machine Average				28.9			11.0	30.5				32.9			
Machine Factor, %				103.3			105.5	112.8				104.2			
Machine Index, %				110.1			112.5	103.6				99.2			

TABLE XI
SUMMARY OF TEST RESULTS FOR MACHINE I
November, 1956

Code	Date Made	Date Recd.	Mill Roll No.	Basis Weight, lb. per 1000 sq. ft.	Caliper, points	Concors Flat Crush, P.s.i.	Single-Face Flat Crush, p.s.i.	Runability
					Min. Av.	Max. Min. Av.	Max. Min. Av.	

No samples submitted.

TABLE XII
SUMMARY OF TEST RESULTS FOR MACHINE J
November, 1956

J-1	11-6-56	11-9-56	77	26.3	11.0	11.4	37.8	34.8	36.1	36.6	31.8	34.3	Satisfactory at 600 f.p.m.
J-2	11-8-56	11-13-56	78	26.1	11.7	12.2	39.0	34.8	36.5	34.6	32.8	33.5	Satisfactory at 600 f.p.m.
J-3	11-13-56	11-16-56	79	26.0	10.5	11.3	37.2	32.4	35.2	36.6	34.6	35.7	Satisfactory at 600 f.p.m.
J-4	11-15-56	11-19-56	80	27.8	11.8	12.2	38.4	34.8	37.0	35.2	32.6	36.0	Satisfactory at 600 f.p.m.
J-5	11-20-56	11-23-56	81	26.8	11.0	12.2	41.4	37.8	39.6	37.4	34.4	36.0	Satisfactory at 600 f.p.m.
Current Machine Average				26.6	11.9				36.9			34.7	
Cumulative Machine Average				26.5	10.5				32.9			33.5	
Machine Factor, %				100.3	112.9				111.9			103.5	
Machine Index, %				98.2	114.8				111.1			100.7	

TABLE XIII
SUMMARY OF TEST RESULTS FOR MACHINE K
November, 1956

K-1	10-8-56	10-26-56	82	26.7	10.7	9.1	10.1	39.6	34.8	37.2	37.8	34.4	35.8	Satisfactory at 600 f.p.m.
K-2	10-10-56	10-26-56	83	25.7	10.1	9.0	9.7	37.8	34.2	36.1	36.8	34.4	35.8	Satisfactory at 600 f.p.m.
K-3	10-27-56	11-5-56	86	25.8	9.2	8.9	9.0	37.2	34.8	36.0	36.0	33.4	34.9	Satisfactory at 600 f.p.m.
K-4	11-1-56	11-5-56	87	25.7	8.9	8.1	8.4	34.2	30.0	31.6	37.6	35.2	36.3	Satisfactory at 600 f.p.m.
Current Machine Average				26.0		9.3			35.2			35.7		
Cumulative Machine Average				26.3		9.2			32.2			33.7		
Machine Factor, %				98.8	100.8				109.5			106.1		
Machine Index, %				95.7	89.8				106.2			103.5		

TABLE XIV
 SUMMARY OF TEST RESULTS FOR MACHINE L
 November, 1956

Code	Date Made	Date Recd.	Mill Roll No.	Basis Weight, lb. per 1000 sq. ft.	Caliper, points			Concora Flat Crush, p.s.i.			Single-Face Flat Crush, p.s.i.			Runability	
					Max.	Min.	Av.	Max.	Min.	Av.	Max.	Min.	Av.		
L-1	10-23-56	10-29-56	205	26.6	11.5	10.5	11.0	42.6	39.0	41.2	42.6	36.8	39.3	Satisfactory at 600 f.p.m.	
L-2	10-26-56	11-2-56	207	26.5	11.5	10.8	11.0	42.0	34.8	39.2	39.4	36.0	37.8	Satisfactory at 600 f.p.m.	
L-3	10-31-56	11-5-56	209	26.8	11.9	10.5	11.1	42.6	40.2	41.6	41.8	39.4	40.7	Satisfactory at 600 f.p.m.	
L-4	11-3-56	11-8-56	211	26.5	11.3	10.1	10.9	44.4	42.0	43.0	42.8	37.8	40.0	Satisfactory at 550 f.p.m.	
L-5	11-6-56	11-13-56	213	26.6	11.0	10.0	10.4	49.2	44.4	46.9	43.4	40.2	42.3	Satisfactory at 600 f.p.m.	
L-6	11-10-56	11-15-56	215	26.8	10.9	10.0	10.4	44.4	39.0	42.4	40.0	35.8	38.8	Satisfactory at 600 f.p.m.	
L-7	11-12-56	11-19-56	217	27.2	11.7	10.0	10.8	48.0	43.2	45.1	38.4	37.0	37.6	Satisfactory at 600 f.p.m.	
L-8	11-17-56	11-23-56	219	27.1	11.1	10.5	10.9	44.4	40.2	42.5	40.3	38.8	39.6	Satisfactory at 600 f.p.m.	
Current Machine Average				26.8			10.8			42.7				39.5	
Cumulative Machine Average				26.4			10.7			37.4				37.7	
Machine Factor, %				101.3			101.4			114.3				104.9	
Machine Index, %				98.7			104.3			128.8				114.5	

TABLE XV
 SUMMARY OF TEST RESULTS FOR MACHINE M

November, 1956

Code	Date Made	Date Recd.	Mill Roll No.	Basis Weight, lb. per 1000 sq. ft.	Caliper, points		Concora Flat Crush, P.S.I.		Single-Face Flat Crush, P.S.I.		Runability			
					Max.	Min.	Max.	Min.	Max.	Min.		Max.	Min.	Av.
M-1	10-23-56	11-2-56	84	30.1	11.0	10.0	10.5	37.8	33.0	35.2	37.0	35.4	36.2	Satisfactory at 600 f.p.m. Satisfactory at 450 f.p.m.
M-2	--	11-9-56	85	28.5	10.6	9.9	10.2	43.2	37.8	40.3	40.0	39.0	39.6	
Current Machine Average				29.3			10.4			37.7			37.9	
Cumulative Machine Average				28.3			10.5			29.7			31.1	
Machine Factor, %				103.5			99.0			127.1			122.0	
Machine Index, %				108.0			99.9			113.8			109.9	