

SCRAMBLED CODE LETTERS FOR PROGRESS REPORT 64, PROJECT
1108-17

Company - Mill	Machine No.	Code Letter
The Chesapeake Corporation - West Point	1	--
Continental Can Company, Inc. - Hopewell	1	D
Crown Zellerbach Corporation - Baltimore	1	J
- Baltimore	2	K
- Bogalusa	4	B
- Dresden	1	Q
- Lebanon	2	G
International Paper Company - Bastrop	1	F
- Bastrop	2	--
-Georgetown	1	O
- Georgetown	2	--
The Mead Corporation - Harriman	1	H
- Knoxville	1	--
- Lynchburg	2	E
- Sylva	1	R
Muskingum Fibre Products Company - Coshocton	1	C
North Carolina Pulp Company - Plymouth	3	P
Olin Mathieson Chemical Corporation - Monroe	1	--
- Monroe	2	--
Owens-Illinois Glass Company - Tomahawk	1	L
- Tomahawk	2	M
- Tomahawk	3	N
- Big Island	1	--
- Big Island	2	--
- Big Island	3	S
St. Joe Paper Company - Port St. Joe	1	A
Union Bag-Camp Paper Corporation - Savannah	2	I
West Virginia Pulp and Paper Company - Covington	6	--
- Covington	7	--
- Charleston	--	--

THE INSTITUTE OF PAPER CHEMISTRY

Appleton, Wisconsin

SUPPLEMENTARY REPORT ON CALIPER OF SINGLE-FACED
BOARD

Project 1108-17

Progress Report 64

to

FOURDRINIER KRAFT BOARD INSTITUTE, INC.

April 1, 1960

THE INSTITUTE OF PAPER CHEMISTRY

Appleton, Wisconsin

This report is supplementary to Progress Report 63 of the baseline study on corrugating medium entitled, "Continuous evaluation of corrugating medium" which provides a program whereby participating mills have the opportunity to submit rolls of medium on a regular weekly schedule for evaluation with regard to physical characteristics of the medium and of the single-faced board made from the medium. Specifically, each medium is evaluated for caliper, basis weight, and Concora flat crush. In addition each medium is fabricated into A-flute single -faced corrugated board on the Institute's corrugator to determine its runability in terms of speed and tension, and the single-faced board obtained at maximum speed with minimum tension is evaluated for its flat crush strength.

This report is an extension of the baseline study described above and is concerned specifically with the caliper and uniformity of caliper of the single-faced board fabricated from each roll of medium. Uniformity of caliper is generally considered to be another facet of the criteria used to evaluate the runability of corrugating medium, and the Technical Committee of the Fourdrinier Kraft Board Institute, Inc., has requested that a measurement of the uniformity of caliper be included as a part of the evaluation given each roll of corrugating medium.

The evaluation of the caliper and uniformity of caliper of the single-faced board made from each roll of corrugating medium was carried out using the five circular specimens that were subsequently tested for flat crush strength. Each specimen was five square inches in area. They were cut at intervals of approximately two feet along the central portion

of a strip of the single-faced board fabricated at maximum speed and minimum tension. On each of these five specimens, caliper measurements were made on five consecutive flutes and the caliper difference between consecutive flutes was calculated, there being four calculations of differences for each specimen. The twenty-five caliper measurements (five calipers on each of the five specimens) were averaged and are reported as the caliper for each sample of medium. Likewise, the twenty caliper differences between consecutive flutes (four caliper differences on each of the five specimens) were averaged, and the maximum, minimum, and average values are reported for each sample of corrugating medium.

The instrument for measuring the caliper of individual flutes of single-faced board consists of a bench-type thickness gage with a presser foot $\frac{3}{8}$ inch in diameter and an anvil consisting of a plane circular surface 2 inches in diameter. The presser foot is attached to a dial indicator which can be read to 0.0001 inch. The load on the presser foot is 100 ± 10 grams. A caliper determination is made by inserting each five-square-inch circular specimen between the presser foot and the anvil so that the foot rests on the second flute from one end of the specimen without touching either of the adjacent flutes. The $\frac{3}{8}$ -inch diameter of the presser foot permits it to contact only one flute with ease. The specimen is pressed gently against the anvil, and the reading is then recorded. As mentioned previously, five consecutive flutes through the center of each specimen are calipered in this way. It should be emphasized that these calipers may not necessarily correspond to regular caliper measurements because of differences in load and other variables.

Caliper data have been obtained on the single-faced board fabricated from each of the hundred and eleven rolls of corrugating medium which were submitted for evaluation during the month of March. Also included for purposes of convenient reference are the single-face flat crush and runability data. The current machine averages for each test are summarized in Table I for Machines A through S. A graphical presentation of the current machine caliper averages on single-faced board is shown in Figure 1, and a similar presentation of the current machine averages for the caliper difference between consecutive flutes is given in Figure 2. The test results obtained on the individual rolls of medium submitted by each company are given in Tables II through XX for Machines A through S, respectively.

It may be seen in Figure 1 and Table I that the average caliper results for the single-faced boards varied from a low value of 193.5 points for Machine K to a high value of 199.4 points for Machines E and R. Likewise, from the results given in Table I and Figure 2, it may be noted that the average caliper difference between consecutive flutes ranged from a minimum of 0.9 points for Machine P to a maximum of 3.6 points for Machine A. The majority of the machines were associated with average caliper differences of less than 2.5 points. The differences which exceeded three points may be excessive.

TABLE I
SUMMARY OF CURRENT MACHINE AVERAGES
March, 1960

Machine	Number of Rolls	Caliper, points	Caliper Difference Between Consecutive Flutes, points	Single-Face Flat Crush, p.s.i.
A	4	197.8	3.6	29.0
B	7	197.7	2.7	30.5
C	9	198.8	3.2	31.2
D	9	197.6	1.7	31.7
E	4	199.4	1.8	31.0
F	8	195.7	1.6	34.9
G	1	197.9	2.2	30.0
H	4	199.2	1.8	28.5
I	8	198.1	2.1	31.3
J	4	196.2	2.0	30.0
K	6	193.5	2.3	34.8
L	8	197.9	2.0	33.7
M	8	198.7	1.6	32.3
N	8	198.3	2.2	33.9
O	8	197.6	2.5	35.0
P	1	194.7	0.9	35.4
Q	8	196.4	3.0	32.0
R	4	199.4	2.0	31.8
S	2	196.4	1.8	34.9
Total	111			

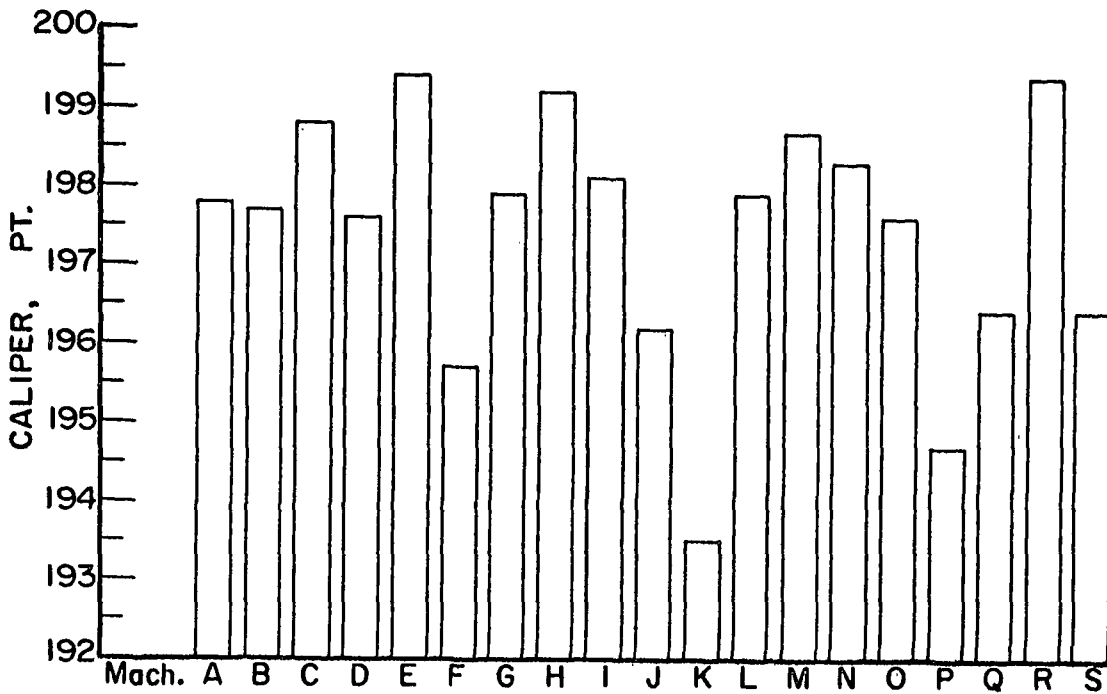


Figure 1

Comparison of Caliper Results on Single-Faced Board
March, 1960

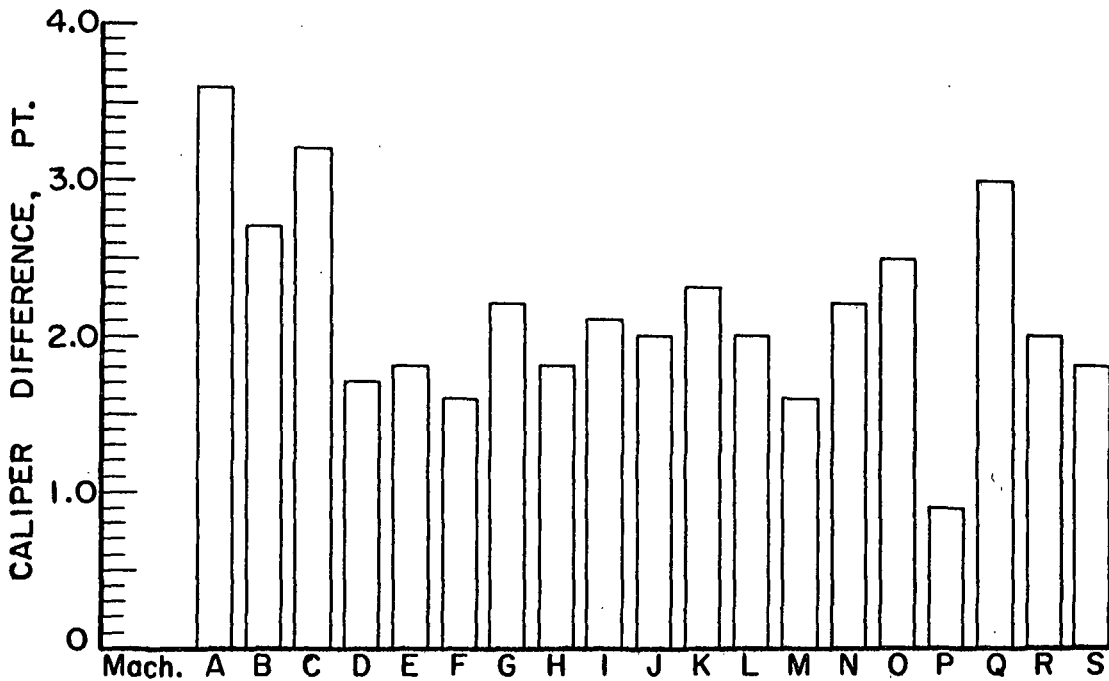


Figure 2

Comparison of the Caliper Differences Between Consecutive
Flutes of Single-Faced Board
March, 1960

TABLE II

SUMMARY OF TEST RESULTS FOR MACHINE A
 March, 1960

Code	Date Made	Mill Roll No.	Cali- per, pt.	Caliper Difference Between Consecu- tive Flutes, points			Single-Face Flat Crush, p.s.i.	Runability (Maximum Ten- sion at 600 f.p.m.), lb./in.
				Max.	Min.	Av.		
A-1	2-10-60	5	197.4	6.9	0.6	3.9	30.5	1/2
A-2	2-10-60	6	196.7	6.6	0.5	3.3	31.1	1/2
A-3	2-29-60	7	198.3	6.4	1.1	3.5	27.9	1-1/2
A-4	2-29-60	8	198.9	6.6	0.1	3.8	26.4	1-1/2
Current Machine Av.			197.8			3.6	29.0	

TABLE III

SUMMARY OF TEST RESULTS FOR MACHINE B
 March, 1960

B-1	2- 9-60	31	197.6	7.4	0.5	3.0	33.2	1-1/2
B-2	2-14-60	32	200.0	8.3	0.0	3.1	32.0	1
B-3	2-17-60	33	197.8	5.8	0.1	2.1	28.2	1-1/2
B-4	2-23-60	34	195.8	6.5	0.0	3.1	29.2	1
B-5	3- 3-60	35	196.6	6.5	0.0	2.0	30.0	1-1/2
B-6	3-11-60	36	198.6	7.0	0.0	3.0	28.7	1-1/2
B-7	3-17-60	37	197.7	5.7	0.2	2.5	32.1	1-1/2
Current Machine Av.			197.7			2.7	30.5	

TABLE IV
 SUMMARY OF TEST RESULTS FOR MACHINE C
 March, 1960

Code	Date Made	Mill Roll No.	Caliper, pt.	Caliper Difference Between Consecutive Flutes, points			Single-Face Flat Crush, p.s.i.	Runability (Maximum Tension at 600 f.p.m.), lb./in.
				Max.	Min.	Avg.		
C-1	2-17-60	309	198.9	6.9	0.2	2.9	28.8	1-1/2
C-2	2-19-60	310	199.4	9.0	1.3	4.3	31.8	1-1/2
C-3	2-22-60	311	198.6	7.1	0.0	2.4	30.8	1-1/2
C-4	2-24-60	312	198.8	6.5	0.1	2.1	30.4	1-1/2
C-5	3- 2-60	313	198.8	8.1	0.1	4.2	31.8	1-1/2
C-6	3- 4-60	314	199.0	7.9	0.1	3.2	31.7	1-1/2
C-7	3- 9-60	315	199.0	9.2	0.1	3.9	32.2	1-1/2
C-8	3-11-60	316	198.8	9.0	0.3	3.9	32.4	1-1/2
C-9	3-13-60	317	198.1	5.3	0.0	2.2	31.4	1-1/2
Current Machine Av.			198.8			3.2	31.2	

TABLE V
 SUMMARY OF TEST RESULTS FOR MACHINE D
 March, 1960

D-1	2- 9-60	242	197.4	3.4	0.1	1.6	31.9	1/2
D-2	2-11-60	243	197.5	3.5	0.0	1.4	31.8	1-1/2
D-3	2-15-60	244	198.0	3.6	0.2	1.4	31.6	1-1/2
D-4	2-19-60	245	197.8	5.2	0.2	1.9	32.7	1
D-5	2-22-60	246	198.1	5.5	0.0	1.7	30.6	1/2
D-6	2-26-60	247	198.6	4.9	0.2	2.6	31.6	1-1/2
D-7	2-29-60	248	198.0	3.2	0.1	1.4	32.0	1-1/2
D-8	3- 3-60	249	196.5	4.7	0.3	2.0	30.6	1-1/2
D-9	3- 5-60	250	196.9	5.6	0.1	1.6	32.4	1-1/2
Current Machine Av.			197.6			1.7	31.7	

TABLE VI

SUMMARY OF TEST RESULTS FOR MACHINE E
 March, 1960

Code	Date Made	Mill Roll No.	Caliper, pt.	Caliper Difference Between Consecutive Flutes, points			Single-Face Flat Crush, p.s.i.	Runability (Maximum Tension at 600 f.p.m.), lb./in.
				Max.	Min.	Av.		
E-1	2-19-60	261	199.1	7.0	0.4	2.3	29.8	1-1/2
E-2	2-19-60	262	198.7	5.5	0.1	1.4	29.0	1-1/2
E-3	3- 9-60	269	199.7	5.0	0.0	2.0	31.2	1-1/2
E-4	3- 9-60	270	200.0	6.0	0.2	1.7	34.1	1-1/2
Current Machine Av.			199.4			1.8	31.0	

TABLE VII

SUMMARY OF TEST RESULTS FOR MACHINE F
 March, 1960

F-1	2-22-60	545	194.9	4.7	0.1	2.0	34.2	1-1/2
F-2	2-25-60	546	195.7	6.3	0.5	2.4	39.5	1-1/2
F-3	3- 1-60	547	195.6	6.2	0.0	1.6	35.8	1-1/2
F-4	3- 4-60	548	196.0	2.9	0.2	1.1	34.8	1-1/2
F-5	3- 8-60	549	196.3	3.5	0.0	1.4	35.0	1-1/2
F-6	3-11-60	550	196.5	3.4	0.0	1.5	34.0	1-1/2
F-7	3-17-60	551	195.4	2.6	0.0	1.2	32.6	1-1/2
F-8	3-22-60	552	195.4	4.4	0.0	1.8	33.5	1-1/2
Current Machine Av.			195.7			1.6	34.9	

TABLE VIII

SUMMARY OF TEST RESULTS FOR MACHINE G
 March, 1960

Code	Date Made	Mill Roll No.	Caliper, pt.	Caliper Difference Between Consecutive Flutes, points			Single-Face Flat Crush, p.s.i.	Runability (Maximum Tension at 600 f.p.m.), lb./in.
				Max.	Min.	Av.		
G-1	2- 6-60	4	197.9	5.4	0.0	2.2	30.0	1-1/2
Current Machine Av.			197.9			2.2	30.0	

TABLE IX

SUMMARY OF TEST RESULTS FOR MACHINE H
 March, 1960

H-1	2-24-60	265	201.6	3.5	0.4	2.0	27.8	1-1/2
H-2	2-24-60	266	200.1	4.9	0.1	2.1	30.8	1-1/2
H-3	3- 8-60	273	197.3	3.8	0.0	1.5	27.3	1-1/2
H-4	3- 8-60	274	197.6	4.7	0.0	1.5	28.1	1-1/2
Current Machine Av.			199.2			1.8	28.5	

TABLE X

SUMMARY OF TEST RESULTS FOR MACHINE I
 March, 1960

Code	Date Made	Mill Roll No.	Caliper, pt.	Caliper Difference Between Consecutive Flutes, points			Single-Face Flat Crush, p.s.i.	Runability (Maximum Tension at 600 f.p.m.), lb./in.
				Max.	Min.	Av.		
I-1	2-20-60	348	197.9	4.1	0.1	1.7	32.8	1-1/2
I-2	2-22-60	349	199.5	4.2	0.2	1.9	31.4	1-1/2
I-3	2-26-60	350	198.2	3.8	0.2	1.5	31.5	1-1/2
I-4	3- 2-60	351	198.6	5.8	0.0	2.6	30.8	1-1/2
I-5	3- 4-60	352	197.2	2.8	0.2	1.4	30.5	1/2
I-6	3-13-60	353	197.8	6.7	0.2	3.2	30.5	1
I-7	3-14-60	354	198.2	4.8	0.4	2.2	29.7	1/2
I-8	3-17-60	355	197.6	5.5	0.0	2.6	33.4	1-1/2
Current Machine Av.			198.1			2.1	31.3	

TABLE XI

SUMMARY OF TEST RESULTS FOR MACHINE J
 March, 1960

J-1	2-24-60	9	195.0	4.3	0.4	1.9	28.8	1-1/2
J-2	2-25-60	10	195.3	4.4	0.3	2.0	30.1	1-1/2
J-3	3- 3-60	11	197.3	6.8	0.0	1.9	29.4	1-1/2
J-4	3- 4-60	12	197.4	4.6	0.0	2.1	31.5	1-1/2
Current Machine Av.			196.2			2.0	30.0	

TABLE XII

SUMMARY OF TEST RESULTS FOR MACHINE K
 March, 1960

Code	Date Made	Mill Roll No.	Caliper, pt.	Caliper Difference Between Consecutive Flutes, points			Single-Face Flat Crush, p.s.i.	Runability (Max. Tension at 600 f.p.m.), lb./in.
				Max.	Min.	Ave.		
K-1	2-19-60	7	193.7	3.9	0.1	1.4	33.8	1-1/2
K-2	2-19-60	8	191.2	6.1	0.3	3.1	32.6	1-1/2
K-3	2-24-60	9	192.4	6.8	0.1	2.0	35.2	1-1/2
K-4	2-25-60	10	194.6	7.6	0.0	3.6	37.2	1-1/2
K-5	3- 8-60	11	194.7	4.3	0.0	1.9	35.1	1-1/2
K-6	3- 9-60	12	194.3	4.3	0.0	1.8	34.8	1-1/2
Current Machine Av.			193.5			2.3	34.8	

TABLE XIII

SUMMARY OF TEST RESULTS FOR MACHINE L
 March, 1960

L-1	2-22-60	--	198.4	4.5	0.1	2.2	35.4	1-1/2
L-2	2-26-60	--	198.7	5.4	0.1	2.6	33.9	1-1/2
L-3	2-29-60	--	198.1	4.4	0.5	2.4	34.2	1-1/2
L-4	3- 5-60	--	198.4	4.8	0.4	2.3	32.0	1-1/2
L-5	3- 7-60	--	198.7	2.7	0.0	1.4	33.5	1-1/2
L-6	3-10-60	--	195.8	4.0	0.2	1.9	32.5	1-1/2
L-7	3-14-60	--	197.7	4.8	0.1	2.3	34.6	1-1/2
L-8	3-17-60	--	197.4	3.8	0.0	1.2	33.3	1-1/2
Current Machine Av.			197.9			2.0	33.7	

TABLE XIV

SUMMARY OF TEST RESULTS FOR MACHINE M
 March, 1960

Code	Date Made	Mill Roll No.	Caliper, pt.	Caliper Difference Between Consecutive Flutes, points			Single-Face Flat Crush, p.s.i.	Runability (Max. Tension at 600 f.p.m.), lb./in.
				Max.	Min.	Avg.		
M-1	2-23-60	---	199.2	3.7	0.0	1.4	32.2	1-1/2
M-2	2-26-60	---	198.6	4.6	0.0	1.6	33.2	1-1/2
M-3	3- 2-60	---	199.3	4.1	0.0	1.4	35.6	1
M-4	3- 4-60	---	198.4	4.2	0.0	1.3	30.8	1-1/2
M-5	3- 8-60	---	199.4	3.2	0.1	1.2	33.3	1-1/2
M-6	3-11-60	---	199.2	5.4	0.1	2.3	29.5	1-1/2
M-7	3-15-60	---	197.7	5.7	0.0	2.4	32.0	1-1/2
M-8	3-19-60	---	198.0	3.8	0.0	1.5	31.6	1-1/2
Current Machine Av.			198.7			1.6	32.3	

TABLE XV

SUMMARY OF TEST RESULTS FOR MACHINE N
 March, 1960

N-1	2-24-60	---	198.4	5.4	0.0	2.3	34.2	1-1/2
N-2	2-27-60	---	199.4	6.5	0.0	1.8	33.7	1-1/2
N-3	3- 3-60	---	196.3	4.6	0.0	1.6	36.9	1/2
N-4	3- 5-60	---	198.4	4.0	0.4	1.8	35.8	1-1/2
N-5	3- 9-60	---	197.7	5.8	0.3	3.6	31.7	1
N-6	3-12-60	---	198.7	6.2	0.0	2.5	33.8	1-1/2
N-7	3-16-60	---	199.0	6.4	0.0	1.9	31.9	1-1/2
N-8	3-19-60	---	198.3	4.1	0.1	2.1	33.4	1-1/2
Current Machine Av.			198.3			2.2	33.9	

TABLE XVI

SUMMARY OF TEST RESULTS FOR MACHINE O
 March, 1960

Code	Date Made	Mill Roll No.	Caliper, pt.	Caliper Difference Between Consecutive Flutes, points			Single-Face Flat Crush, p.s.i.	Runability (Max. Tension at 600 f.p.m.), lb./in.
				Max.	Min.	Av.		
0-1	2-17-60	383	197.6	3.5	0.1	1.7	34.3	1-1/2
0-2	2-23-60	384	198.8	6.0	0.0	2.3	33.8	1
0-3	2-26-60	385	196.4	8.7	1.0	4.2	38.4	1
0-4	3- 1-60	386	199.1	4.0	0.3	1.8	33.7	1-1/2
0-5	3- 3-60	387	198.8	4.6	0.2	2.1	33.6	1-1/2
0-6	3- 8-60	388	196.2	3.5	0.0	1.2	36.7	1-1/2
0-7	3-12-60	389	197.3	6.9	1.0	4.5	33.8	1-1/2
0-8	3-15-60	390	196.8	3.5	0.2	2.1	35.8	1-1/2
Current Machine Av.			197.6			2.5	35.0	

TABLE XVII

SUMMARY OF TEST RESULTS FOR MACHINE P
 March, 1960

P-1	2- 7-60	192	194.7	2.1	0.0	0.9	35.4	1/2
Current Machine Av.			194.7			0.9	35.4	

TABLE XVIII

SUMMARY OF TEST RESULTS FOR MACHINE Q
March, 1960

Code	Date Made	Mill Roll No.	Caliper, pt.	Caliper Difference Between Consecutive Flutes, points			Single-Face Flat Crush, p.s.i.	Runability (Max. tension at 600 f.p.m.), lb./in.
				Max.	Min.	Av.		
Q-1	2-23-60	21	198.1	11.0	0.4	4.0	31.0	1-1/2
Q-2	2-26-60	22	196.7	4.7	0.0	2.1	33.0	1-1/2
Q-3	--	23	197.5	8.6	0.1	3.2	30.4	1-1/2
Q-4	3- 4-60	24	196.8	5.5	0.1	2.3	29.7	1-1/2
Q-5	3- 8-60	25	197.0	7.6	0.0	2.9	33.0	1-1/2
Q-6	3-11-60	26	194.8	7.0	0.4	3.3	33.6	1-1/2
Q-7	3-16-60	27	195.2	7.5	1.1	3.9	34.0	1-1/2
Q-8	3-18-60	28	195.5	4.8	0.0	1.9	31.5	1-1/2
Current Machine Av.			196.4			3.0	32.0	

TABLE XIX

SUMMARY OF TEST RESULTS FOR MACHINE R
March, 1960

R-1	3- 3-60	269	199.6	6.0	0.3	2.6	31.5	1-1/2
R-2	3- 3-60	270	199.7	2.9	0.1	1.1	30.9	1-1/2
R-3	3-17-60	277	199.1	6.0	0.2	2.9	31.8	1-1/2
R-4	3-17-60	278	199.1	3.0	0.1	1.4	33.1	1-1/2
Current Machine Av.			199.4			2.0	31.8	

TABLE XX

SUMMARY OF TEST RESULTS FOR MACHINE S
March, 1960

S-1	2-18-60	2286	196.9	3.4	0.0	1.2	33.1	1
S-2	2-22-60	3135	195.9	6.6	0.0	2.4	36.7	1/2
Current Machine Av.			196.4			1.8	34.9	

THE INSTITUTE OF PAPER CHEMISTRY

W. N. Hubert

W. N. Hubert, Research Aide
Container Section

R. C. McKee

R. C. McKee, Chief, Container Section